



City Research Online

City, University of London Institutional Repository

Citation: Ous, T. & Arcoumanis, C. (2013). Degradation aspects of water formation and transport in Proton Exchange Membrane Fuel Cell: A review. *Journal of Power Sources*, 240, pp. 558-582. doi: 10.1016/j.jpowsour.2013.04.044

This is the accepted version of the paper.

This version of the publication may differ from the final published version.

Permanent repository link: <https://openaccess.city.ac.uk/id/eprint/6495/>

Link to published version: <https://doi.org/10.1016/j.jpowsour.2013.04.044>

Copyright: City Research Online aims to make research outputs of City, University of London available to a wider audience. Copyright and Moral Rights remain with the author(s) and/or copyright holders. URLs from City Research Online may be freely distributed and linked to.

Reuse: Copies of full items can be used for personal research or study, educational, or not-for-profit purposes without prior permission or charge. Provided that the authors, title and full bibliographic details are credited, a hyperlink and/or URL is given for the original metadata page and the content is not changed in any way.

Degradation aspects of water formation and transport in PEMFC: A review

T. Ous¹ and C. Arcoumanis²

^{1,2}School of Engineering and Mathematical Sciences, City University London, Northampton Square, London EC1V 0HB, United Kingdom

(t.ous@city.ac.uk)¹,(C.Arcoumanis@city.c.uk)²

Abstract

This review paper summarises the key aspects of Proton Exchange Membrane Fuel Cell (PEMFC) degradation that are associated with water formation, retention, accumulation, and transport mechanisms within the cell. Issues related to loss of active surface area of the catalyst, ionomer dissolution, membrane swelling, ice formation, corrosion, and contamination are also addressed and discussed. The impact of each of these water mechanisms on cell performance and durability was found to be different and to vary according to the design of the cell and its operating conditions. For example, the presence of liquid water within Membrane Electrode Assembly (MEA), as a result of water accumulation, can be detrimental if the operating temperature of the cell drops to sub-freezing. The volume expansion of liquid water due to ice formation can damage the morphology of different parts of the cell and may shorten its life-time. This can be more serious, for example, during the water transport mechanism where migration of Pt particles from the catalyst may take place after detachment from the carbon support. Furthermore, the effect of transport mechanism could be augmented if humid reactant gases containing impurities poison the membrane, leading to the same outcome as water retention or accumulation.

Overall, the impact of water mechanisms can be classified as aging or catastrophic. Aging has a long-term impact over the duration of the PEMFC life-time whereas in the catastrophic mechanism the impact is immediate. The conversion of cell residual water into ice at sub-freezing temperatures by the water retention/ accumulation mechanism and the access of poisoning contaminants through the water transport mechanism are considered to fall into the catastrophic category. The effect of water mechanisms on PEMFC degradation can be reduced or even eliminated by (a) using advanced materials for improving the electrical, chemical and mechanical stability of the cell components against deterioration, and (b) implementing effective strategies for water management in the cell.

Keywords: PEMFC; water management; degradation; water formation and transport; flooding; ice formation

Contents

1.	Introduction	3
2.	Water distribution and transport in PEMFC	5
3.	Water production	11
3.1.	Catalyst deterioration	12
3.1.1.	Pt and ionomer dissolution	12
3.1.2.	Carbon corrosion	13
3.2.	Mitigation strategies	14
4.	Water retention and accumulation	17
4.1.	Water retention	17
4.1.1.	Membrane Swelling	17
4.2.1.	Corrosion	19
4.3.1.	Ice formation	21
4.2.	Water flooding	24
4.3.	Mitigation strategies	25
4.3.1.	Membrane swelling	25
4.3.2.	Corrosion	27
4.3.3.	Ice formation	30
4.3.4.	Flooding	32
5.	Water transport in PEMFC	33
5.1.	MEA and GDL structure	34
5.2.	Contamination	36
5.3.	Mitigation strategies	37
6.	Concluding remarks	38
7.	References	41

1. Introduction

Fuel cells have the potential to resolve the current energy crisis of the 21st century. These electrochemical energy devices convert the chemical energy of hydrogen fuel into electrical energy efficiently [1]. They offer great flexibility in their design which allows them to be in various configurations and to operate with a wide range of hydrocarbon fuels, features that broaden the scope of their applications. Furthermore, the fact that hydrogen is an abundant source gives fuel cells the advantage to be one of the most sustainable solutions for future energy needs.

The commercialisation of fuel cells is mainly affected by their high cost and the lack of a hydrogen infrastructure. Attempts to reduce the cost of fuel cells and to develop a global hydrogen network for their use are still ongoing. The primary focus is to minimise the loading of Platinum (Pt) in the catalyst of the Membrane Electrode Assembly (MEA) which is considered to be the main contributor to the high cost [2]. Some studies have suggested the use of more effective techniques for Pt deposition onto the catalyst to reduce its loading [3-7], others concentrated on enhancing the polarisation performance of the cell to compensate for further Pt reduction [8-10]. Although some studies [11] claimed that reduction of up to 50% (e.g. $0.15 \text{ mg-Pt cm}^{-2}$) is achievable with marginal compromise to the fuel cell stack efficiency (<1%), further reduction is still needed [12]. The manufacturing cost of fuel cell components, particularly the MEA and the Gas Diffusion Layer (GDL), is another significant contributor to the overall cost [2]. An approach which can make them more affordable is to increase the manufacturing volume of fuel cell stacks and to reduce the complexity of the manufacturing processes of some of their components [2]. It is expected that, as fuel cell stacks become commercially viable, hydrogen fuelling infrastructure will be established that is easily accessible for supporting the penetration of fuel cells into the market place [13-14]. This remains a major concern particularly for the transport sector where issues associated with hydrogen production [15-16], safety [17-19], on-board and off-board storage [20-22] have surfaced.

The durability of fuel cells is another obstacle affecting their commercialisation [23]. Currently, PEMFCs can operate for some 2500hrs in transportation [24]. Although this timescale has doubled in recent years, it is still inadequate and may need further doubling (~5000hrs) in order to meet the target for year 2015 aimed by the US Department of Energy (DOE), the Japan's New Energy and Industrial Technology Development Organisation (NEDO), and the European Hydrogen and Fuel Cell Technology Platform (HFP). For stationary applications, the life-time requirement for fuel cells extends to 40,000hrs [25]. The reason for the longer life period in this case is attributed to the fact that the fuel cell load is more stable than under transport conditions. The rapid change in fuel cell load, usually referred to as dynamic load cycling, affects significantly the degradation rate [26] and the life-time expectancy of the cell [27]. Potential load cycling can severely affect the mechanical and chemical properties of the catalyst and its carbon support leading to an early cell failure [28].

Various durability tests were implemented by fuel cell developers in order to predict their life-time under practical operating conditions. Emphasis on developing accelerated life-time tests, also called accelerated stress tests (ASTs), has increased in recent years to prevent the prolonged test periods and high costs associated with real time tests. The results obtained from those accelerated tests were found not to be consistent and to differ considerably from the real lifetime or steady state measurements [28-34]. This is probably expected as measurements were carried out under different operating conditions and for different fuel cell component designs. Furthermore, some durability measurements [35-42] were made of individual components rather than of the complete cell unit. Thus, the effect of degradation on the neighbouring components which consequently affects the life-time of the entire cell will not be represented. This stresses the need for standardised durability protocols which would ensure uniformity between these measurements.

Degradation of PEMFC can be caused by a number of factors associated with the design of the cell and its operation. These factors can be classified into two types: catastrophic and aging. Catastrophic factors are the ones that can cause immediate or early failure in cell performance due to severe mechanical or chemical damage to the cell during operation. The Pinhole formation on the surface of the membrane, for instance, can be very damaging to the cell since it allows reactant gases to cross-over from the anode or the cathode side leading to catalytic combustion and a sudden drop in the cell's power output [43, 44]. Membrane perforations or cracks in the cell components may be the result of impaired design/ fabrication during preparation process, improper cell assembly, or operation of the cell at extremely high pressures and temperatures. Membrane poisoning is another detrimental factor to the lifetime of PEMFC. High concentration levels of impurities such as carbon monoxide (CO) in the reactant gases results in CO adsorption to the platinum surface of the catalyst which blocks the active hydrogen sites [45, 46].

Aging factors represent the natural cause of degradation due to cell electrochemical reaction. Unlike catastrophic, their effects on depleting cell's performance occur gradually. Three phases of voltage drop were identified in the aging process representing stable operation, slow decrease in cell voltage and rapid fall in voltage [47]. The degradation rate is a function of the operational time of the cell and is usually expressed as the drop in microvolt scale per hour of operation (e.g. $\mu\text{V}/\text{hr}$). This rate is strongly dependant on the deterioration rate of the cell's materials such as the change in the mechanical and chemical properties of the catalyst including the loss in electro-catalyst surface area due to growth in the platinum particle size [48, 49], corrosion of platinum-based catalysts [50, 51], and corrosion of carbon support catalyst [52]. A comprehensive review of PEMFC components degradation can be found in [53].

Although deterioration of the material is inevitable, due to the electrochemical nature of the fuel cell reaction, its rate can be minimised. Many attempts were made in the past few years to develop more robust components and operational regimes capable of withstanding harsh fuel cell conditions against degradation. In [54] the design of membranes was suggested to be made thicker to reduce hydrogen

crossover to the cathode. According to [55], sulfonated polyimide membranes exhibit better stability than Nafion under electric load cycling. [56] and [57] found Pt stability in the catalyst to be improved against dissolution by using multiwalled carbon nanotubes (CNTs) and by modifying Pt nanoparticules with gold (Au) clusters. Others [58], [59] have pointed to the effect of carbon film coating on improving the mechanical and electrical properties of gas diffusion layers. In [60] the role of homogeneous coating in controlling the diffusion overvoltage from the gas diffusion layers was revealed. Several other studies [61-66] stressed the importance of coating for bipolar plates to prevent surface corrosion. [67] and [68] suggested to operate PEMFC under low relative humidity (RH) to minimise the loss of Pt active surface area contrary to [48] and [69] which concluded that low RH increases carbon corrosion in the catalyst. Others like [70] suggested reducing RH, temperature and hydrogen pressure during PEMFC operation to suppress the hydrogen cross-over mechanism. The influence of fuel and oxidant starvation [71], open circuit operation [72], excessive air bleeding [73], humidity cycling [74, 75], load-on/off cycling [76], and freeze/thaw cycling [77] on structural changes of the membrane was also demonstrated. A more detailed analysis of the effect of the operating conditions on the PEMFC durability can be found in [78].

Despite all these investigations, very few studies have highlighted the role of water on the degradation of PEMFC. This review paper attempts to focus on the impact of (a) water production during the electrochemical reaction of the cell, (b) water accumulation in the channels and reaction sites and (c) water transport mechanisms on the electrical, mechanical, thermal and chemical/electrochemical deterioration of the PEMFC components.

2. Water distribution and transport

Good water distribution in PEMFC is a recipe for achieving effective water management and enhanced performance of the cell. The ionic conductivity of Nafion is strongly dependant upon the amount of water available in the membrane [79]. The water which is absorbed by the sulphonic acid groups (HSO_3^-) of the membrane due to its hydrophilic characteristic enables H^+ ions to move freely on weakening the attraction force between H^+ and SO_3^- ions [80]. The more water molecules are present in each SO_3^- chain, the better the conductivity of H^+ becomes. Nevertheless, too much water can block the reaction sites of the neighbouring electrodes preventing the access of reactant gases to the cell. Therefore, the amount of water in these two regions must be kept in optimum balance for cell performance.

New materials and designs were developed to maintain this delicate balance. Appropriate loading of oxygen permeable and hydrophobic dimethyl silicone oil (DSO) [81], hygroscopic γ -alumina particles [82], silicon dioxide particles [83, 84] and silica-based composites [85, 86] on the catalyst layer showed improvement in the wettability of the membrane under low humidification conditions. Chao

et al [82] revealed that the addition of only 10% of γ -alumina to the anode catalyst layer is sufficient to increase the wettability and achieve high cell performance. Although with addition of 40% of γ -alumina the wettability increased, which was evident from the decrease in the droplets contact angle with the catalyst surface (109° at 10% and 0° at 40% loading), the polarisation performance of the cell dropped due to flooding. Similar drop in performance, because of flooding, was reported in Jung et al [84] et al when SiO_2 was loaded to the cathode catalyst layer; they found that loading the anode with 40 wt.% of SiO_2 gives the best performance even under 0% relative humidity of the anode.

The use of a micro porous layer (MPL) between the gas diffusion and catalyst layers proved to offer advantages towards flooding in PEMFC. Generally, the water saturates at the interface of the catalyst with GDL [87] due to a sudden change in the pore size of these mated layers [88]. As a result, a water film is formed at the interface region where more space is available to accommodate the accumulated water. To some extent, MPL acts as a barrier limiting the access of water flow to the GDL [89] while facilitating an effective water drainage mechanism [90]. When Yau et al [89] inserted MPL into the MEA design, the back diffusion of water to the anode was enhanced. Eventually, the water cross-over flux from the cathode to the anode was increased (e.g. 33.7% with MPL versus 27.4% without MPL at $\text{RH}_c=26\%$ and $\text{RH}_a=75\%$ respectively) indicating less passage of water to the GDL micro-channels.

Coating MPL with hydrophobic substances such as fluorinated ethylene propylene (FEP) [91], polytetrafluoroethylene (PTFE) [92, 93], or with copolymer containing hydrophilic functional groups [94] and composite carbon black [95], has been suggested as an effective strategy for managing water transport within the cell. The improvement in cell polarisation [91] was clearly due to the change in FEP loading (e.g. 30% FEP loading by screen-printed technique) which served to expel excessive product water. The increase in PTFE and carbon loading tends to reduce water diffusion into the GDL channels [92, 96]. When the PTFE loading on MPL increased from 0 to 40wt%, the water flux across the GDL was reduced by almost 30% under an air flow rate of 4SLPM (0.75g/min to 0.55g/min) [92]. Furthermore, increasing the amount of PTFE in the MPLs makes the in-plane permeability within the GDL higher [93]. Different carbon materials for MPL were examined including acetylene black, composite carbon black (80 wt.% acetylene black + 20 wt.% black pearls 2000) and black pearls 2000 [95]. The cell with the composite carbon material exhibited the best performance. Their polarisation measurements were supported by Scanning Electron Microscopy (SEM) observation of MPL structure. The images showed formation of bi-functional pores on the surface which facilitated the transport of both reactants and liquid water.

Similarly, the change of MPL morphology with respect to the pore size diameter, layer thickness [97] and surface roughness [98] has an effect on water mass transfer and local transport. In [98] the importance of MPL surface roughness towards water transport at the interfacial region of MPL/catalyst (CL) was highlighted. The role of surface roughness becomes more pronounced under compressive conditions where interfacial gabs and macro-cracks can be formed. Their optical profilometry measurements revealed that cracks on the MPL surface occur at random locations and in

various magnitudes to the extent that they can be as deep as the entire thickness of the MPL. Figure 1 shows a cross-sectional SEM image of a cracked MPL where a large-size channel was created across the layer enabling easy passage for the water flow.

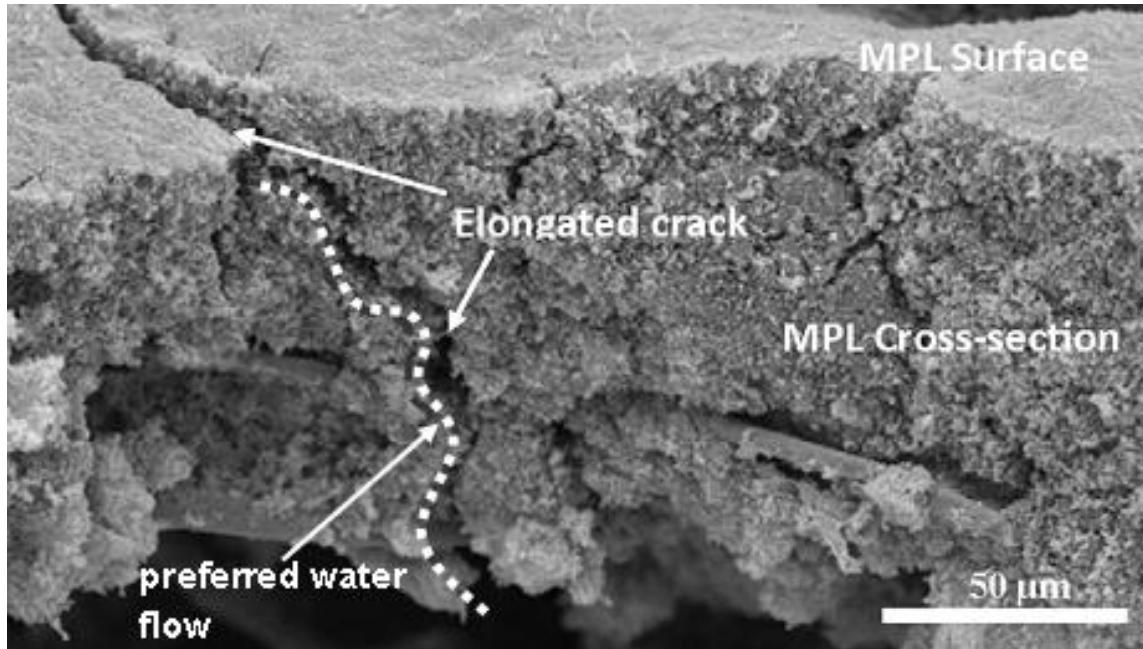


Figure 1 (a) Cross-sectional SEM image of MPL of SGL 10BB type h (Reproduced from [98] with permission)

Under low humidification conditions when maintaining full hydration of the membrane is arduous, the size of MPL pores is kept minimal in order to restrict the flow of by-product water to GDL and avoid drying up the membrane [99]. Kitahara et al [99] were able to improve cell performance under 0% RH of reactant air when they reduced the mean pore diameter of MPL from 10 to 1 μm . At a cell voltage of 0.4V, the current density was almost doubled. On the contrary, to get rid of the liquid water under high humidity conditions, MPL's porosity need to be increased and its thickness reduced [100]. The simulations presented in [100] showed that by increasing the MPL porosity from 0.2 to 0.5, the liquid water flux through the GDL can increase by around 9 times (e.g. at a porosity of 0.5, the flux was $4.505 \times 10^{-3} \text{ kg s}^{-1} \text{ m}^{-2}$).

More advanced designs were developed such as graded-porosity type MPL (GMPL) where porosity decreases from the inner layer MPL/membrane to the outer layer MPL/GDL to facilitate the transport of liquid water through larger pores and gas diffusion via small pores [101]. Another design was a GDL modified hydrophobic/hydrophilic double micro porous layer (GDBL) that contains a hydrophobic MPL on the surface of the GDL and a hydrophilic MPL in the middle acting as an internal humidifier due to its water adsorption ability [102].

Despite all these modifications in the design of MEA, the effect of the cell operating conditions on water distribution and transport remains most pronounced. Operating PEMFC with high relative

humidity gases increases the risk of flooding in the cell [103, 104]. They showed that cathode channels become more flooded with liquid water as RH of reactant air increases from 26% to 66% for the same current density (e.g. 0.8A. cm^{-2}) [103]. When they operated the cell with dry air of 26% RH, liquid water was visible in the channels only when the stoichiometric air flow was set to 2.5 and below. Meanwhile with 66% RH of air, water was still present even at higher stoichiometric values. Generally, flooding can be prevented by running the cell with high stoichiometric flow rates [105] or elevated temperatures [106, 107, 108]. Ous and Arcoumanis [107] found that flooding in the cathode channels can be overcome by raising the temperature from 30°C to 60°C under the testing conditions shown in Figure 2. The benefit of using heat as a mechanism for water extraction from the cell can be extended to the polarisation performance of the cell. Increasing the operating temperature of the cell enhances the rates of electrochemical kinetics of the catalyst [109-111]. In [109] an explanation was given of how high temperatures affect the electrode reversible potential (thermodynamic open circuit voltage), Tafel slope, and exchange current density. At temperatures above 100°C , the reduction in the electrode reversible potential is less due to the change in the reaction entropy (e.g. gaseous reactants are converted to gaseous product instead of liquid). To be noted is the improvement with temperature in the exchange current density and Tafel slope for both hydrogen oxidation reaction (HOR) and oxygen reduction reaction (ORR).

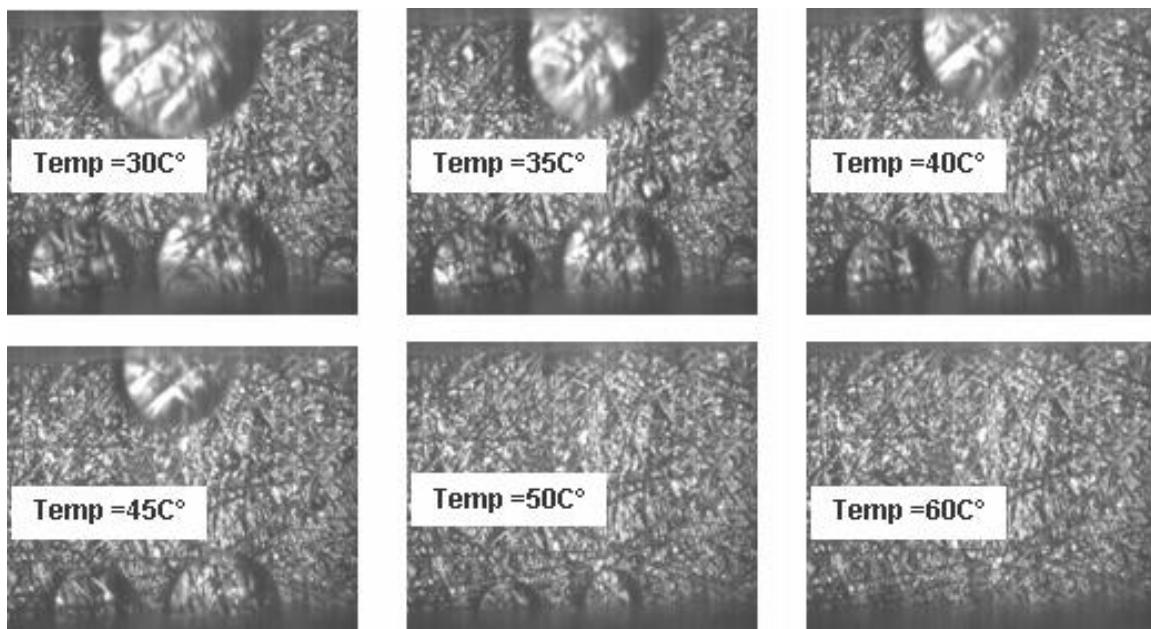


Figure 2 Images of water accumulation in the cathode flow channels for different fuel cell operating temperatures [107]

Currently, major research activities are focusing on the development of next generation membranes that can operate efficiently at high operating temperatures ($\geq 100^\circ\text{C}$) [112-120]. If successful, issues related to water management, cooling, CO tolerance of the cell etc will be much simplified [109, 121].

Further development of these high temperature membranes is required to extend their limited life-time and durability beyond 1000hrs [122-124]. The phosphoric acid-doped polybenzimidazole electrolyte high-temperature membranes presented in [122] was able to operate only for 1220hrs despite the low current density (0.2Acm^{-2}). When they tested the cell under 190°C , the cell voltage started to drop significantly after 1000hrs of operation and by 1220hrs the voltage was zero. The same type of membranes was examined in [123]; considerable hydrogen cross-over was reported after 510hrs of continuous testing at 714mAcm^{-2} followed by 90hrs of intermittent testing at 0.3Acm^{-2} which was due to the physical degradation of these membranes including agglomeration of the electro-catalysts and membrane thinning.

A number of visualisation techniques were applied to monitor the water distribution and transport in different parts of PEMFC including fluorescence microscopy [125], Environmental Scanning Electron Microscope (ESEM) [88, 126], X-Ray radiography [127-133], X-Ray tomography [134], neutron radiography [135-137], magnetic resonance [138], and video cameras [139-143]. An overview of these experimental techniques can be found in [144, 145]. Similarly, several two-dimensional and three-dimensional based models were developed to simulate the multiphase flow of gas and/or liquid water in the membrane [146-148], GDL [149-154], CL/MPL/GDL structure [155, 156], and cathode gas flow channels [157-160]. These studies have provided detailed understanding of in-plane and through-plane water accumulation and transport within these micro porous layers.

The water produced by the cell appears first at the catalyst layer of the cathode where oxygen reduction reaction (ORR) takes place. Depending on the hydration state of the membrane, water can either travel to the electrolyte to support the back diffusion stream or in the opposite direction towards MPL. Due to the hydrophobic nature of MPL, the formation of water films at the catalyst will be prevented and the access of product water to GDL will be limited [131]. The X-ray visualisation of [131] showed high-resolution cross-sectional images (with spatial resolution of $0.8\text{ }\mu\text{m}$) of water in-situ distribution for two types of GDLs, with and without MPL. From these images, it can be seen that water saturation in the GDL without MPL (Figure 3a) was significantly higher than the one with added MPL (Figure 3b). In the later case, water droplets appeared on the surface of the GDL because of the highly hydrophobic MPL.

The water in the GDL is subject to viscous, capillary and gravitational forces. The fact that the capillary number (the ratio of viscous forces to interfacial tension forces) is relatively small, implies that water transport in GDL is dominated by capillary diffusion. The simulations of [154] using mean value model (MVM) confirmed that the capillary force is the main mechanism to drive the water flux within the GDL.

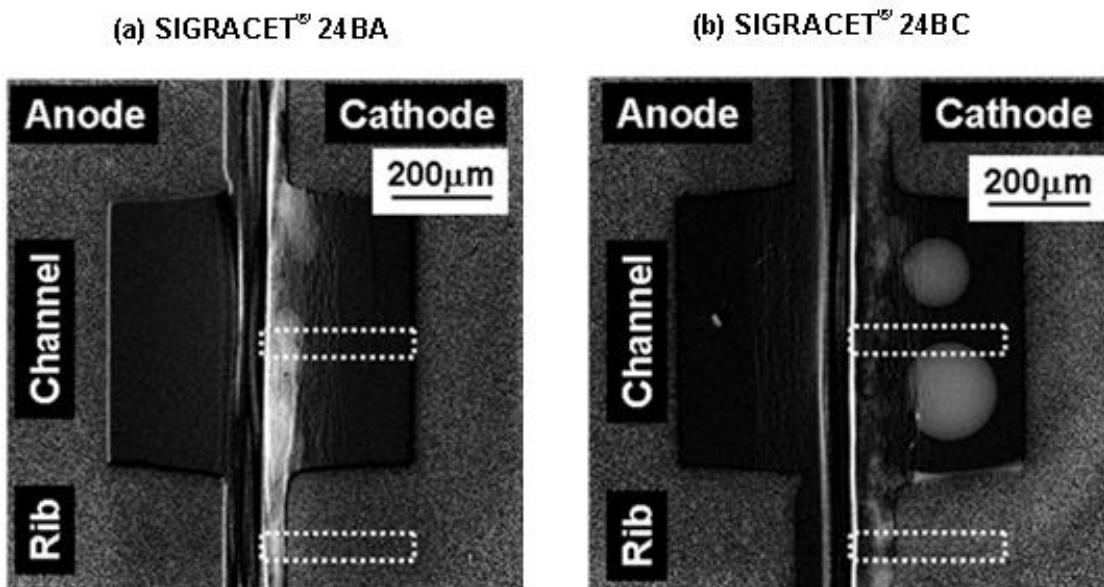


Figure 3 Cross-sectional images of water accumulation under channel and rib area at current density of 0.8 Acm^{-2} for (a) SIGRACET® 24BA; and (b) SIGRACET® 24BC h (Reproduced from [131] with permission)

The distribution of the liquid water is strongly affected by the geometry of the GDL structure [150] and weakly by the cross leakage gas flow streams [136]. Water tends to accumulate initially more under ribs or lands than under channels [130, 131, 149, 153] which is probably expected since air will have less access and longer diffusion length to reach those regions and remove liquid water. The images captured by [131] and presented in Figures 4a and 4b show clearly higher concentration of liquid water under the rib area for the two types of GDLs, with and without MPL, at a current density of 0.4 Acm^{-2} . Water starts to build up close to the channel walls forming liquid films as a result of the hydrophilic capillary force of the walls and the drag force of the gas flow in the flow channels [143]. As water continues to penetrate the GDL, particularly at high current densities, the water accumulated under the channel regions travels first towards the air flow channels [156] developing on the surface as droplets [131, 142]. Figures 3a and 3b illustrate how by increasing the current density to 0.8 Acm^{-2} the GDL without MPL (24BA type) becomes flooded with liquid water whereas the addition of MPL (24BC type) leads to droplets appearing on the surface of the cathode channels.

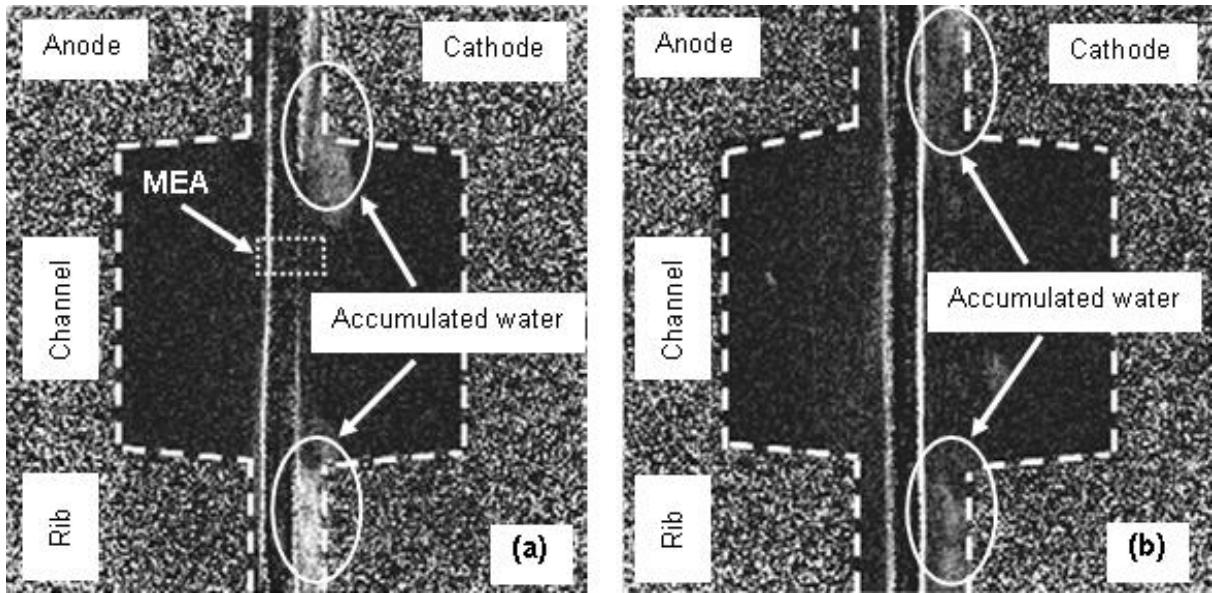


Figure 4 Cross-sectional images of water accumulation under channel and rib area at current density of 0.4 Acm^{-2} for (a) SIGRACET® 24BA; and (b) SIGRACET® 24BC h (Reproduced from [131] with permission)

The detachment of droplets from the surface of GDL occurs when droplets become larger in size as illustrated in Figure 5 [140]. Ous and Arcoumanis [140] showed that droplets with size larger than 0.4mm can detach from the surface of GDL (Toray TGP-H-060) by an air velocity below 60m/s whereas smaller droplets maintain their direct contact with the surface. The reason for this is that bigger droplets have larger contact surface area with the flowing air. When the aerodynamic force of the air flow gradually increases, droplets lean to the opposite direction of the airflow until they reach their critical contact angle and detach completely from the surface [140]. In [160] values for the critical receding contact angle are reported to be in the range of 50-80°C for carbon papers and around 90°C for carbon cloth.

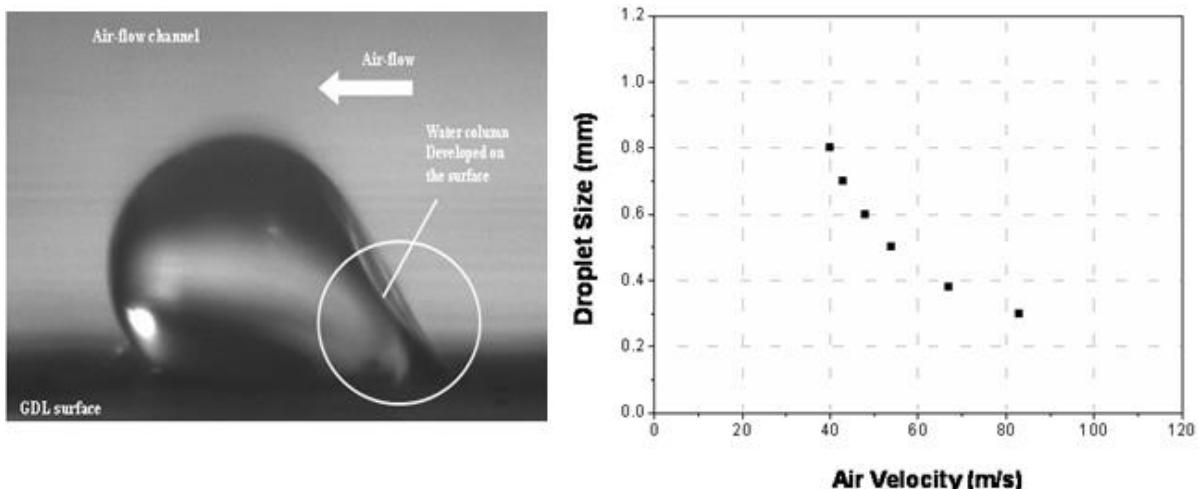


Figure 5 (a) Image of droplet detachment from the GDL surface by the airflow (b) Air velocity detachment for different droplet sizes [140]

The structural properties of GDL such as porosity and surface roughness [158, 160, 161] were found to have an effect on the contact angle and pinning phenomena. In [160] the static and dynamic contact angle of water droplets on different GDL designs including carbon cloth and carbon papers were measured and found to be different. For example, static angle of droplet with size of 1.2 mm on a carbon paper type 1 was $\sim 120^\circ\text{C}$. For a similar droplet size, the static angle on carbon paper type 2 and carbon cloth was 136°C and 140°C , respectively. Also the design aspects of flow channel plates including channel height [158], channel-land ratio [162] and flow patterns [163] play a significant role on droplet deformation and detachment. When the height of the channel increased from 250 to 500 μm in the simulations, a change in the evolution of water droplet shape in the flow channels was observed [158]. With higher channels, droplets tend to grow bigger in size keeping the flow field in the channel more uniform. Thus shearing stress and pressure difference on the interface of the water droplet become relatively weaker.

Based on these design considerations, it is clear that unless the stoichiometric air flow is high water slugs will develop leading to flooding in the cathode channels [107]. It was shown by Ous and Arcoumanis [107] (Figure 6) that water disappeared completely from the channels only when air stoichiometry (λ_{air}) reached the value of 36. Below that stoichiometric point, water films start to evolve from the channel walls and gradually grow in size until they merge and block the access of the air flow in the channels.

Direct visualisation techniques can reveal the location of water flooding in the flow channels of an operating cell. If optical accessibility to the channels is not feasible, current density distribution or temperature distribution measurements of the cell, also called mapping, can assist in predicting the water concentration profiles across the membrane. The correlation between water, current and temperature was investigated in many studies [164-172]. In general, water tends to accumulate near the outlet of the cathode flow channels despite the appearance first of reactant air at the inlets. The fact that the air velocity reduces gradually along the flow channels enables more formation of water droplets on the GDL surface towards the channel exit. In [173] and [174] there is agreement that water accumulation takes place at the exit of the flow channels based on their optical observations. The higher the air velocity at the inlet (e.g. 16ms^{-1} vs. 7.4ms^{-1} at the outlet [174]) the more sufficient it is to remove any liquid water from those regions. The calculations carried out by [175] have suggested different trends. The velocity of the airflow was lowest in the middle channels maybe because of the effect of cell back-pressure that kept the air velocity high at the exit of the channels.

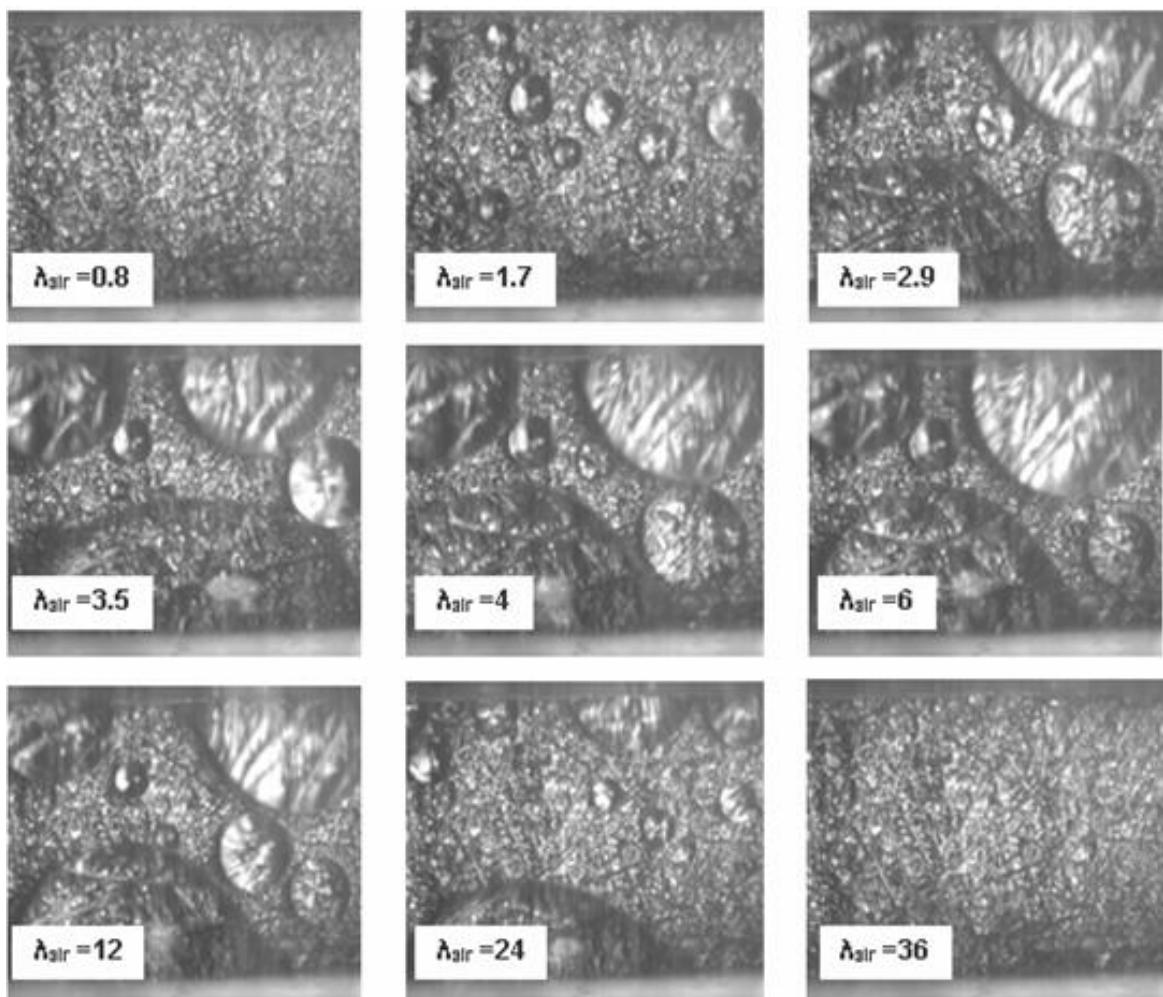


Figure 6 Images of water accumulation in the cathode flow channels within a range of operating air stoichiometry [107]

3. Water production

It is likely that the best way to assess the effect of water formation on the PEMFC durability is to understand the electrochemical reaction of the cell in more depth. The formation of by-product water takes place on the surface of Pt particles within the cathode catalyst layer by two gas-phase reaction pathways: O₂-dissociation and OOH-formation [176]. In the O₂-dissociation pathway, dioxygen adsorbs on the Pt surface [177] and dissociates. Each oxygen atom then reacts with chemisorbed hydrogen atoms to form water. Similar outcome exist from the OOH-formation pathway as a hydrogen atom on the surface first reacts with adsorbed O₂ to form OOH. This then dissociates to form chemisorbed OH and O which react with other chemisorbed hydrogen to form water. According to [176], the OOH-formation is more favourable for the cathode reaction due to its higher energy barrier of the dissociation step (i.e. 17 Kcal/mol). However, the fact that water is generated at the catalyst makes the catalyst structure more exposed to deterioration through the water formation process than other parts of the cell.

The design of the catalyst structure consists of three main components: an electronically conducting material (Pt/C), an ionically conducting material (perflurosulfonate ionomer (PFSI)), and an electronically and ionically insulating material (PTFE). These components are randomly distributed in the form of clusters bridging the Nafion membrane with current collection sites, as illustrated in Figure 7. Gaseous reactants and liquid products are able to penetrate through the void regions of these clusters; the distribution of clusters and the ratio of particles loading (e.g. % Pt/C vs. PFSI vs. PTFE) determines the catalyst utilization [178].

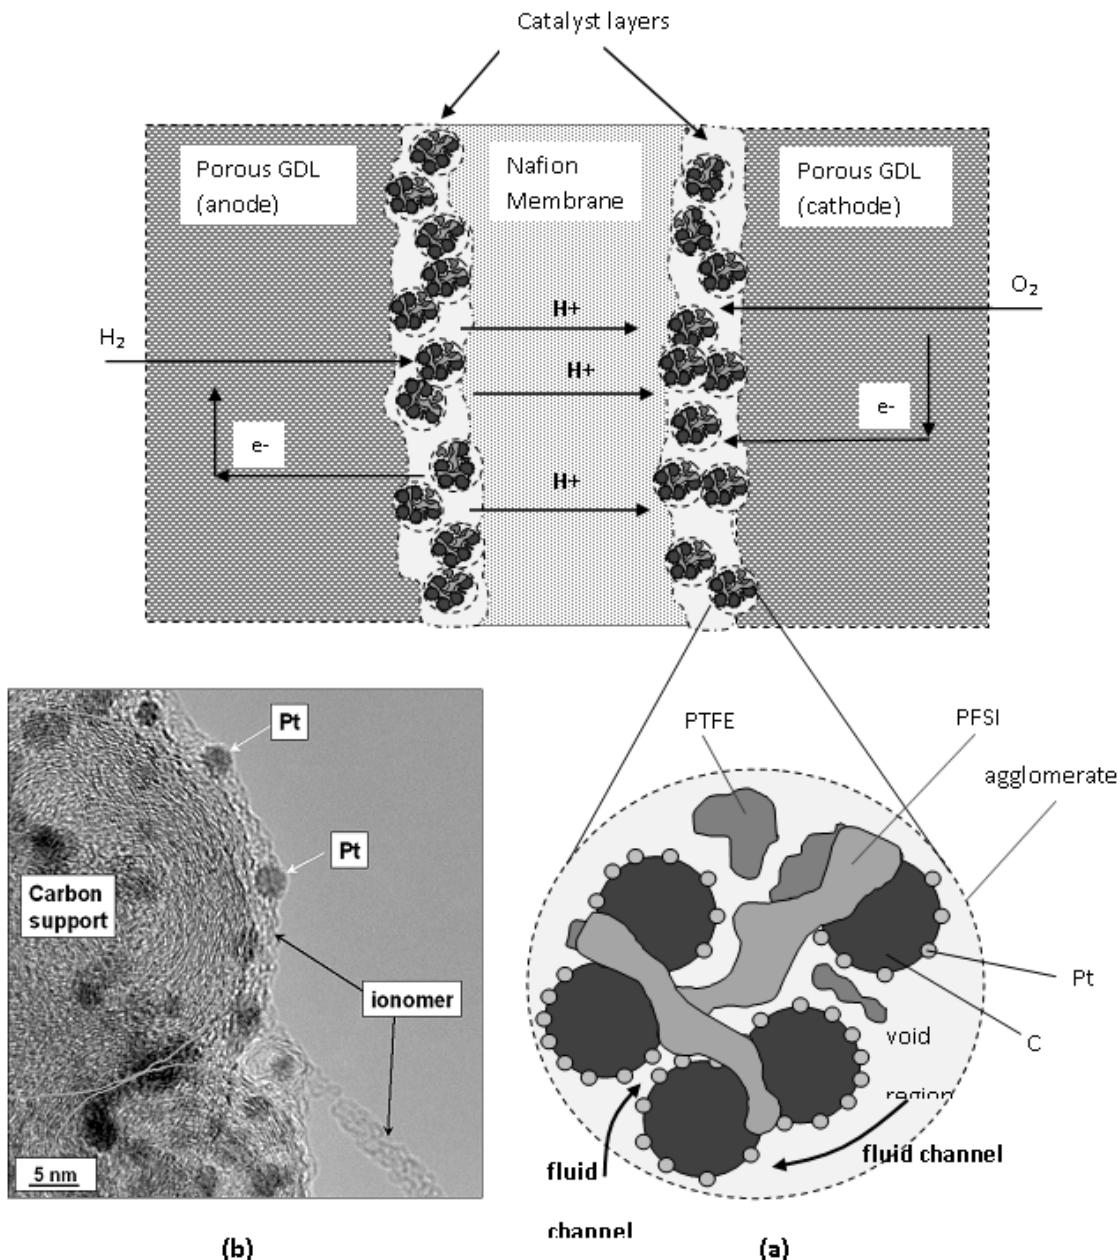


Figure 7 (a) Cross-sectional view of a typical Membrane Electrode Assembly (MEA) of PEMFC (b) TEM Image of Pt catalyst particles on carbon support surrounded by recast ionomer h (4.b is reproduced from [362] with permission)

3.1 Catalyst deterioration

3.1.1 Pt and Ionomer dissolution

In Pt/C clusters within the catalyst layer, Pt particles are deposited on a relatively larger carbon support as shown in Figure 7. During the electrochemical reaction of the catalyst, these nanocomposites undergo structural changes in terms of Pt concentration and distribution. These changes, also known as the loss in the active surface area of the catalyst, were associated in previous studies [179-181] with four main mechanisms: (a) Ostwald ripening (b) Pt crystal migration and coalescence (c) detachment and agglomeration of Pt nanoparticles, and (d) dissolution and reprecipitation of Pt single crystals in the ionomer and membrane.

Figures 8 and 9 show TEM images presented in [363] of Pt_3Cr and Pt particles agglomeration at the cathode and anode catalyst layers, respectively, after cell operation. At the catalyst cathode, Figure 8, Pt_3Cr particles were enlarged to almost twice their original size after 500 hrs of testing. The size has changed from ~3-10 nm in the fresh cathode layer to ~6-20 nm. Coarsening of Pt particles was more severe at the catalyst anode as shown in Figure 9. After 1000 hrs of testing, Pt particles at the anode-membrane interface not only increased in size (e.g. from 1-12 nm to 20-40 nm) but also changed in shape to cuboidal with faceted sides.

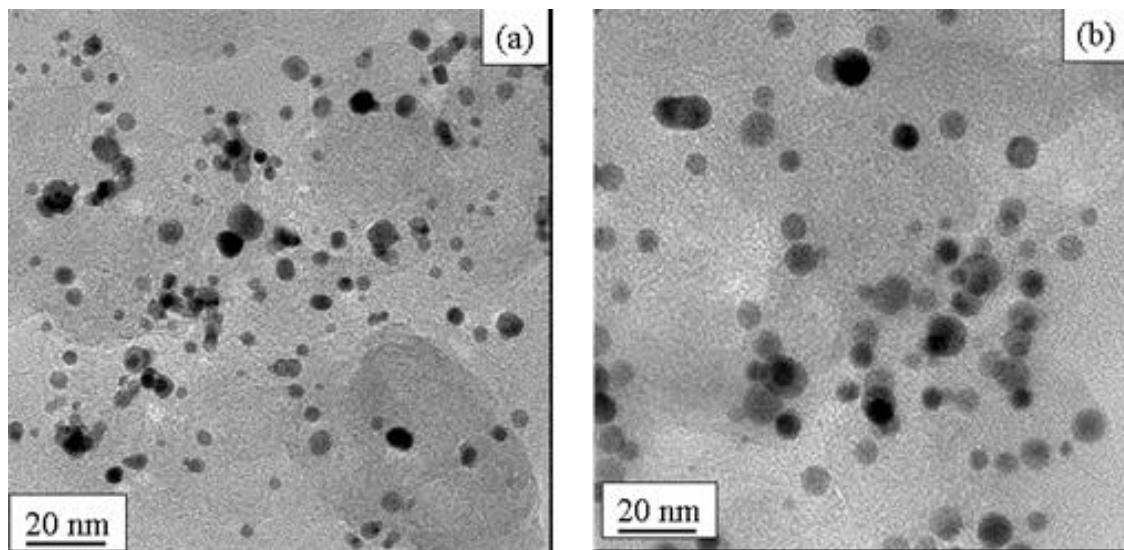


Figure 8 TEM Images of Pt_3Cr catalyst particles in (a) fresh cathode catalyst layer and (b) cathode catalyst layer in MEA electrochemically aged for 500 hrs (Reproduced from [363] with permission)

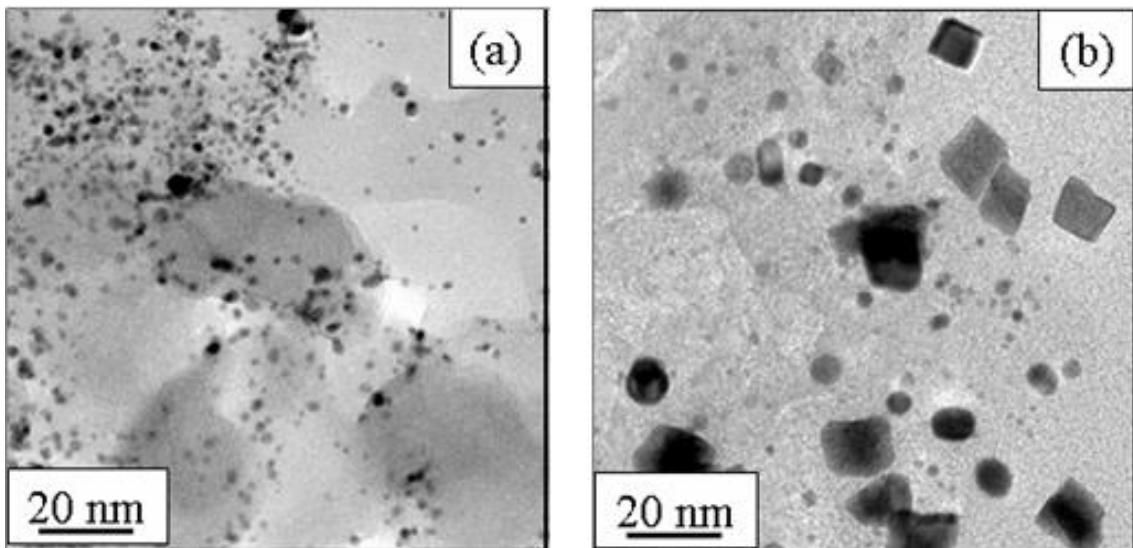


Figure 9 TEM images of Pt catalyst Particles in (a) fresh anode Pt catalyst layer and (b) anode catalyst layer at anode-membrane interface in MEA electrochemically aged for 1000 hrs (Reproduced from [363] with permission)

Potential cycling is considered to be the main cause of coarsening and coalescence of Pt particles in the catalyst. The effect of cycling becomes more noticeable with an increased number of applied cycles [186-190] as well as with changing the profile and frequency of these cycles [182-185]. In [183] it has been reported a 75% loss of Pt surface area after varying the cell voltage between 0.65 and 1.05V for 10,000 potential cycles. The Pt loss above 1 volt of cell voltage was also found high in [182] and its cause associated with Pt grain growth. The voltage level in [185] was slightly lower (e.g. 0.95V) but for more testing cycles (15000 cycles). They also examined two cycling profiles (square and triangle) and found that the loss of Pt mass activity per hour is almost doubled when the cycle period is halved. The loss was higher for the square wave than the triangular cycle profiles (e.g. 4 vs. 1.8 $\mu\text{A mg}^{-1}$ cycle $^{-1}$). The catalyst surface area was reduced dramatically by more than 50% from 70-30 m^2g^{-1} after 15000 testing cycles. This was in agreement with the results of [184] where it was found that when alternating voltage cycling (0.5-1.3 V_{RHE}) is applied with square waves of 30 s time period, the active surface area is reduced by 40% ($50-30 \text{ m}^2 \text{ g}^{-1}$) just after 200 min of operation.

The results data obtained in [184, 185] were at much higher level than the measurements of [186]. After 3000 of H₂/air cycles, Pt reduction from the cathode and anode by 15.6 and 6.3% of their initial ECAs of 55.4 and 54.2 $\text{m}^2 \text{ g}^{-1}$, respectively was observed [186]. Different results were obtained by other researchers: 70% reduction after 83,000 cycles ($80-27 \text{ m}^2 \text{ g}^{-1}$) [189], 25% after 400 cycles [187], and ~50% after 2400 cycles [190]. Logically, the higher the number of test cycles, the higher the Pt loss from the surface area of the catalyst. However, direct comparison is difficult because of the many influencing factors that can not be quantified accurately like the case of the technique used for Pt deposition on carbon support, the type of surfactant for Pt nano-particles [191] as well as other design and operational factors concerning the cell.

It is not clear yet whether water formation plays a role in the coarsening and coalescence of Pt particles. Only few reports have highlighted the effect of water on the growth of Pt particles [192, 218], Pt adsorption [177], and Pt migration [193]. In [192] it was agreed that the hydration level of the catalyst influences the crystallite migration particle growth mechanism. The particle size of the cathode and anode electrodes was found, therefore, to be different. This was based on their Pt distribution curve measurements and on the expectation that the presence of liquid water lowers the activation energy for the particle's growth. The review of [218] pointed to the fact that by increasing RH the Pt-particle size would also increase. Again, it is not easy to identify the cause since the increase in Pt size could simply be due to water flooding at the catalyst layer rather than enhancement of ORR and thus water formation. Also the loss in the active surface area of the catalyst by Pt migration could also be caused by water transport in PEMFC since once Pt particles are detached from their carbon support, they become vulnerable to further displacement; this is discussed in more detail in section 5.

As Pt particles dissipate from the catalyst layer during the cell reaction, so does the catalyst ionomer [36]. Previous studies associated the dissolution of ionomer from MEAs to a number of factors such as hydrogen crossover [199], Nafion loading [198], and cell operation under OCV [44, 200] and extreme relative humidity conditions [30, 201]. However, none of these studies associated the segregation of ionomer to the water production process in PEMFCs. Probably the best way to detect this is to monitor the change in the concentration level of fluoride (F^-) and sulphate (SO_4^{2-}) anions of the cell. According to a number of studies, the change in F^- and SO_4^{2-} concentration is attributed to the variation of the relative humidity of the reactant gases. The effect of the relative humidity on the fluoride emission rate from the cell is discussed in section 5.1.

3.1.2 Carbon corrosion

Carbon corrosion was detected in many occasions following the operation of the cell under potential cycling [182, 184, 188, 194], start-up and shutdown [176], localised fuel starvation [195, 196], and extended OCV [197]. Wilson et al [194] presented TEM images showing how potential cycling causes considerable dissipation of Pt particles from their carbon support in the catalyst. After 2 and 4 hrs of cycling between 0.4-1.4V, the amount of Pt decreased to about 71% and 47%, respectively.

The stability of Pt particles is strongly affected by the corrosion of their carbon support during the electrochemical reaction of the cell. Ball et al [188] attributed the poor stability of Pt particles in their tested catalyst to the dissolution/ sintering of carbon. They calculated the cumulative carbon corrosion for a range of commercially available and heat treated carbon blacks, e.g. expressed as maximum weight loss in wt%, and found that high area carbons are 25 times more corrosive than low area or heat-treated carbons. The increase in specific surface area of the carbon substrate in Pt/C catalyst tends to influence the carbon corrosion process. When Okada et al [311] examined different surface

areas of carbon substrates the ones with the largest area caused more Pt dissolution from the catalyst and higher CO₂ generation rate from the cell. This result is probably expected since larger carbon particles will normally support more Pt particles on their surface and hence the damage would be more pronounced.

3.2 Mitigation strategies

New alloys were developed to enhance the performance and durability of Pt-based catalysts. The aim was to (1) improve the catalytic ORR activity (2) minimise the loss of Pt particles from the active surface area of the catalyst, and (3) make carbon-support more resistant to corrosion. One way to achieve this is to reinforce the design of the catalyst by impregnating Pt particles with substances that increase their stability on the carbon support. Platinum-Titanium (Pt-Ti) and Platinum-Ruthenium/Carbon (Pt-Ru), for example, were suggested by [202] as suitable alloys with high Pt stability under severe acidic conditions. When these alloys were utilised in the design of MEA, the cell was more CO-tolerant than pure Pt catalyst as deduced from the negative shift measurements of the cell potential. Their results also showed that these alloys have better ORR activity than pure Pt catalysts, hence higher kinetic current densities of the cell.

Cobalt (Co) is another metal that can potentially improve the stability of the catalysts. The fact that their bond dissociation energy with Pt particles is relatively high (~ 1072 kJ/mol), makes them suitable candidates for Pt-based catalysts; Pt-Co based alloys have been tested in previous experimental investigations [188, 189, 203-205] and showed improved cell polarisation performance compared to conventional Pt/C catalysts. Based on [189], the mass and specific activity of the Pt-Co cathode catalyst is 2X and 4X higher than Pt/C catalyst, respectively. The loss in the surface area of Pt-Co catalysts tends to be quite slow reaching a maximum of 43% after 83,000 potential cycles ($35-20 \text{ m}^2 \text{ g}^{-1}$). However, the measurements of Ball et al [188] did not show any sign of loss in the surface area of Pt-Co catalysts after cycling. This was the case except for when the catalyst was immersed in 1M H₂SO₄ solution.

The effect of Co on Pt stability of the catalyst was demonstrated in [203] by capturing transmission electron microscopy (TEM) images of the catalyst structure in the presence and absence of Co after 10,000 operating cycles. In Pt/C-based catalysts, Pt particles migrate towards the membrane layer whereas this was not the case with the PtCo/C design. To enhance the stability of Pt-Co even further, Tada et al [204] suggested replacing the conventional carbon black with new carbon support that has optimal combination of carbon surface area and PtCo particle size (~800 m² g⁻¹, PtCo ~ 4-5 nm). This proposed design exhibited high ORR activity of the catalyst as evident from the polarisation results of the cell.

An alternative method to minimise the loss of Pt from the active surface area is to change the actual design of the catalyst. Instead of bonding Pt particles chemically to the surface of the carbon support, Pt atoms can be encapsulated inside a fullerene cage. This new type of catalyst, known as metallofullerenes, is considered to be one of the most promising designs to extend the life time of PEMFC [206]. Fullerenes can be in different shapes, such as spherical (buckyballs), cylindrical (carbon nanotubes or buckytubes), or an aggregate of cylindrical in the form of thin sheet (buckypapers). Relevant research focuses mainly on buckypapers amongst other types of metallofullerenes based catalysts. The design of these newly developed catalysts consists of single-walled nanotubes (SWNT), double-walled nanotubes (DWNT), multi-walled nanotubes (MWNT), or carbon nanofibers (CNF). Various techniques were used for the preparation of these catalysts such as ion exchange [207], borohydride [207], ethylene glycol reduction [208], direct sputter deposition [209], and electro-deposition method [210].

Wang et al [207] examined the ion exchange preparation method against the borohydride method on MWNT for the same Pt loading. They found the ion exchange technique to be more effective in terms of ORR and Pt utilization; the later can be further improved by using nanotube-based catalysts. This claim was supported by the measurements of [209-212] which showed high polarization performance of the cell. The good accessibility to reactant gases and the uniform distribution of Pt on the carbon structure are not the only advantages of these catalysts, but good durability as well. Chen et al [208] measured the degradation rate of MWNT, DWNT, and SWNT-based catalysts against commercial Pt/carbon black under an accelerated durability test (ADT). The ratio of Pt loss from the active surface area was reduced after 1000 cycles by around 1.5 times when using Pt/MWNT or Pt/DWNT and by 1.2 times for SWNT compared to a typical Pt/C catalyst. All of these catalyst designs had the same initial Pt concentration, which was in the range between $63\text{-}65 \text{ m}^2 \text{ g}^{-1}$, for accurate comparison. The loss in Pt/C was 48%, while in Pt/MWNT/ Pt/DWNT and Pt/SWNT it was 32% and 38%, respectively. This reported value of Pt loss in SWNT (e.g. 1.2 times) was much lower than that detected in [211] (e.g. 3.8 times). After 400hrs of ADT, the loss of Pt from the active surface area using buckypaper support was 18% while the Pt loss was 69% in Pt/C. The difference between these two results could be attributed to the design aspects of the tested cells as well as to some of the operating conditions such as the level of voltage cycling [211].

The use of different substances other than carbon for Pt-based catalysts was previously investigated with materials like aluminium oxide (Al_2O_3) [213], titanium dioxide (TiO_2) [214], zirconium dioxide (ZrO_2) [215], and tin dioxide (SnO_2) [216]. The advantage of using Al_2O_3 or alumina as catalyst support is due to its insulating characteristic. Since electron transport through the carbon support contributes to the growth of Pt particles, insulating-type support could prevent the passage of electrical paths, thus suppressing degradation.

On the other hand, when Pt-alumina catalyst was examined [213], Pt particles have remained almost the same size (~8 nm) after immersing it in deionised water at 80°C for one week. Suzuki et al [215] used different catalyst design, e.g. Pt-S-ZrO₂, and kept its electronic conductivity to a level where the ohmic loss of the cell is minimal. The performance of this catalyst was better than Pt/C when Nafion ionomer was not added to the design. The open circuit voltage of the cell (OCV) using a Pt- S-ZrO₂ cathode was slightly higher than the Pt/C type (0.883 vs. 0.868 V) and, at a current density of 2 A cm⁻², the cell voltage was 0.36 V compared to 0.31 V for Pt/C. Probably the best result was achieved in [214] when Pt/TONT catalyst was used. The active surface area of the catalyst was reduced by only 20.3% after 10,000 of accelerated potential cycles. This relatively small loss of Pt was purely due to the strong and stabilised physical interaction between Pt-Pt particles and Pt-TONT in the catalyst. Again this synergistic effect between Pt and TONT was the main reason for the improved ORR activities of the catalyst. The mass and area-normalised kinetic current densities at 0.8 V using a Pt/TONT catalyst was ~ 5.3X and 2.2X greater than the Pt catalyst, respectively.

Chen et al [217] even suggested removing the carbon support of Pt particles completely from the design of the catalyst and use Pt/alloy nanotubes (PtNTs) instead. The idea was to alleviate most of the degradation pathways initiated by the carbon. This design was examined against Pt/C and Pt/carbon black catalysts and exhibited minimal reduction of the electrochemical active surface area. The Pt loss of PtNT, Pt/carbon black, and Pt/C catalysts was found 20%, 50%, and 90%, respectively after 1000 operating cycles. These values are significantly higher than those previously reported in [208] and [211].

4. Water retention and accumulation

4.1 Water retention

The presence of liquid water in PEMFC has a detrimental effect on the mechanical, electrical and chemical properties of the cell components. The deterioration of these properties can be attributed to three main mechanisms known as membrane swelling, corrosion, and ice formation.

4.1.1 Membrane Swelling

Swelling occurs as a result of water absorption by the membrane which expands its polymeric matrix. When liquid water is absorbed, the ionic constituents within the membrane become surrounded by those water molecules while the polymeric matrix resists the uptake of more water. The water inside the membrane increases its pressure relative to the external water surrounding the membrane due to

the effect of the elastic forces of the polymeric matrix. The pressure difference between the internal and external water, known as swelling pressure, determines the increase in the partial molar volume of the solvent as a function of the operating temperature, water activity, compression load, and relative humidity [220-222]. The neutron-based images presented in [221] showed the changes in the physical dimensions of the PFSA type membranes under wet conditions; e.g. the thickness of these membranes was increased by 0.1 mm. Parrondo et al [220] explained that such change in the membrane matrix structure is strongly dependant on the water activities of the ionic solution. For example, when they treated the membrane with KCl solution, the membrane thickness remained the same whereas with HCl and NaCl solutions the thickness changed by 10% and 5.5%, respectively.

In general, swelling develops in an anisotropic fashion since membranes creep more in one direction than in others. Membranes have a different creep response depending upon their water content and the surrounding temperature. Majsztrik et al [224] elucidate the effect of both temperature and water on the mechanical properties of Nafion by arguing that hydrophilic domains within the Nafion structure become stable when water interacts with the sulfonic acid groups whereas these domains break apart with increasing temperature. This combined and complex effect causes major changes in the number, strength and flexibility of the cross-links between the hydrophilic domains. In order to investigate this phenomenon, Majsztrik et al monitored the viscoelastic response of Nafion under a range of temperature and hydration conditions. They found that the tensile creep strain of Nafion increases with increasing water activity, e.g. increase in RH, for the whole temperature range tested (25-60°C). The measurements also showed that strain values become higher under wetter conditions at lower temperatures (25-50°C) but reduce at higher temperatures (60°C).

The increase in the membrane thickness, known as the membrane thickening phenomenon, introduces non-uniform local stresses that can contribute to the mechanical failure of membrane particularly in areas that are more exposed to compression by the assembly of the cell. The simulations carried out by Kusoglu et al [225] showed how hygro-thermal loading affects the stress distribution profile in the membrane. The in-plane stresses were mostly driven by the swelling strain, particularly on both ends of the membrane where stress is higher due to cell clamping.

The change in the mechanical characteristics of the membranes is correlated to the level and number of RH operating cycles applied to PEMFC. This was examined in the experimental work of [235] where an increase of both parameters resulted in a significant reduction of the MEA ductility. The average strain-to-failure was reduced by around 40% (from 1.32 to 0.58) after 100 cycles in the 30-80% RH range. Also, the elastic modulus of the membrane was reduced from ~ 480 to 280 MPa when RH increased from 25 to 75%. These results which were validated using a finite element model, revealed the formation and growth of mechanical defects such as crack and crazing in the membrane and MEAs. Kusoglu et al [238] were also able to simulate the trend of the in-plane stresses across the

membrane during five humidity loading cycles (95-30% RH). It was clear from their results that the value of in-plane stresses differ depending on the local contact area of the membrane (e.g. either facing the flow channel or in direct contact with the channel land). Calculations made by Kusoglu et al [237] revealed that residual stresses can be up to 10MPa which may lead to delamination of the membrane and the gas diffusion layer and similarly the high in-plane stresses were associated to crazing and its growth. The simulations of [296] suggest that in-plane stresses are much higher under the land regions than under the flow channels at any level of relative humidity of the reactant gases. For instance, at 0.05 swelling strain of the MEA under 100% RH, the in-plane stresses under the middle area of the flow channels were nullified.

The damage escalates further with additional tensile stresses when the membranes enter the dehydration phase in low relative humidity cycles. This can result in membrane thinning [231, 232], delamination [233], or pinhole formation under extensive RH cycling [229, 230, 234]. Chen and Fuller [233] presented SEM images showing pinhole formation and signs of delamination on the surface of the membrane when operating the cell under low RH operation of 36%. The observed degradation was validated using a numerical model based on the main chain unzipping process of membranes. The simulations revealed that low humidity conditions enhance the side chain scission process creating many weak end-groups in the membrane's chemical structure, thus accelerating the degradation process. Similarly, the SEM observations of [232] revealed images of membrane thinning under relatively low humidity conditions of 65.8% at both the anode and cathode. As a result, the hydrogen crossover rate has increased gradually reducing the amount of hydrogen reactant; the degradation rate of the cell voltage was calculated to be around 0.0537mVh^{-1} .

4.1.2 Corrosion

The formation of hydrogen peroxide (H_2O_2) often occurs during the electrochemical reaction of PEMFC. This introduces dangerous radicals such as hydroxyl (OH) and hydroperoxyl (OOH) radicals that can potentially attack the membrane and accelerate the chemical degradation process of the cell. Based on [241, 242], these radicals tend to alleviate the interface between the catalyst and ionomer and as a result, the active surface area of the catalyst is significantly reduced. The relative humidity of the reactant gases was linked in some way to the formation rate of H_2O_2 . Sethuraman et al [239] found noticeable differences in the amount of H_2O_2 generated at the cathode between dry and full humidity conditions. At a testing temperature of 95°C, the rate was reduced 7X as RH increases from 0 to 100% ($0.7 \text{ to } 0.1 \text{ mol cm}^{-2} \text{ s}^{-1} \times 10^6$).

Despite the majority of studies blaming voltage cycling of the cell for the carbon corrosion in PEMFC [184, 185, 187-189, 218, 243], some studies have associated its cause to the presence of liquid water in the catalyst [248-252]. Maass et al [249] found that the corrosion rate of carbon is linearly dependant on the molar water concentration. For each H_2O molecule present one molecule of CO_2 is

formed. When they raised the molar water concentration by a factor of three (0.1-0.3) under anodic potential limit testing, the corrosion rate of carbon increased by an equal proportion (e.g. from ~2.4 to $7.2 \text{ g h}^{-1} \text{ cm}^{-2}$). This finding implies that the corrosion rate would be highest at the maximum current density.

The increase in the relative humidity of the reactant gases increases the risk of carbon corrosion at the catalyst. The measurements carried out by Stevens et al [244] showed significant increase in the carbon combustion rate for XC72 and BP2000 type carbon support when the cell operation changed from dry to wet conditions. The carbon corrosion of the cathode catalyst layer in [343] was enhanced noticeably when the cathode inlet RH increased from 0 to 100%. The gradual decrease in the catalyst thickness (~70% reduction, e.g. $10.5 - 6.6 \mu\text{m}$) and the increase in the carbon dioxide production at the catalyst ($350 - 1,300 \text{ ppm s}^{-1}$) confirmed the corrosion of carbon. Interestingly, RH was found to have negligible effect on the degradation rate of the anode catalyst as revealed from their back scattered Electron Microscopy (BSEM) images.

Corrosion can also affect the bipolar plates of the cell if no surface treatment is made to metallic-type plates to withstand harsh acidic and humid conditions [253-255]. Passive films can be formed at the interfacial regions between the cell components raising the overall ohmic resistance of the cell. This happens mainly at the interface with the gas diffusion layer creating additional interfacial contact resistance (ICR) with the bipolar plates; the thickness of this passive film determines the value of ICR. Antunes et al [253] evaluated a range of materials from previous experimental investigations to find the best material for bipolar plates with minimum corrosion resistance.

Typically, the value of ICR reaches a maximum when the film reaches maximum thickness or stabilises in thickness. This was observed in [257] when ICR continued to increase from 200 to $320 \text{ m}\Omega \text{ cm}^2$ until the passive film reached maturity thickness after 30min of cell operation. Stability of the passive film thickness was also detected in [258] where it took 50 min for the film to develop to a maximum thickness of 3nm at 0.6 V in a simulated cathode environment against 20 min for 2.6 nm film at -0.1 V in an anode environment. It is worth noting that the thickness of passive films and the corresponding contact resistance will vary based on the compaction force applied to the cell assembly; the contact resistance gradient tends to be much smaller at large compaction forces.

Another effect of the corrosion of metallic bipolar plates is the release of metallic-based cations like Fe^{3+} , Ni^{2+} , Cu^{2+} , Cr^{3+} . The origin of these cations could be the dissolution of the alloys used as coating material for the plates. Using mass spectroscopy techniques, traces of chromium, nickel, iron, sulphur and aluminium from the by-product water were detected after operating the cell with aluminium plates coated with carbide-based alloy [260]. Their energy dispersive X-ray (EDX) analysis revealed more changes in Ni at the cathode than the anode which was attributed to the higher relative humidity as well as the electrochemical activity of the cathode. A list of major contaminants and their origins

affecting the performance of PEMFC was identified by Cheng et al [318]. Independent of the source of these impurity cations, they can potentially attack the membrane and deteriorate the mechanical and chemical stability of Nafion. [254] et al highlighted a number of cooling materials and techniques so that deterioration mechanisms like catalyst poisoning, reduction of membrane conductivity, passive film formation, reactant crossover, and bin-hole formation on bipolar plates can be prevented.

The change of the ionic conductivity of polymer membranes could be strongly affected by the amount of impurities in the cell. Indeed, this was addressed in [262] when immersed membrane samples in sulphate salt solutions were used to understand the effect of inorganic cations. They found that the reduction in the membrane's conductivity is negligible at low impurity levels (e.g. 0.1, 1, 10 ppm) but becomes significant at high levels (100ppm). They also demonstrated that the effect of each type of impurity can be different. For example, Ni^{2+} , Cu^{2+} contaminated membranes displayed lower conductivity than Na^+ ones whereas Fe^{3+} exhibited the lowest conductivity amongst all.

4.1.3 Ice Formation

The damage originated from the lingering water in the cell becomes more severe when liquid water turns into ice under subfreezing temperatures which can block the access of gases into the reaction sites of the catalyst causing gradual drop in cell's performance. This was confirmed by the experimental measurements of [296] where the current density of the cell was reduced linearly as water continued to freeze. The phase transformation, caused by freeze-thaw cycles, also results in volume expansion of the retained water. This introduces local isotropic stresses that can damage the structure of the membrane and other porous layers of the cell including the catalyst, GDL, and MPL. The SEM images presented in [267] and reproduced in Figure 10 show detrimental changes to the catalyst surface of a fully hydrated MEA under 10 freeze-thaw cycles at temperatures reaching -30°C .

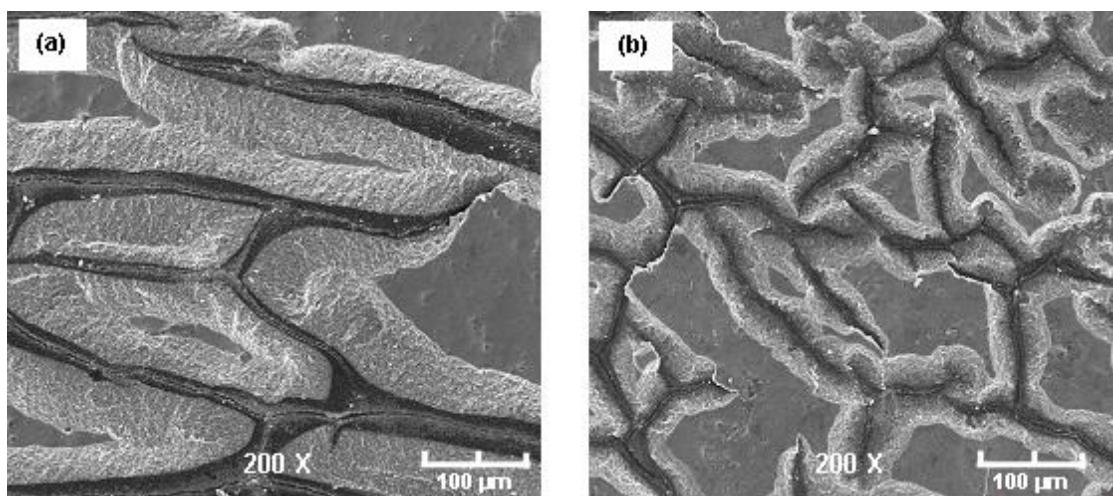


Figure 10 SEM images of MEA without purging after 10 freeze-thaw cycles between 20 and -30°C (a) anode (b) cathode (Reproduced from [267] with permission)

Furthermore to the structural damage, the electrochemical active surface area of both the anode and cathode catalysts was reduced considerably, e.g. the cathode by 23% and the anode by 15% after 20 freeze-thaw cycles.

An early impact of ice formation on the MEA structure could be on affecting its porosity. The environmental scanning electron microscopy (ESEM) observations made by Alink et al [277] revealed a significant increase in the porosity of a damaged MEA when wet stack underwent freeze/thaw cycling. This led to the exposure of the catalyst layer and further decrease in its surface area by Pt particles detachment. As it can be seen from Figure 7, the damage in the cathode was more substantial than the anode probably due to its higher water concentration. Li et al [268] revealed, based on their cryogenic FESEM analysis, that the porosity change across the catalyst layer due to ice formation is uneven. Eventually, the biggest change was at the interface region with the membrane layer (~25%). This finding is not in agreement with the CRYO SEM observations of [296].

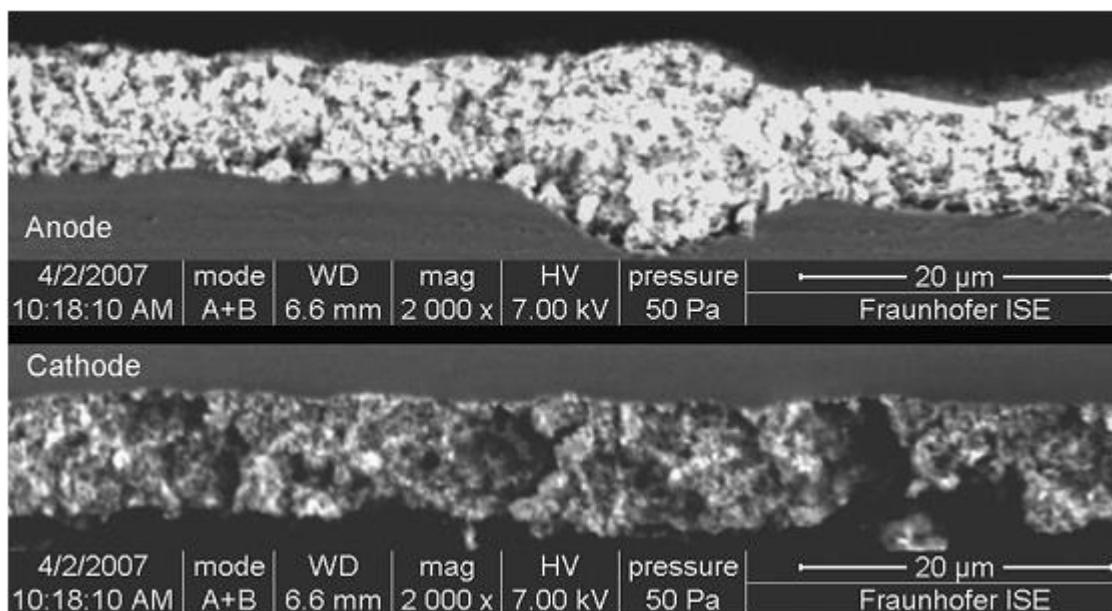


Figure 11 Cross-section of MEA catalyst layers after 71 of freeze/thaw wet cycles (Reproduced from [277] with permission)

Although, both studies identified two distinct ice density regions in the catalyst layer, Kusoglu et al [296] believe that the majority of ice is formed closer to the GDL side rather than the membrane. They based their theory on the fact that existing ice prior to subzero operation will melt by the reaction heat of the catalysts. Liquid water will therefore migrate away from the hot membrane to the cooler GDL and continue to freeze.

In addition to the change in porosity, ice formation can damage the structure of other parts of the cell. This occurs more noticeably in regions of high water concentration within the cell. The damage detected by Lee et al [270] under freeze/thaw cycles was more severe when MPL was added to the design of the cell. At a high current density of 1 A cm^{-2} , the degradation gradient in the cell voltage for the same number of test cycles was 4.3 with MPL against 3.2 without MPL. This is likely because MPLs capture most of the liquid water for sustaining the membrane and catalyst layers at desirable hydration state. The damage might equally be the same when the cell generates more by-product water at high current densities. The results of [270] showed that despite the above role of MPL, the formation of ice-sheet between the catalyst layer and GDL can be prevented which hastens the degradation of mass transport as well as increases the total polarization resistance of the cell significantly.

Morphological damages of the PEMFC components due to ice formation can have serious consequences on the performance and durability of the cell. This includes scenarios like fuel crossover [273, 274], catalytic combustion as a result of pinhole formation [272, 273], fuel/oxidant starvation caused by water flooding in cracked regions [132, 275], accelerated catalyst erosion due to further exposure of the electrochemical surface area [276, 277], and increase in the ohmic resistance of the cell reflecting the increase in bulk resistivity (interfacial contact resistance) of the damaged layers [76, 278, 279]. Visual evidence of pinhole formation and micro-cracking on the surface of the membrane is provided in Figure 12a [273] following operation at sub-zero temperatures (e.g. cathode temperature below -5°C). The cell voltage has decreased and suddenly collapsed to zero after four cycles even at the low current density of 350 mA.cm^{-2} .

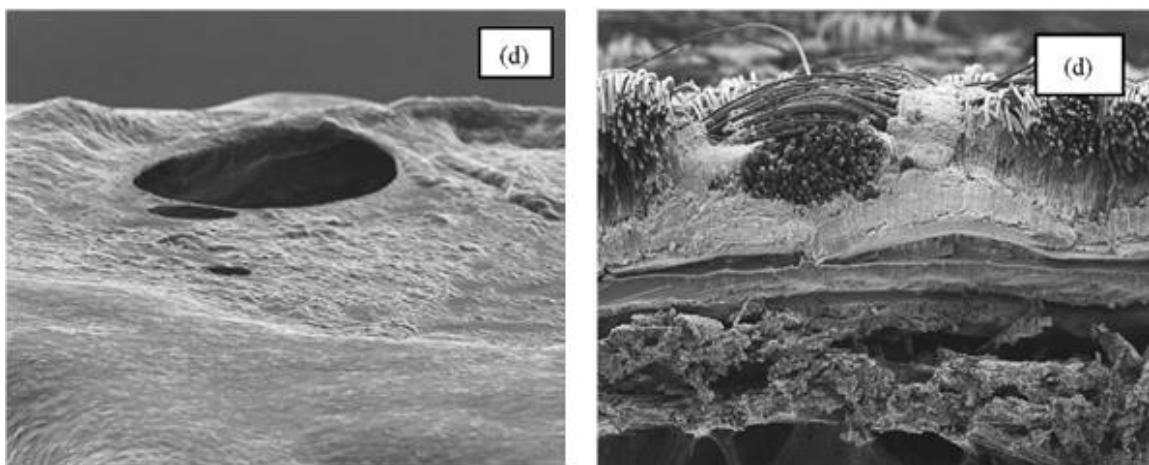


Figure 12 Effect of sub-zero temperature on MEA after operation at -30°C (a) pinhole formation on membrane from cathode outlet regions (b) catalyst delamination from GDL (Reproduced from [273] with permission)

Ice formation can also lead to the delamination of catalyst layers. Water tends to accumulate and freeze forming ice lenses at interfacial regions adjacent to the catalyst layer, e.g. either between catalyst and diffusion layer or catalyst and polymer membrane. This phenomenon was highlighted in

the simulations of [282] where formation of ice lens in the interfacial regions was predicted. Other experimental studies used in-situ optical techniques have also observed this phenomenon [273, 281]. Figure 8b shows an image captured in [273] of catalyst layer delamination from both the membrane and the gas diffusion layer (GDL) sides. According to their measurements, this delamination resulted in hydrogen crossover and consequent drop in cell performance. Similarly, in [44] the danger of delamination in oxygen crossover was pointed out which enhances the formation of hydrogen peroxide causing catalytic combustion at the anode.

The effect of catalyst delamination tends to be significant on the ohmic loss of the cell. Kim et al [280] compared the change in cell resistance caused by the delamination at membrane/catalyst (M/CL), catalyst/gas diffusion layer (CL/GDL), and gas diffusion layer/bipolar plate (GDL/BPP) interfaces. The increase in the interfacial resistance of M/CL and CL/GDL was much higher than that of the GDL/BPP. Their measurements showed that with a delamination area of 50 μm , the cell resistance was increased by around 30% for M/CL and CL/ GDL but only 10% for GDL/BPP.

Delamination of the catalyst layer can also lead to higher loss of Pt particles from the active surface area of the catalyst. Yang et al [281] were able to capture TEM images showing a gap at the interface between the cathode catalyst layer and the membrane. Consequently, Pt particles were increased in size (3 to 5-8 nm) followed by significant reduction in the specific surface area of the catalyst (~ 50%). Meanwhile, Ge and Wang [284] justified the 35% reduction in Pt surface area of their tested cell at – 30°C through the formation of an ice sheet between Pt particles and ionomers in the cathode catalyst layer.

Not all the residual water in the membrane freezes when the temperature reaches 0°C. Three types of water molecules known as non-freezing water, bond freezing water, and free water were distinguished by researchers during subfreezing temperatures. Each of these types has different freezing points depending on the nature of their molecular chemical bonds. For instant, Lu et al [286] detected three distinctive water states in subfreezing temperatures using a dielectric relaxation spectroscopy technique. They found in the kHz frequency region that water molecules are hydrogen-bonded to the sulfonates whereas in the GHz domain water molecules are either in liquid bulk-like or loose bond forms.

As temperature drops to 0°C, only the unbounded free water (bulk water) molecules transform into ice. The images presented in [287] showed that even at temperatures of – 3°C, liquid water is still present in the form of droplets on the surface of the catalyst. However, these droplets were not observed when the cold start was at –5 °C. This suggests that the freezing-point depression of water in the catalyst is no more than 2°C. The generation of liquid water below 0°C was again witnessed in [289, 290] but the temperature of water freezing was even lower (e.g. –10°C in [298]). Ishikawa et al

[289] attributed the reason for this low temperature to the freezing phenomenon of the super-cooled generated water where heat of solidification is emitted and the temperature rises to 0°C.

Apparently, water becomes completely frozen at much lower temperatures than -10°C. The study carried out by Saito et al [291] suggest that even at temperatures below -20°C the non-freezing water molecules remain unfrozen and move within the membrane. Their analysis was based on the estimation of the water self-diffusion coefficient, and on the differential scanning calorimetry (DSC) measurements that enabled the observation of the anomalous behaviour of non-freezing water. Interestingly, Mukundan et al [292] detected at the extremely low temperature of -80°C interfacial failure in the cell suggesting possible freezing point of water in the cell.

The reduction of the water content due to ice formation clearly reduces the mobility of hydrogen ions across the membrane; a reduction in the ionic conductivity of the membrane is therefore expected. The experimental work of [294] showed how by decreasing the cell temperature to -25°C, the water content of PFSA and BPSH membranes can be significantly reduced and the proton transport coefficients to become much less. Based on the measurements represented in [292] and [295], the membranes conductivity reduces substantially at subfreezing temperatures. The conductivity in [292] was reduced from 87 to 6 mS.cm⁻¹ as temperature drops from +30 to -30°C. Similar results were obtained by Koiwai et al [295] as conductivity reduced from 100 to ~1 mS.cm⁻¹ with temperature dropping from 40°C to -40°C. According to Alink et al [277], the decrease in membrane conductivity under sub-zero temperatures is attributed to membrane dehydration as a result of changes in the capillary pressure at the membrane/catalyst interface. They explained that during the heating process, the phase transition from ice to liquid water results in an increase of the capillary pressure leading to expansion of the membrane channels and increase of conductivity.

4.2 Water flooding

Flooding in PEMFC often occurs at high current densities when the generation rate of by-product water exceeds the removal rate of residual water from the cell. Flooding can be detected in-situ by either direct visualisation of the cell sub-layers or by monitoring the membrane's ohmic resistance. For example, as reported in [328], the change in the standard deviation of impedance measurements was an indication of flooding in PEMFC. Generally, measurements of membrane's impedance are carried out when optical accessibility to the cell is quite limited.

The sudden drop in the voltage level of the cell is another sign of flooding in PEMFC. The blockage by residual water of the access of reactant gases to the catalyst sites means the electrochemical reaction of the cell will stop. The sharp voltage decline takes place immediately after reaching the limiting current density of the cell better known as the cut-off current density. Many experimental studies have demonstrated this behaviour and attempted to extend this cut-off value which can be achieved by introducing advanced water management schemes to the cell.

Although many techniques have been used to detect flooding in PEMFC, optical visualisation techniques remain the most effective. Not only they help to identify key parameters that cause flooding, but also enable the anticipation of water flooding before happening. For example, the photographic images captured in [107] have allowed monitoring of the water build-up in the cathode flow channels. From those images, they were able to estimate how long it takes for a single PEMFC to be flooded with liquid water. As predicted after 30 min of operation, the channels were completely flooded followed by a significant drop in the cell current (e.g. 4.5 to 0.5 A). It is worth noting that almost all in-situ visualisation of water droplets on the surface of the membrane are made from the top view of the air flow channels which doesn't allow parameters such as droplets contact angles, droplets height, and droplets interfacial area with the surface to be estimated. However, it is possible to view droplet formation on the surface of the membrane from both the top and side view of the channels simultaneously as shown by Ous and Arcoumanis [141]. Figure 13 illustrates the optical set-up used in [141] which consists of two synchronised cameras positioned orthogonally while Figure 14 shows images of droplet formation on the surface of GDL at various locations in the air channels.

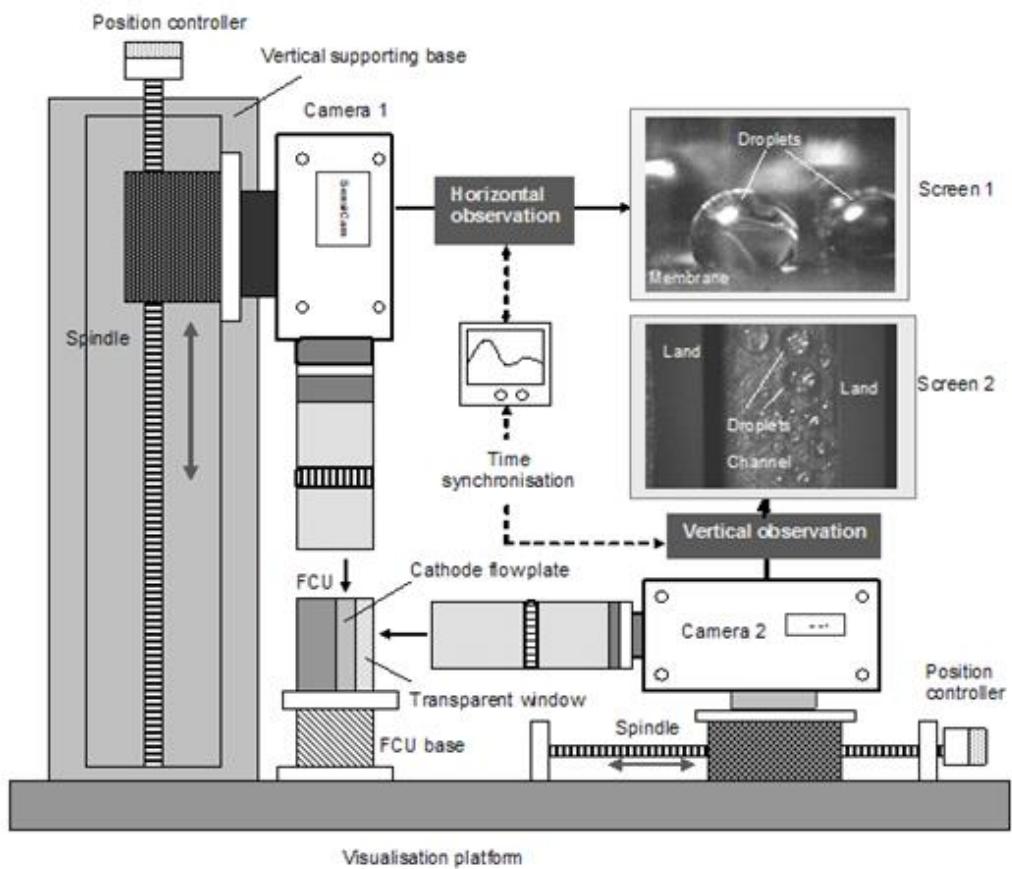


Figure 13 Visualisation set-up [141]

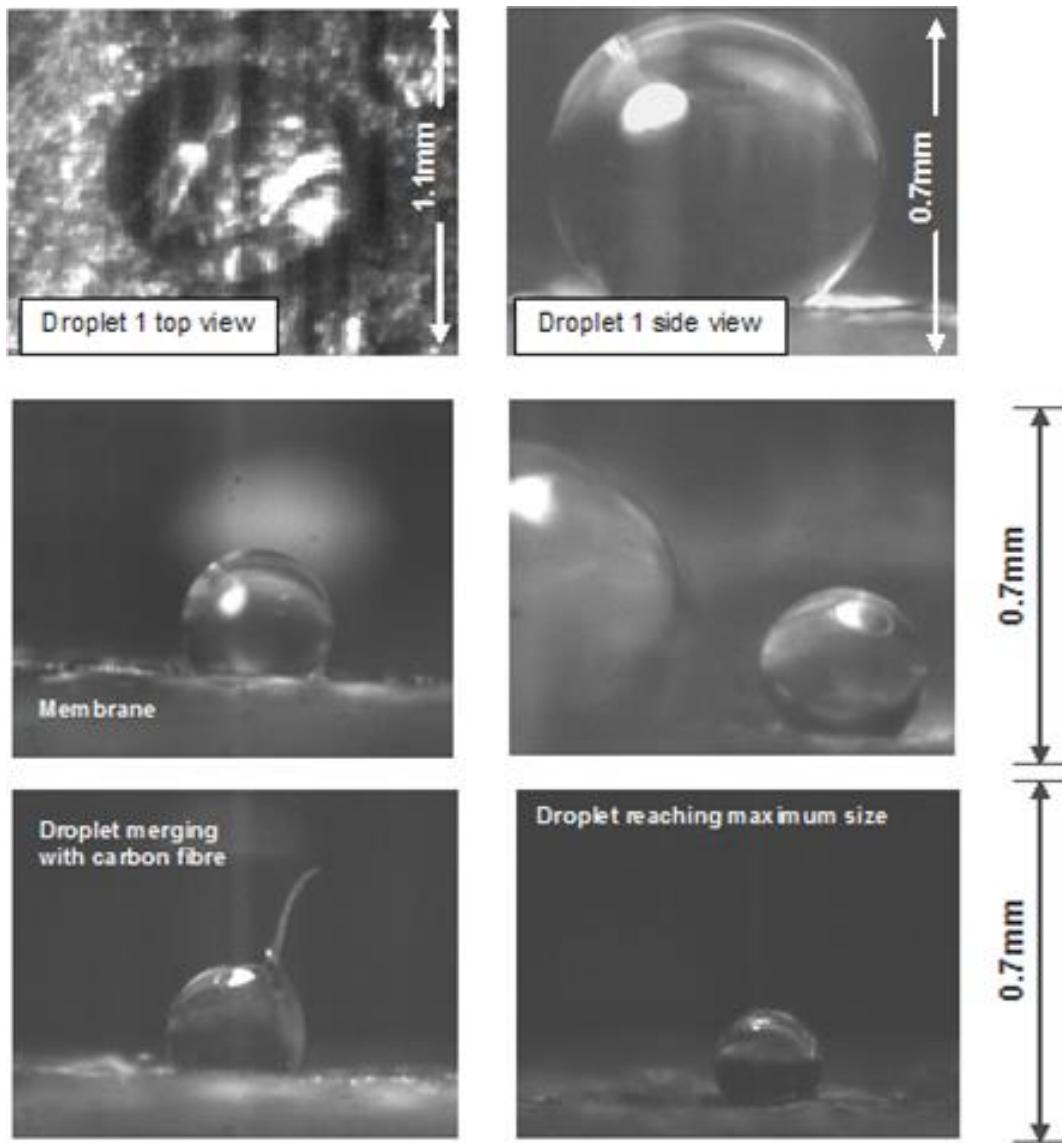


Figure 14 Droplet formation on the surface of GDL at various locations in the cathode flow channels [141]

Water flooding does not only affect PEMFC performance but its durability too. This is due to the presence of excessive water that leaves the cell fuel starved and thus induces local potential on the electrodes. Reiser et al [246] demonstrated both experimentally and numerically how local starvation of hydrogen can raise the cathode interfacial potential to as high as 1.44 V. At this high potential carbon corrosion of the catalyst can take place in just a few hours. The effect of this reverse-current mechanism was detected later by electron microprobe analysis (EMPA) images which showed significant decrease in the catalyst active surface area and thinning of the cathode electrode. Similarly when Patterson and Darling [195] restricted the access of hydrogen fuel to the cell by impregnating the anode GDL with kynar film, the cathode catalyst layer was severely corroded. Their EMPA images showed significant thinning of the cathode catalyst layer. Similar thinning of the cathode electrodes was observed by Liu et al [196]. The thickness was reduced by as much as 60% in the H₂

starved region in comparison to the 10% reduction of the surrounding areas. Based on the limiting current density distribution map of their measured MEA, this H₂ starved region has also the lowest value of current density. Finally, the role of water flooding on carbon corrosion of the catalyst was further entrenched by Li et al [330] who discovered after observing the MEA structure that carbon corrosion was more severe underneath the flow-plate lands where most water is expected to accumulate. Membrane thinning was in fact present in those under-land regions where thicknesses of 4 mm compared to 10 mm under the channels were observed.

4.3 Mitigation Strategies

4.3.1 Membrane swelling

Since swelling of polymer membranes is strongly dependant on their water content, it is plausible to operate the cell under less wet conditions. However, this will be at the expense of the ionic conductivity of the membrane which may cause greater decline in cell performance than what swelling would initiate. Controlling the access of external water to the cell through relative humidity can minimise the effect of swelling. The simulation of [296] showed how swelling stresses in the MEA become much higher with increasing RH. For example, the in-plane stresses in the membrane at a swelling strain of 0.05 were increased from 0 to 4 MPa as RH increases by only 10% (e.g. from 90 to 100% RH). Another model developed by Parrondo et al [220] suggests that the compressive force applied during cell assembly affects membrane swelling. Since compromising with the operating conditions is unwise for the sake of cell performance, it could be more sensible to modify instead the design of MEA and its assembly at an early stage to account for swelling.

Improving the mechanical and chemical properties of polymer membranes is probably the best approach to prevent swelling. A number of composite designs were developed in order to achieve minimal change in the membrane structure while keeping its conductivity at the highest level possible. Statterfield et al [223] suggested the addition of Titanium oxide (titania) for improving the elastic and plastic deformation behaviour of Nafion under changes in temperature and water concentration. These composite membranes (e.g. Nafion-titania) exhibited less strain hardening than Nafion and resulted in 40% reduction in the membrane's creep compared to Nafion. Similarly, the focus in [223] was to improve the elastic modulus of Nafion 115 membranes by adding titania particles. This composite membrane showed after 3000 min of operation ~40% more reduction of creeping compared to extruded and recast Nafion types under the same stress conditions. The water uptake of these composite membranes was examined by means of resistivity measurements of the membrane which was reduced noticeably during the early stages of testing due to water absorption. Although the resistivity of Nafion/titania composites decreased slightly faster than the extruded Nafion with water absorption, these composite membranes still have lower resistance than Nafion.

The design developed by Ballengee and Pintauro [298] performed well against swelling. They used a composite of 70 vol% 660 equivalent weight perfluorosulfonic acid and 30 vol% polyphenylsulfone with the aim of conserving the dimensional stability of the member after water uptake. The in-plane swelling was increased by only 5% from the original size of the membrane at room temperature. Another sulfonated poly design was examined in [299] which contains sulfonic acid groups on aliphatic side chains. Although this design exhibited good protonic conductivity of around 0.11 S.cm^{-1} , the swelling ratio was slightly higher than what was achieved in [298] ($\sim 12.9\%$ at 100°C). The difference between these two swelling ratios maybe attributed to the degree of sulfonation applied during membrane preparation as pointed out by Reyna-Valencia et al [236].

Various materials and preparation techniques were used in order to develop novel membrane designs that are capable of overcoming the effects of swelling. Parrondo et al [220] suggested treating the polymeric matrix of membranes with acids and heat to improve the mechanical properties of polymer against changes in water activity. The intention was to decrease the elastic forces of the matrix and the swelling pressure so that the water content in the membrane remains relatively high. This design actually improves the water-uptake of polymer remarkably. A different approach was suggested in [297] for blending sulfonated polyethersulfone (SPES) based membranes with polyacrylonitrile (PAN) and polysulfone (PSU) composites. Their design was based on creating sulfone cross-linking groups between the polymer chains to bridge the arylsulfonic acid groups of SPES with the aryl groups in PSU. Their idea was to control the sulfonation level of SPES in order to improve the solubility of the material as well as to reinforce its structure. This design gave good results as the swelling ratio decreased by more than 70% while the drop in the membrane's conductivity was just 25%.

A new class of polymers, known as microblock ionomer, was developed by Zhu et al [300] as a potential swelling-resistant membrane. The new design is based on sequence-distribution of sulphonic acid in ionomer backbone forming ionic and non-ionic spacer segments. This unique structure of phase-separation between hydrophilic and hydrophobic domains performed seemingly well against swelling. At a temperature of 120°C , the ion exchange capability of the membrane was more than 2meq g^{-1} .

Another approach to overcome swelling is to use gel-based membranes. These newly developed membranes are expected to be less susceptible to physical changes in aqueous solutions than traditional polymer membranes. Since their acidic structure (e.g. loosely bonded rather than formed within the polymer matrix) promotes protonic transport, their conductivity is not critically influenced by the hydration state or humidity of the reactant gases. The advantage of using this type of membrane becomes more pronounced at high operating temperatures where the majority of the water content in the membrane evaporates. Previous experimental studies [301-303] haven't reported any evidence of swelling of these gel membranes. Their focus was instead on the ionic conductivity and stability of these membranes under high temperature conditions. The measurements of [302]

suggested that the conductivity of these membranes was around 0.01 S cm^{-1} at 100°C . Similar results were obtained by [303] but at the slightly higher temperature of 115°C . The highest conductivity was reported in [301] where it reached a value of 0.1 S.cm^{-1} at room temperature and remained the same up to 85°C .

4.3.2 Corrosion

New materials were developed to prevent carbon corrosion in the catalyst layer of PEMFC. The prime intention was either to improve the electrochemical stability of the carbon particles or to replace the carbon support with novel materials completely. It is worth noting that the type of carbon substrate used for the catalyst layer plays a key role in the carbon corrosion of PEMFC. Okada et al [311] highlighted the advantages of using small surface area of carbon to support Pt particles in the catalysts. Graphitized carbon was the preferred option which showed improvements in catalyst durability and the overall performance of the cell. With this type of carbon, the amounts of Pt dissolution and CO_2 generated by the cell were quite small.

Carbon black is commonly used as a support for Pt catalysts in PEMFC. They offer a number of advantages that make them more attractive than other materials; this includes high porosity, high electrical conductivity, electrochemical stability, and nano size particles for the large active surface area of the catalyst.

Carbon black-supported Pt catalysts were previously examined in [211] and [304] against new designs of single and multi-walled carbon nanotubes (MWNT). The comparison was based on the change in Pt agglomeration and distribution at the catalyst surface after cell operation. Wang et al [304] found only nominal reduction in Pt loss by around 37% under constant potential when MWNT was utilized as catalyst support compared to 80% of carbon black Vulcan CX-72. The reason for this large difference in the results was due to Pt migration and ripening/aggregation which were enhanced by the carbon corrosion of the catalyst. Similarly, the Pt loss in [211] was reduced by almost half under accelerated degradation testing, e.g. 43% with single-walled buckpaper compared to 80% loss with Pt/carbon. According to [211] the slow formation of surface oxides in the buckpaper design was the main reason for such a significant difference in the corrosion resistance.

The addition of Titania (TiO_2) to carbon-supported platinum catalyst (Pt/C-TiO_2 or $\text{Pt-TiO}_2/\text{C}$) was suggested by Selvaganesh et al [307] and Sambandam et al [308]. Both studies have agreed about the role of Titania in improving the performance and durability of PEMFC. The measurements in [307] showed lower degradation in cell performance of the $\text{Pt-TiO}_2/\text{C}$ than the typical Pt/C catalyst. After 5000 test cycles, the degradation of $\text{Pt-TiO}_2/\text{C}$ was 10% compared to 28% for Pt/C . The effect of TiO_2 was evident from the FESEM (Field Emission Scanning Electron Microscopy) images which showed higher deformation of the MEA structure with Pt/C catalyst in comparison to the $\text{Pt/ TiO}_2/\text{C}$ design. Similar results from their galvanostatic measurements were shown in [308] indicating superior

stability of Pt/C-TiO₂. By inserting the data from the electrochemical impedance spectroscopy spectra to a Randles equivalent circuit, Warburg element, and transmission line models, they were able to simulate O₂ transport and estimate the electrical resistivity of the catalyst. They found that Pt/C catalysts limit the flow of O₂ through the micro-porous structure of the electrode. This is mainly due to the increase in the catalyst layer thickness originating from the lower loading of Pt on the carbon support. Alternatively, Huang et al [305] suggested replacing the carbon with Titania. Their analysis suggests that Pt/C catalyst suffered severe carbon corrosion, Pt dissolution, and catalyst particle sintering after 2000 potential cycles. Meanwhile, Pt/TiO₂ experienced only a small drop in voltage (~ 0.09V at 0.8 Acm⁻²) despite doubling the number of test cycles.

Metallic bipolar plates are the other components in PEMFC that are susceptible to corrosion. Various materials and coating techniques were utilized to avert corrosion of these plates including ferritic stainless steel (AISI446) [258]; metallic amorphous alloys (Fe₅₀Cr₁₈Mo₈AL₂C₁₄B₆) [312]; sulfuric acids (H₂SO₄) [256]; TiN coating by multi-arc ion plating [313]; stainless steel alloys (Fe-20Cr-4V) by thermal nitridation [314]; Polymer Polypyrrole and Polyaniline coating by cyclic voltammetry and painting [315]; and YZU001 like-diamond film by physical vapor deposition (PVD) [316]. The main focus has been on the polarisation characteristics of the cell but more specifically on the magnitude of ICR between the plates and the neighbouring carbon diffusion layers.

Lee et al [316] were able to compare the contact resistance of coated aluminium, stainless steel (SS316L), and graphite plates as a function of the compaction force. The contact resistance of coated aluminium was smaller than that of the uncoated stainless steel resulting in better cell performance. At a constant cell voltage of 0.6V, the current density of SS316L was 158 mA.cm⁻² whereas for coated aluminium was 232 mA.cm⁻². Graphite plates exhibited the best characteristics with the lowest contact resistance and slowest corrosion rate. Under 30kg of applied compaction force, the contact resistance of SS316L, coated aluminium, and graphite plates after 4hrs testing were 27, 25, and 15 mΩ, respectively. Jayaraj et al [312] suggested using metallic amorphous bulk alloy (Fe₅₀Cr₁₈Mo₈AL₂C₁₄B₆) as a potential replacement of stainless steel for bipolar plates. They found this new alloy to be more resistant to corrosion than the stainless steel SS316L when tested in 1 M H₂SO₄ +² ppm F⁻ solution at 75°C; the passive film formed on the surface was also found to be very stable.

In [314] and [315] concentration was focused more on reducing the interfacial contact resistance between the plates and the neighbouring GDL for maintaining optimum performance of the cell. Brady et al [314] applied a new coating alloy (Fe-20Cr-4V) on stainless steel plates using nitridation and pre-oxidation treatments whereas in [315] aluminium plates were painted with Polyaniline. The coating method proposed in [315] proved to be effective since the increase in ICR value was still at an acceptable level, e.g. ~ 0.3Ω cm² above 200 N cm⁻² compressive force.

The increase in ICR due to the formation of a passive film at the interface between the corroded plates and the neighbouring GDL is directly proportional to the thickness of the film. Once the film stops developing, the value of ICR stabilises. Yang et al [256] have suggested that a way to reduce the thickness of this n-type semiconductor film is to increase the concentration level of the sulphuric acid in the cell. This was their conclusion after they monitored the corrosion behaviour of SS316L bipolar plates in a simulated PEMFC cathode environment and at different sulphuric acid concentrations.

Another advantage of coating is to prevent the disassociation and dissolution of metallic cations such as Fe^{3+} , Ni^{2+} , Cu^{2+} , Cr^{3+} that can potentially contaminate other parts of the cell and poison the polymer membrane and catalyst layers. The review conducted by Cheng et al [318] highlighted the danger of small quantities of these impurities in damaging the anode, membrane, and cathode chemical properties and causing a drop in cell performance.

4.3.3 Ice formation

Numerous techniques can be applied to prevent ice formation from deteriorating the performance and lifetime of PEMFC. One way to achieve this is to introduce heat to the cell in order to maintain its thermal state above freezing. Sun et al [319], for example, suggested generating heat by mixing hydrogen and oxygen gases in the cathode channels to enable for catalytic hydrogen reaction. This method did not cause drop in cell performance and it was also safer to operate having the concentration of hydrogen not exceeding 40% of the total gas mix (H_2/O_2). Apparently, this method has enabled the temperature of the cell to be raised from cold start condition of -20°C to 0°C in 6 minutes with only a 20% hydrogen concentration.

Ge and Wang [284] were also able to increase the cell temperature to as high as 70°C and at the same time avoid significant Pt reduction from the active surface area of the catalyst. The trapped liquid water between Pt particles and ionomers in the cathode catalyst layer under -30°C cold-start caused the surface area to decrease by around 35% (e.g. ~ 73 to $47 \text{ m}^2 \text{ g}^{-1}$). According to the current and temperature distribution measurements of [320], the highest current density during failed cold start is occurring initially towards the reactant inlet regions of the cell; around 40-50% of the total cell current is produced in these regions. This finding suggests that it is more effective to apply external heat to the inlet rather than to other regions of the cell.

Purging the cell with dry gases is another method to overcome the effect of ice formation. The concept is to remove liquid water from the cell before it is transformed into ice at subfreezing temperatures. However, this process has to be repeated every time the cell is out of operation, i.e. it shuts down. Experimentalists tend to disagree about the duration needed for purging to achieve successful cold start operation of the cell. For example in [288], a duration of 120 s is suggested to be sufficient whereas in [320] much longer period of 2 hrs is recommended. Obviously the purging duration will be dependant on the design of the cell and its operating condition. Ge and Wang [288]

showed the effect of purging time on the amount of water extraction from the membrane and how it improves the performance of the cell. This was again confirmed in [263] when they compared the performance of the cell with and without purging under a temperature of -10°C . Despite the fact that the measurements were carried out at a low current density ($\sim 0.15 \text{ A.cm}^{-2}$), the current density dropped significantly without purging after just 15 s of operation. In contrast, the duration until failure was extended to 268 s when purging was used.

One of the main advantages of purging is to protect the PEMFC components from structural damages by subfreezing temperatures. The purging used in [267] was sufficient to maintain the catalyst structure unchanged under temperature cycles of -30°C in comparison to the damage with the non-purging condition as illustrated in Figure 10. The impact of purging is not only on the durability of PEMFC but on its performance as well. In [273], the cell failed to operate even at -5°C and at a low current density of no more than 200 mA.cm^{-2} when purging was not employed. The free water, which is expected to be trapped at the catalyst layer, can freeze hindering the access of reactants to the reaction sites of the catalyst and causing a performance drop.

It is important to set the relative humidity of the purging gases to a medium level, neither too dry nor too wet. Otherwise the cell can suffer from poor ionic conductivity of the reduced water amount in the membrane or from water flooding at the early stages of subsequent operating cycles. When Hou et al [321] increased the relative humidity of the purging gas from 16.6% to 64.9%, although no performance loss was detected after 20 freeze/thaw cycles, the flow channels were completely flooded with liquid water in the first cycle at high current density (1 A.cm^{-2}). Consequently, the MEA was more damaged at -30°C with an increase from the initial porosity by 10% compared to 2% of the drier purge gas.

Other parameters such as purging time, gas flow rate, cell current and temperature also determine how effective the purging process is. One may expect that if purging is happening quite frequently or for long duration, the cell membrane would dehydrate more easily. In fact, in [322] was shown that, for purging the cell, high flow rates and temperatures are the most influential factors. They examined different purging scenarios and found that raising the flow rate of the purging gas extracts more water than extending the purging duration for the same amount of purge gas. Furthermore, purging at ambient temperatures is inefficient.

Four gases have been mainly used for purging in PEMFC including air, H_2 , O_2 , and N_2 ; each of these gases performs differently. When Gavello et al [323] tried purging the cell with N_2 , air and H_2 gases, they found that the best combination is to use dry air and dry H_2 at the cathode and anode, respectively. With this purging strategy, MEAs exhibit the smallest loss in power density and minimal damage of their structure (e.g. loss of 7.6% after 20 Freeze/Thaw cycles and 19.3% after 30 cycles). The only disadvantage was that it encourages strong migration of Pt particles from the catalytic layer

towards the membrane. Alternatively, Cho et al [325] tried purging the anode with dry N₂ and the cathode with O₂. The performance degradation rate of the cell was significantly reduced from 2.3% to 0.06%, and the reduction in Pt utilisation of the catalyst was also very small (~ 3% during 7 testing cycles). Song and Kim [324] suggested purging only the cathode with dry air but not the anode since the damage of freezing on the anode is quite small; they tested various purging schemes and operating conditions to assess their effects in terms of Pt loss from the catalyst surface area and the mass transfer limitation. Purging the cell with antifreeze solutions is another alternative to the dry gas approach. Cho et al [325] used 30% methanol and 35% ethylene glycol solutions for purging and by doing so the performance degradation rate of the cell was reduced to – 0.16% and 0.47%, respectively.

Other researchers relied instead on improving the design of MEA against freeze/thaw degradation cycles. For example, Saito et al [291] suggested using membranes with low equivalent weight (EW) values and high amount of freezing water (e.g. weakly interacting water with ionic groups) in order to enhance the H⁺ conductivity. Wang et al [326] employed multi-walled carbon nanotubes (MWCNTs) to reinforce Nafion resin for enhancing the mechanical stability and tensile strength of the membrane. The increase in the H₂ oxidation current density of MWCNT-reinforced Nafion membrane was eventually lower compared to Nafion-112 (71% vs 109%). Song et al [327] added isopropyl alcohol and isopropyl butyl acetate to the catalytic ink of catalyst-coated membrane. These two designs not only improved the ionic resistance of the membrane but also exhibited less degradation in terms of the electrochemical active surface area and polarisation curves of the cell.

4.3.4 Flooding

The best way to avoid water flooding in PEMFC is probably to operate the cell under conditions which allow effective water extraction from the cell. Obviously operating the cell under low current densities minimises the risk of flooding, as a result of the proportional relationship between cell current and by-product water; thus water management becomes less of an issue. Nevertheless, increasing the temperature of the cell has two main advantages. First, it allows rapid evaporation of the residual water in the cell, thus preventing further water accumulation, and also it enhances the kinetics of the catalyst.

Ous and Arcoumanis [107] estimated the amount of water that can be removed from a single PEM cell for each 1deg temperature rise (~34nl/°C). Their in-situ visualisation of the cathode and anode flow channels showed that water disappears completely from the channels as the temperature reaches 60°C. The same happened when they increased the air flow rate to the high stoichiometry of 36 where water droplets on the surface of the channels were all blown away. Their measurements also suggest that, on average, temperature has a higher extraction rate of liquid water from the flow channels of the

cell than stoichiometric air (~34 nanoliter /°C vs. 26 nanoliter/°C). However, both of these operating parameters should not be excessive otherwise the membrane could become fully dehydrated.

An alternative method to prevent flooding in PEMFC is to use materials that can improve the transport of liquid water in the cell. For instance, loading the catalyst or GDL with hydrophobic substances such as poly tetrafluoroethylene (PTFE) helps to expel excess water from the void regions of these layers. Oh et al [331] have suggested moderate addition of copolymer P (VdF-Co-HFp) to the catalyst layers in order to improve the hydrophobic characteristics of catalysts and suppress water flooding. The improvement in the hydrophobicity of the catalyst was evident from the contact angle measurements of water droplets on the surface. These measurements showed a noticeable angle increase with added copolymer, e.g. contact angles were 36°, 86° and 105° with copolymer loading of 0, 2-5 and 10 wt%, respectively. The performance of the cell was enhanced both in terms of current density and ohmic resistance of the catalyst. However, excessive loading proved detrimental to the polarisation performance. When copolymer loading was increased from 5 to 10wt%, the current density of the cell dropped from 530 to 484 mA.cm⁻². The addition of oxygen permeable and hydrophobic dimethyl silicone oil (DSO) to the catalyst layer was also suggested by Li et al [332] in order to improve the water balance and oxygen accessibility to the catalyst cathode. Again, the hydrophobicity of the catalyst was increased remarkably with the addition of only 0.5 mg.cm⁻² of DSO, as evidence by the improvement in the limiting current density of the cell which was extended from 1.2 to 2 A.cm⁻².

Lin and Nguyen [333] stated that the cell can still operate with maximum gas and water transport mechanisms during flooding with a moderate addition of PTFE to GDL. When they compared the performance of the cell with different PTFE loading of Toray carbon paper (10, 20, and 30% PTFE), the paper with the medium PTFE content (e.g. 20%) showed the best performance. They argued that combination of hydrophobic pores for gas transport and hydrophilic pores for liquid water transport can give GDLs the ultimate design configuration against water flooding.

5. Water transport in PEMFC

Water in PEMFC originates from two main sources. It is either produced by ORR at the catalyst cathode or fed externally into the cell through the humidification or cooling gases. The amount of by-product water can be calculated directly from the current density of the cell. The amount of external water is, however, more difficult to estimate since it varies depending on the temperature, pressure and flow rate of the humid/ coolant gas used.

In general, water transport in PEMFC involves a complex interplay of processes. In the membrane, for example, there are three water fluxes during the operation of the cell known as electro-osmotic

drag, back diffusion and water generation. The effect of electro-osmotic drag on the water distribution is considered to be the dominant as many hydrogen ions drag water molecules when travelling from the anode to cathode. Meanwhile, the high concentration of the water generated at the cathode forces the water stream to diffuse back into the anode. The balance between these two fluxes is critical for maintaining a uniform water distribution across the membrane and hence an optimum ionic conductivity of the membrane. The effect of back diffusion becomes more significant at high current densities and particularly when the extraction rate of water from the cathode region is extremely low.

5.1 MEA and GDL structure

Various models [334-338] have been developed to simulate water transport mechanisms across polymer type membranes. The aim is to estimate the water diffusion rate during the operation of PEMFC including parameters like water transport and electro-osmotic drag coefficients (e.g. the water transport coefficient is defined as the ratio of net water flux across the membrane to water production, whereas the drag coefficient is the number of water molecules transported per proton). Interestingly enough, one of these models e.g. [335] is suggesting that aging has no influence on the water transport coefficient despite other studies [220-224, 228-230] where a significant change in the physical properties of aged membranes was detected. However, none of these studies have addressed the effect of water transport mechanism on membrane durability. This effect was rather related by other experimental and modelling investigations to the relative humidity condition of the cell.

Since increasing the RH of the reactant gases increases the rate of water flux across the membrane layer [335, 339] and results in higher release of fluoride ions from those membranes [30, 75, 340, 341], water transport in the membrane is expected to play a part in the fluoride emission of PEMFC. Water transport may also affect some of the mechanical, electrical, and chemical properties of the MEA like the porosity of GDL, polymer chains, and Pt distribution in the catalyst. The simulations carried out by Lin and Nguyen [233] showed how, by increasing the relative humidity of the reactant gases, the polymer chains in the membranes become more susceptible to unzipping.

The results presented in [30] showed an increase in the concentration level of fluoride ions by more than 3X (~450 ppb) after 800 hrs under highly water saturated operation (e.g. air humidity is 100% and hydrogen >100% RH). They suggested that the main cause for this was the water generated and the inlet water flow which could wash away the recast ionomer from the cathode catalyst continuously. Under the same humidity but slightly higher Nafion membrane loading (e.g. 100% RH at 33 wt % Nafion), Young et al [198] detected fluoride loss of around 25% after 440 hrs of AST ($60 \mu\text{mole cm}^{-2}$ from total MEA content of $230 \mu\text{mole cm}^{-2}$). Uchida et al [340] also found that, increasing the relative humidity of mixed gases ($\text{H}_2 + 10\% \text{ air}$, $\text{air} + 2\% \text{ H}_2$), increases the fluoride emission rate (FER) almost linearly. Raising RH from 0 to 90%, the FER using $\text{H}_2 + 10\% \text{ air}$ mixture increases from $3.5\text{-}10 \text{ nmol h}^{-1}$ whereas for $\text{air} + 2\% \text{ H}_2$ mixture the range of increase was from $1.25\text{-}7 \text{ nmol h}^{-1}$.

Apparently, fluoride emission rate does not only increase at the high RH operation but under low humidity conditions too. Kundu et al [201] detected significant loss of fluoride, by around 45%, when RH was reduced from 100% to 20% (e.g. from ~ 29 to $52 \mu\text{mol cm}^{-2}$). Again, the comparison made in [233] between different humidity conditions (e.g. 82%, 55%, and 36% RH) revealed much higher FER values at humidity levels lower than 50%.

The dissolution of Pt particles from the active surface area of the catalyst layer due to the increase in the RH of the reactant gases was reported previously in [245, 343]. Uchimura et al [245] found that the active surface area of the catalyst reduces dramatically by around 50% when RH increases from 30 to 100%. Furthermore, they claimed that if the membrane can survive low RH conditions, the dissolution of Pt particles would be significantly diminished. The reason for Pt dissolution at high RH conditions could be attributed to the enhanced ORR activity of the catalyst at the high hydration state of the membrane. It may also be due to water flooding which can cause fuel starvation in the cell and induction of a local potential on the electrodes [195, 196, 246, 247].

Migration of Pt_3Cr alloy particles from the catalyst layers under fully humidified conditions was observed in [30] and [193]. Xie et al [30] presented images showing chromium particles accumulated in the anode catalyst layer. One possible explanation for this is that the high current density they operated at ($> 1 \text{ A cm}^{-2}$) has generated excessive water facilitating chromium particles to be carried away by the back diffusion stream to the anode. Similarly, the Pt migration detected in [343] was found to be more severe at the cathode layer than the anode. When the cell was operated with three different levels of cathode inlet RH (e.g. 0, 50, and 100%) for 1500 cycles, the highest Pt loss from the catalyst cathode was at 100% RH [343]. According to their analysis, this was attributed to the corrosion of the carbon support which intensifies at higher RH.

The partial pressure of H_2 and O_2 tends to influence the distribution of Pt particles according to the simulations of [197]. Their model showed how relative local flux of H_2 and O_2 determines the location of Pt repositioning. This was validated by SEM images which revealed the formation of a Pt band closer to the anode or cathode catalyst layers depending on the operation pressure ratio of the reactant gases. For example, when the H_2/O_2 pressure was reduced to 20%, the Pt band appeared near to the anode catalyst layer (e.g. away by $4.3 \mu\text{m}$) rather than near to the cathode/ membrane interface when the pressure ratio is equal. In [193] the migration of Pt_3Cr particles was from both electrodes towards the membrane and in addition, they found that pure Pt particles are more susceptible to migration than Pt_3Cr alloy due to their electrochemical instability. This was concluded after observing that stronger migration is taking place at the pure-Pt anode catalyst.

The mechanical properties of GDL should also be affected by the water transport mechanism in PEMFC. Numerical simulations of the water transport through different types of GDL were carried out in numerous investigations [344-358]. The majority of these two- and three-dimensional models

suggest that the transport of liquid water through GDL is mainly dominated by the hydrophobic and morphological properties of the GDL including porosity, tortuosity, cross sectional area, thickness, and PTFE loading. Other design and operating factors such as the compaction force used for the cell assembly [125], operating temperature [346], stoichiometric ratio of reactant gases [347], and GDL wettability [348, 353] were also found to affect water diffusion in the GDL. It is expected that the more the water diffuses through the layer, the more the damage on the GDL structure can be. However, still more research work needs to be done in this area to understand this effect in depth.

5.2 Contamination

The effect of relative humidity on the degradation of PEMFC was previously associated to a number of factors such as membrane swelling [221, 230], membrane thinning [231, 232], creep formation and cracking [74, 233], fluoride concentration change [30, 75, 201, 341], catalyst particles migration [67, 68], carbon corrosion [48, 69, 244, 245], pin-hole formation [228-230, 234], hydrogen crossover [36, 70, 75] and local fuel starvation [195, 196, 246, 247].

Equally damaging as these factors is the kind of water used for the humidification of the reactant gases. Drinking water contains harmful contaminants such as Fe, Cu, Cr, Si, and Al that can potentially poison the MEA and cause performance decay of the cell. The concentration level of the contaminants determines the deterioration rate of the MEA. In [359], Fe concentration was initially less than 1ppm in their tested GORE-SELECT membrane. The level of Fe increased dramatically when external water was added to the cell under humid-air operation as evident from their MEA durability measurements which revealed higher fluoride release rate (FRR) than in the case of the cathode running with dry air (e.g. 1.6E-08 vs. 1.5E-07 g cm⁻² h⁻¹).

The corrosion of fuel cell stack components like metal bipolar plates, end plates or humidifier reservoir is another source of impurities. Liquid water may carry traces of metal ions such as Fe⁺² and Cu²⁺ to the MEA causing permanent defects to its electrical, mechanical, and chemical properties. The review of [318] highlighted the effects of these impurities on cell performance which were found to be detrimental particularly in terms of the cell electrode kinetics, conductivity, and mass transfer.

Probably the best example to demonstrate the role of water in transporting these harmful contaminants is from the experimental work of Pozio et al [360]. When they used two different end plates in the cell, e.g. stainless steel SS316L and aluminium Al, they discovered significant difference in fluoride release under the same testing conditions (14ppm for SS316L vs. 1.2ppm for Al). The pH level of water collected at the anode and cathode for SS316L was around 30% lower than in the case of the Al plate. Clearly the water was the primary agent for revealing such differences and transporting traces of contaminants.

5.3 Mitigation strategies

The effect of water transport on the degradation of PEMFC can be minimised if the amount of water moisture in the cell is kept small. However, as explained before in section 4.4.1, this has a dramatic impact on membrane conductivity and cell performance. The best solution could be to maintain the hydration level in the cell but reinforce the design of MEA to withstand levels of deterioration originating from the water transport mechanisms.

A number of composite membranes were developed in order to improve the electrochemical stability of MEA. Trogadas et al [361] added CeO₂ nanoparticles into Nafion membranes to reduce the fluoride emission rate from both electrodes. Without compromising in terms of proton conductivities and hydrogen crossover of the cell, the rate was lowered by more than one order of magnitude compared to a typical Nafion membrane (e.g. from 0.1 to 0.01 $\mu\text{mol h}^{-1} \text{cm}^{-2}$). Inaba et al [44] also suggested introducing an anti-gas crossover layer, a peroxide decomposition layer and Fe²⁺ ion-trap layer into the MEA design in order to prevent oxygen crossover and consequent formation of hydrogen peroxide and catalytic combustion at the anode. In addition, as mentioned in section 3.2, the MEA stability can be enhanced by impregnating the catalyst layer with alloys such as titanium [202], cobalt [188, 203], aluminium oxide [213], titanium dioxide [214], zirconium dioxide [215] and tin dioxide [216].

Some other composites were designed specifically to operate under low RH conditions [86, 34]. Su et al [86] used Pt/SiO₂/C for the anode catalyst aiming to achieve acceptable polarisation performance of the cell at low RH values. Indeed, the voltage and current density of their design cell (0.6V, 0.65Acm^{-2}) remained almost unchanged despite the significant drop in RH level at both the anode and cathode (e.g. RH reduced from 100% to 28%). Similarly, the Nafion-Teflon-phosphotungstic acid (NTPA) design of [34] had a marginal drop in cell voltage (~90mV) at the low RH values of 25%. It is worth noting that operating the cell at low RH using these types of self-humidifying membranes offers two advantages in terms of PEMFC durability. First, it reduces the number of hydration/dehydration cycles during the life span of the cell which often lead to mechanical failures of the MEA. The second advantage is minimising the risk for foreign particles to access the cell with humidified gases and cause damage to the MEA.

Finally, PEMFC membranes are chemically fragile. The quality of the water used in the humidification process of the reactant gases is another important requirement for achieving durable cells. Deionised water is preferable since no ionic impurities are present. However, in case impurities are introduced from other external sources, such as a humidifier reservoir or other cell components, installing a filtration system at the inlet of the cell would probably be the most effective way to reduce or even eliminate the effect of these impurities.

6. Concluding Remarks

The water management system does not only affect PEMFC performance but also its durability. A number of degradation factors such as the loss of active surface area of the catalyst, ionomer

dissolution, corrosion, contamination, and morphological damages of MEA and GDL were identified which are influenced by water formation, retention, accumulation and transport mechanisms within the cell.

It is difficult to determine accurately the impact of each of these water mechanisms on the deterioration rate of the cell as it varies depending on the design and the operating conditions of the cell. For example, the effect of water retention and accumulation becomes more severe when the cell operates at subfreezing temperatures. The volume expansion of liquid water due to the ice formation causes morphological damages to different parts of the cell which can accelerate the degradation process. Furthermore, the effect of these water mechanisms on cell durability can be classified into two main categories: aging and catastrophic. With aging, durability and performance behaviour of the cell tend to decline steadily over time whereas in the case of catastrophic ones the cell fails instantly. The role of water formation has been considered to fall into the ‘aging’ category as the loss of Pt active surface area and ionomer dissolution of the MEA happen interchangeably. A similar classification applies to the effect of water retention, accumulation and transport where changes in MEA and GDL properties including membrane swelling, porosity, corrosion of carbon catalyst support and metallic bipolar plates occur during the life-time of PEMFC. Only two factors, such as the formation of cell residual water into ice at subfreezing temperatures and the access of foreign contaminants by external humidification, are classified as catastrophic. These factors can lead to serious consequences such as membrane poisoning and catalytic combustion which cause an immediate termination of the PEMFC operation.

In conclusion, the effect of water mechanisms on PEMFC degradation can be minimised or even eliminated by (a) using advanced materials particularly for MEA and GDL to improve their stability (b) implementing effective strategies for extracting residual water from the cell, and (c) ensuring contamination-free operation of the cell to prevent poisoning of the membrane.

Nomenclature

ADT	accelerated durability test
AST	accelerated stress test
BPP	bipolar plate
BSEM	back scattered Electron Microscopy
CL	catalyst layer
CNF	carbon nanofibers
CNT	carbon nanotubes
DOE	department of energy
DSC	differential scanning calorimetry
DSO	dimethyl silicone oil
DWNT	double-walled nanotubes
EDX	energy dispersive X-ray
EMPA	electron microprobe analysis
ESEM	environmental scanning electron microscopy
EW	equivalent weight
GDBL	double micro porous layer
GDL	gas diffusion layer
GMPL	graded micro porous layer
HFP	european hydrogen and fuel cell technology platform
HOR	hydrogen oxidation reaction
ICR	interfacial contact resistance
FEP	ethylene propylene
FER	fluoride emission rate
FESEM	field emission scanning electron microscopy
FRR	fluoride release rate
M	membrane
MEA	membrane electrode assembly
MPL	micro porous layer
MVM	mean value model
MWNT	mutli-walled carbon nanotubes
NEDO	new energy and industrial technology development organisation
NTPA	nafion-teflon-phosphotungstic acid
ORR	oxygen reduction reaction
PAN	polyacrylonitrile
PEMFC	proton exchange membrane fuel cell
PFSI	perflurosulfonete ionomer
PSU	polysulfone
PTFE	polytetrafluoroethylene
PVD	physical vapor deposition
RH	relative humidity
SEM	scanning electron microscopy
SPES	sulfonated polyethersulfone
SWNT	single-walled nanotubes
TEM	transmission electron microscopy
λ_{air}	air stoichiometry

References

- [1] Colella W. G., Timme R. J., Brouwer J., Sammes N. M. "Fuel cell efficiency can exceed 50% at peak power" *Journal of Power Sources*, In Press, Accepted Manuscript (2011).
- [2] Jason Marcinkoski, Brian D. James, Jeff A. Kalinoski, Walt Podolski, Thomas Benjamin and John Kopasz "Manufacturing process assumptions used in fuel cell system cost analyses" *Journal of Power Sources* Volume 196, Issue 12, pp. 5282-5292 (2011)
- [3] N. Rajalakshmi, K.S. Dhathathreyan "Nanostructured platinum catalyst layer prepared by pulsed electrodeposition for use in PEM fuel cells" *International Journal of Hydrogen Energy*, Volume 33, Issue 20, pp. 5672-5677 (2008)
- [4] Ashkan Esmaeilifar, Soosan Rowshanzamir, Mohammad H. Eikani, Ehsan Ghazanfari "Preparation of low-platinum-loading electrocatalysts using electroless deposition method for proton exchange membrane fuel cell systems" *Electrochimica Acta*, Volume 56, Issue 1, pp. 271-277(2010)
- [5] Seunghee Woo, In Kim, Jae Kwang Lee, Sungyool Bong, Jaeyoung Lee, Hasuck Kim "Preparation of cost-effective Pt-Co electrodes by pulse electrodeposition for PEMFC electrocatalysts" *Electrochimica Acta*, Volume 56, Issue 8, pp. 3036-3041(2011)
- [6] S. Martin, P.L. Garcia-Ybarra, J.L. Castillo "High platinum utilization in ultra-low Pt loaded PEM fuel cell cathodes prepared by electrospraying" *International Journal of Hydrogen Energy*, Volume 35, Issue 19 pp. 10446-10451 (2010)
- [7] Roswitha Zeis, Anant Mathur, Greg Fritz, Joe Lee, Jonah Erlebacher "Platinum-plated nanoporous gold: An efficient, low Pt loading electrocatalyst for PEM fuel cells" *Journal of Power Sources*, Volume 165, Issue 1, pp. 65-72 (2007)
- [8] M. Prasanna, E.A. Cho, H.-J. Kim, T.-H. Lim, I.-H. Oh, Sung-Ahn Hong "Effects of platinum loading on performance of proton-exchange membrane fuel cells using surface-modified Nafion membranes" *Journal of Power Sources*, Volume 160, Issue 1, pp. 90-96 (2006).
- [9] Yuan Yuan, Joshua A. Smith, Gabriel Goenaga, Di-Jia Liu, Zhiping Luo, Jingbo Liu "Platinum decorated aligned carbon nanotubes: Electrocatalyst for improved performance of proton exchange membrane fuel cells" *Journal of Power Sources*, Volume 196, Issue 15, pp. 6160-6167 (2011)
- [10] H. Perez, A. Morin, L. Akroud, C. Cremona, B. Baret, J. Haccoun, S. Escribano, A. Etcheberry "Evidence for high performances of low Pt loading electrodes based on capped platinum electrocatalyst and carbon nanotubes in fuel cell devices" *Electrochimica Acta*, Volume 55, Issue 7, pp. 2358-2362 (2010)
- [11] R.K. Ahluwalia, X. Wang, J. Kwon, A. Rousseau, J. Kalinoski, B. James, J. Marcinkoski "Performance and cost of automotive fuel cell systems with ultra-low platinum loadings" *Journal of Power Sources*, Volume 196, Issue 10, pp. 4619-4630 (2011)
- [12] Bin Wang "Recent development of non-platinum catalysts for oxygen reduction reaction" *Journal of Power Sources*, Volume 152, pp. 1-15 (2005)
- [13] Paolo Agnolucci "Hydrogen infrastructure for the transport sector" *International Journal of Hydrogen Energy*, Volume 32, Issue 15, pp. 3526-3544 (2007)

- [14] Greg Frenette, Daniel Forthoffer “Economic & commercial viability of hydrogen fuel cell vehicles from an automotive manufacturer perspective” International Journal of Hydrogen Energy, Volume 34, Issue 9, pp. 3578-3588 (2009)
- [15] Tasneem Abbasi, S.A. Abbasi ‘Renewable’ hydrogen: Prospects and challenges” Renewable and Sustainable Energy Reviews, Volume 15, Issue 6, pp. 3034-3040 (2011)
- [16] Andreas Pastowski, Thomas Grube “Scope and perspectives of industrial hydrogen production and infrastructure for fuel cell vehicles in North Rhine-Westphalia” Energy Policy, Volume 38, Issue 10, pp. 5382-5387(2010)
- [17] F. Markert, S.K. Nielsen, J.L. Paulsen, V. Andersen “Safety aspects of future infrastructure scenarios with hydrogen refuelling stations” International Journal of Hydrogen Energy, Volume 32, Issue 13, pp.2227-2234 (2007)
- [18] Vivek P. Utgikar, Todd Thiesen “Safety of compressed hydrogen fuel tanks: Leakage from stationary vehicles” Technology in Society, Volume 27, Issue 3, pp. 315-320 (2005)
- [19] U. Schmidchen “FUELS - SAFETY | Hydrogen: Overview” Encyclopedia of Electrochemical Power Sources, pp. 519-527 (2009)
- [20] R.K. Ahluwalia, T.Q. Hua, J.-K. Peng, S. Lasher, K. McKenney, J. Sinha, M. Gardiner “Technical assessment of cryo-compressed hydrogen storage tank systems for automotive applications” International Journal of Hydrogen Energy, Volume 35, Issue 9, pp. 4171-4184 (2010)
- [21] Jinyang Zheng, Xianxin Liu, Ping Xu, Pengfei Liu, Yongzhi Zhao, Jian Yang “Development of high pressure gaseous hydrogen storage technologies” International Journal of Hydrogen Energy, In Press, Corrected Proof, Available online 15 April 2011
- [22] Jorgensen, S.W.“Hydrogen storage tanks for vehicles: Recent progress and current status” Current Opinion in Solid State and Materials Science, Volume 15, Issue 2, pp. 39-43 (2011)
- [23] R.S. Gemmen, C.D. Johnson, “Evaluation of fuel cell system efficiency and degradation at development and during commercialization” Journal of Power Sources, Volume 159, Issue 1, pp. 646-655 (2006)
- [24] Yun Wang, Ken S. Chen, Jeffrey Mishler, Sung Chan Cho, Xavier Cordobes Adroher ”A review of polymer electrolyte membrane fuel cells: Technology, applications, and needs on fundamental research” Applied Energy, Volume 88, Issue 4, pp. 981-1007 (2011).
- [25] M. Marrony “Fuel Cell – Overview| Lifetime Prediction” Encyclopedia of Electrochemical Power Sources, pp. 297-308 (2009)
- [26] R. Lin, B. Li, Y.P. Hou, J.M. Ma “Investigation of dynamic driving cycle effect on performance degradation and micro-structure change of PEM fuel cell” International Journal of Hydrogen Energy, Volume 34, Issue 5, pp. 2369-2376 (2009)
- [27] M. Marrony, R. Barrera, S. Quenet, S. Ginocchio, L. Montelatici, A. Aslanides “Durability study and lifetime prediction of baseline proton exchange membrane fuel cell under severe operating conditions” Journal of Power Sources, Volume 182, Issue 2, pp. 469-475 (2008).
- [28] J. Zhang, R.N. Carter, P.T. Yu, W. Gu, F.T. Wagner, H.A. Gasteiger “Fuel Cells – Proton Exchange Membrane Fuel Cells | Catalysts: Life-Limiting Considerations” Encyclopedia of Electrochemical Power Sources, pp. 626-638 (2009)
- [29] S. -Y. Ahn, S. -J. Shin, H. Y. Ha, S. -A. Hong, Y. -C. Lee, T. W. Lim, I. -H. Oh, “Performance and lifetime analysis of the kW-class PEMFC stack”, Journal of Power Sources, Volume 106, Issues 1-2, pp. 295-303 (2002)

- [30] Jian Xie, David L. Wood III, David M. Wayne, Thomas A. Zawodzinski, Plamen Atanassov, and Rodney L. Borup "Durability of PEFCs at High Humidity Conditions" *J. Electrochem. Soc.*, Volume 152, Issue 1, pp. A104-A113 (2005)
- [31] J. Scholte, N. Berg, P. Wilde, L. Jörissen, J. Garche "Development and performance of a 10 kW PEMFC stack" *Journal of Power Sources*, Volume 127, Issues 1-2, pp. 206-212 (2004)
- [32] J. Yu, T.Matsuura, Y. Yoshikawa,M.N. Islam,M. Hori, *Electrochem. Solid-State Letters* "In Situ Analysis of Performance Degradation of a PEMFC under Nonsaturated Humidification" *Electrochemical and Solid-State Letters*, Volume 8, Issue 3, pp. A156-A158 (2005)
- [33] Michael W. Fowler, Ronald F. Mann, John C. Amphlett, Brant A. Peppley, Pierre R. Roberge "Incorporation of voltage degradation into a generalised steady state electrochemical model for a PEM fuel cell" *Journal of Power Sources*, Volume 106, Issues 1-2, pp. 274-283(2002)
- [34] H. Xu, M. Wu, Y. Liu, V. Mittal, R. Vieth, H.R. Kunz, L.J. Bonville, J.M. Fenton "Durability of Nafion-Teflon-Phosphotungstic Acid Composite Membranes in PEM Fuel Cells at 100{degree sign}C and 25%RH" *ECS Transactions*, Volume 3 Issue 1, pp. 561-568 (2006)
- [35] Chih-Wei Lin, Chi-Hui Chien, Jinzhu Tan, Yuh J. Chao, J.W. Van Zee "Chemical degradation of five elastomeric seal materials in a simulated and an accelerated PEM fuel cell" *Journal of Power Sources*, Volume 196, Issue 4, pp. 1955-1966 (2011)
- [36] Feng-Yuan Zhang, Suresh G. Advani, Ajay K. Prasad, Mary E. Boggs, Shawn P. Sullivan, Thomas P. Beebe Jr. "Quantitative characterization of catalyst layer degradation in PEM fuel cells by X-ray photoelectron spectroscopy" *Electrochimica Acta*, Volume 54, Issue 16, pp. 4025-4030 (2009)
- [37] Shengsheng Zhang, Xiao-Zi Yuan, Jason Ng Cheng Hin, Haijiang Wang, K. Andreas Friedrich, Mathias Schulze "A review of platinum-based catalyst layer degradation in proton exchange membrane fuel cells" *Journal of Power Sources*, Volume 194, Issue 2, pp. 588-600 (2009)
- [38] Yongtaek Lee, Bosung Kim, Yongchan Kim, Xianguo Li "Effects of a microporous layer on the performance degradation of proton exchange membrane fuel cells through repetitive freezing" *Journal of Power Sources*, Volume 196, Issue 4, pp. 1940-1947 (2011)
- [39] Jinfeng Wu, Jonathan J. Martin, Francesco P. Orfino, Haijiang Wang, Colleen Legzdins, Xiao-Zi Yuan, Colin Sun "In situ accelerated degradation of gas diffusion layer in proton exchange membrane fuel cell: Part I: Effect of elevated temperature and flow rate" *Journal of Power Sources*, Volume 195, Issue 7, pp. 1888-1894 (2010)
- [40] Junhyun Cho, Taehun Ha, Jaeman Park, Han-Sang Kim, Kyoungdoug Min, Eunsook Lee, Jy-Young Jyoung "Analysis of transient response of a unit proton-exchange membrane fuel cell with a degraded gas diffusion layer" *International Journal of Hydrogen Energy*, Volume 36, Issue 10, pp. 6090-6098 (2011)
- [41] Christoph Hartnig, Thomas J. Schmidt "On a new degradation mode for high-temperature polymer electrolyte fuel cells: How bipolar plate degradation affects cell performance" *Electrochimica Acta*, Volume 56, Issue 11, pp. 4237-4242 (2011)
- [42] Y. Hung, H. Tawfik, D. Mahajan "Durability and characterization studies of polymer electrolyte membrane fuel cell's coated aluminum bipolar plates and membrane electrode assembly" *Journal of Power Sources*, Volume 186, Issue 1, pp. 123-127 (2009)
- [43] Adam Z. Weber "Gas-Crossover and Membrane-Pinhole Effects in Polymer-Electrolyte Fuel Cells" *Journal of The Electrochemical Society*, 155 (6) B521-B531 (2008)

- [44] Minoru Inaba, Taro Kinumoto, Masayuki Kiriake, Ryota Umebayashi, Akimasa Tasaka, Zempachi Ogumi “Gas crossover and membrane degradation in polymer electrolyte fuel cells” *Electrochimica Acta*, Volume 51, Issue 26, pp. 5746-5753 (2006)
- [45] Wei-Mon Yan, Hsin-Sen Chu, Meng-Xi Lu, Fang-Bor Weng, Guo-Bin Jung, Chi-Yuan Lee “Degradation of proton exchange membrane fuel cells due to CO and CO₂ poisoning” *Journal of Power Sources*, Volume 188, Issue 1, pp. 141-147 (2009)
- [46] Georgeta Postole, Aline Auroux “The poisoning level of Pt/C catalysts used in PEM fuel cells by the hydrogen feed gas impurities: The bonding strength” *International Journal of Hydrogen Energy*, Volume 36, Issue 11, pp. 6817-6825 (2011)
- [47] A. A. Kulikovsky, H. Scharmann, K. Wippermann “Dynamics of fuel cell performance degradation” *Electrochemistry Communications*, Volume 6, Issue 1, pp. 75-82 (2004)
- [48] Rod L. j, John R. Davey, Fernando H. Garzon, David L Wood, Michael A. Inbody “PEM fuel cell electrocatalyst durability measurements” *Journal of Power Sources*, Volume 163, Issue 1, pp. 76-81 (2006)
- [49] A.D. Modestov, M.R. Tarasevich, V.Ya. Filimonov, N.M. Zagudaeva “Degradation of high temperature MEA with PBI-H₃PO₄ membrane in a life test” *Electrochimica Acta*, Volume 54, Issue 27, pp. 7121-7127 (2009)
- [50] Héctor R. Colón-Mercado, Branko N. Popov “Stability of platinum based alloy cathode catalysts in PEM fuel cells” *Journal of Power Sources*, Volume 155, Issue 2, pp. 253-263 (2006)
- [51] Karel Bouzek, Martin Paidar, Jakub Mališ, Ivo Jakubec, Luděk Janík “Influence of hydrogen contamination by mercury on the lifetime of the PEM-type fuel cell” *Electrochimica Acta*, Volume 56, Issue 2, pp. 889-895 (2010)
- [52] Mei Cai, Martin S. Ruthkosky, Belabbes Merzougui, Swathy Swathirajan, Michael P. Balogh, Se H. Oh “Investigation of thermal and electrochemical degradation of fuel cell catalysts” *Journal of Power Sources*, Volume 160, Issue 2, PP. 977-986 (2006)
- [53] Jinfeng Wu, Xiao Zi Yuan, Jonathan J. Martin, Haijiang Wang, Jiujun Zhang, Jun Shen, Shaohong Wu, Walter Merida “A review of PEM fuel cell durability: Degradation mechanisms and mitigation strategies” *Journal of Power Sources*, Volume 184, Issue 1, pp. 104-119 (2008)
- [54] Xiao-Zi Yuan, Shengsheng Zhang, Haijiang Wang, Jinfeng Wu, Jian Colin Sun, Renate Hiesgen, K. Andreas Friedrich, Matthias Schulze, Andrea Haug “Degradation of a polymer exchange membrane fuel cell stack with Nafion® membranes of different thicknesses: Part I. In situ diagnosis” *Journal of Power Sources*, Volume 195, Issue 22, pp. 7594-7599 (2010)
- [55] Gilles Meyer, Gérard Gebel, Laurent Gonon, Philipe Capron, Didier Marscaq, Catherine Marestin, Régis Mercier “Degradation of sulfonated polyimide membranes in fuel cell conditions” *Journal of Power Sources*, Volume 157, Issue 1, pp. 293-301 (2006)
- [56] Yuyan Shao, Geping Yin, Yunzhi Gao, and Pengfei Shi “Durability Study of Pt/C and Pt/CNTs Catalysts under Simulated PEM Fuel Cell Conditions” *Journal of the Electrochemical Society* Volume 153, Issue 6, pp. A1093-A1097 (2006)
- [57] J. Zhang, K. Sasaki, E. Sutter, R. R. Adzic “Stabilization of Platinum Oxygen-Reduction Electrocatalysts Using Gold Clusters” *Science*, Volume 315, 220-222 (2007)
- [58] Zhi-yong XIE, Gu-yin JIN, Min ZHANG, Zhe-an SU, Ming-yu ZHANG, Jian-xun CHEN, Qi-zhong HUANG “Improved properties of carbon fiber paper as electrode for fuel cell by coating pyrocarbon via CVD method” *Transactions of Nonferrous Metals Society of China*, Volume 20, Issue 8, pp. 1412-1417 (2010)

[59] Jui-Hsiang Lin, Wei-Hung Chen, Shih-Hsuan Su, Yuan-Kai Liao, Tse-Hao Ko “Carbon film coating on gas diffusion layer for proton exchange membrane fuel cells” Journal of Power Sources, Volume 184, Issue 1, pp. 38-43 (2008)

[60] Yusuke Hiramitsu, Hitoshi Sato, Kenji Kobayashi, Michio Hori “Controlling gas diffusion layer oxidation by homogeneous hydrophobic coating for polymer electrolyte fuel cells” Journal of Power Sources, Volume 196, Issue 13, pp. 5453-5469 (2011)

[61] H. Tawfik, Y. Hung, D. Mahajan “Metal bipolar plates for PEM fuel cell—A review” Journal of Power Sources, Volume 163, Issue 2, pp. 755-767 (2007)

[62] Moucheng Li, Suzhen Luo, Chaoliu Zeng, Jianian Shen, Haichao Lin, Chunan Cao “Corrosion behavior of TiN coated type 316 stainless steel in simulated PEMFC environments” Corrosion Science, Volume 46, Issue 6, pp. 1369-1380 (2004)

[63] Ji Hun Park, Dongjin Byun, Joong Kee Lee “Employment of fluorine doped zinc tin oxide (ZnSnO_x:F) coating layer on stainless steel 316 for a bipolar plate for PEMFC” Materials Chemistry and Physics, Volume 128, Issues 1-2, pp. 39-43 (2011)

[64] E.A. Cho, U.-S. Jeon, S.-A. Hong, I.-H. Oh, S.-G. Kang “Performance of a 1 kW-class PEMFC stack using TiN-coated 316 stainless steel bipolar plates” Journal of Power Sources, Volume 142, Issues 1-2, pp. 177-183 (2005)

[65] Y.J. Ren, C.L. Zeng “Effect of conducting composite polypyrrole/polyaniline coatings on the corrosion resistance of type 304 stainless steel for bipolar plates of proton-exchange membrane fuel cells” Journal of Power Sources, Volume 182, Issue 2, pp. 524-530 (2008)

[66] Young-Hoon Yun “Deposition of gold–titanium and gold–nickel coatings on electropolished 316L stainless steel bipolar plates for proton exchange membrane fuel cells” International Journal of Hydrogen Energy, Volume 35, Issue 4, pp. 1713-1718 (2010)

[67] M.F. Mathias, R. Makharia, H.A. Gasteiger, J.J. Conley, T.J. Fuller, G.J. Gittleman, S.S. Kocha, D.P. Miller, C.K. Mittelsteadt, T. Xie, S.G. Yan, P.T. Yu “Two Fuel Cell Cars In Every Garage?” The Electrochemical Society Interface, Volume 14, No. 3, pp. 24-35 (2005)

[68] Wu Bi, Qunhui Sun, Yulin Deng, Thomas F. Fuller “The effect of humidity and oxygen partial pressure on degradation of Pt/C catalyst in PEM fuel cell” Electrochimica Acta, Volume 54, Issue 6, pp. 1826-1833 (2009)

[69] D. A. Stevens, M. T. Hicks, G. M. Haugen, and J. R. Dahn, “Ex Situ and In Situ Stability Studies of PEMFC Catalysts”, Journal of the Electrochemical Society, Volume 152, Issue 12, pp. A2309-A2315 (2005)

[70] Minoru Inaba, Taro Kinumoto, Masayuki Kiriake, Ryota Umebayashi, Akimasa Tasaka, Zempachi Ogumi “Gas crossover and membrane degradation in polymer electrolyte fuel cells” Electrochimica Acta, Volume 51, Issue 26, pp. 5746-5753 (2006)

[71] N. Yousfi-Steiner, Ph. Moçotéguy, D. Candusso, D. Hissel “A review on polymer electrolyte membrane fuel cell catalyst degradation and starvation issues: Causes, consequences and diagnostic for mitigation” Journal of Power Sources, Volume 194, Issue 1, pp. 130-145 (2009)

[72] Shengsheng Zhang, Xiao-Zi Yuan, Jason Ng Cheng Hin, Haijiang Wang, Jinfeng Wu, K. Andreas Friedrich, Mathias Schulze “Effects of open-circuit operation on membrane and catalyst layer degradation in proton exchange membrane fuel cells” Journal of Power Sources, Volume 195, Issue 4, pp. 1142-1148 (2010)

[73] Minoru Inaba, Masashi Sugishita, Junpei Wada, Koichi Matsuzawa, Hirohisa Yamada, Akimasa Tasaka “Impacts of air bleeding on membrane degradation in polymer electrolyte fuel cells” Journal of Power Sources, Volume 178, Issue 2, pp. 699-705 (2008)

- [74] Ting-Chu Jao, Guo-Bin Jung, Pei-Hung Chi, Shih-Tsung Ke, Shih-Hung Chan "Investigation of degradation behavior of membrane electrode assembly with polytetrafluoroethylene/Nafion composite membrane" *Journal of Power Sources*, Volume 196, Issue 4, pp. 1818-1825 (2011)
- [75] Karachakorn Panha, Michael Fowler, Xiao-Zi Yuan, Haijiang Wang "Accelerated durability testing via reactants relative humidity cycling on PEM fuel cells" *Applied Energy*, Volume 93, pp. 90-97, 2012
- [76] G.J.M. Janssen, E.F. Sitters, A. Pfrang "Proton-exchange-membrane fuel cells durability evaluated by load-on/off cycling" *Journal of Power Sources*, Volume 191, Issue 2, pp. 501-509 (2009)
- [77] Maji Luo, Chengyong Huang, Wei Liu, Zhiping Luo, Mu Pan "Degradation behaviors of polymer electrolyte membrane fuel cell under freeze/thaw cycles" *International Journal of Hydrogen Energy*, Volume 35, Issue 7, pp. 2986-2993 (2010)
- [78] Rod Borup, Jeremy Meyers, Bryan Pivovar, Yu Seung Kim, Rangachary Mukundan, Nancy Garland, Deborah Myers, Mahlon Wilson, Fernando Garzon, David Wood, Piotr Zelenay, Karen More, Ken Stroh, Tom Zawodzinski, James Boncella, James E. McGrath, Minoru Inaba, Kenji Miyatake, Michio Hori, Kenichiro Ota, Zempachi Ogumi, Seizo Miyata, Atsushi Nishikata, Zyun Siroma, Yoshiharu Uchimoto, Kazuaki Yasuda, Kenichi Kimijima, and Norio Iwashita, "Scientific Aspects of Polymer Electrolyte Fuel Cell Durability and Degradation," *Chemical Reviews*, Volume 107, pp. 3904-3951 (2007)
- [79] Hiroshi Ito, Tetsuhiko Maeda, Akihiro Nakano, Hiroyasu Takenaka, "Properties of Nafion membranes under PEM water electrolysis conditions" *International Journal of Hydrogen Energy*, Volume 36, Issue 17, pp. 10527-10540 (2011)
- [80] J. Larminie, A. Dicks, *Fuel Cell Systems Explained*, second ed., John Wiley & Sons Ltd. pp. 70-71 (2003)
- [81] Aidan Li, Siew Hwa Chan, Nam-trung Nguyen, "Anti-flooding cathode catalyst layer for high performance PEM fuel cell" *Electrochemistry Communications*, Volume 11, Issue 4, pp. 897-900 (2009)
- [82] Wen-Kai Chao, Chih-Ming Lee, Du-Cheng Tsai, Chih-Cheng Chou, Kan-Lin Hsueh, Fuh-Sheng Shieu, "Improvement of the proton exchange membrane fuel cell (PEMFC) performance at low-humidity conditions by adding hygroscopic γ -Al₂O₃ particles into the catalyst layer" *Journal of Power Sources*, Volume 185, Issue 1, pp. 136-142 (2008)
- [83] Zhili Miao, Hongmei Yu, Wei Song, Dan Zhao, Lixing Hao, Baolian Yi, Zhigang Shao , "Effect of hydrophilic SiO₂ additive in cathode catalyst layers on proton exchange membrane fuel cells" *Electrochemistry Communications*, Volume 11, Issue 4, pp. 787-790 (2009)
- [84] Un Ho Jung, Ki Tae Park, Eun Hee Park, Sung Hyun Kim, "Improvement of low-humidity performance of PEMFC by addition of hydrophilic SiO₂ particles to catalyst layer" *Journal of Power Sources*, Volume 159, Issue 1, pp. 529-532 (2006)
- [85] Singaram Vengatesan, Hyoung-Juhn Kim, Sang-Yeop Lee, EunAe Cho, Heung Yong Ha, In-Hwan Oh, Seong-Ahn Hong, Tae-Hoon Lim, "High temperature operation of PEMFC: A novel approach using MEA with silica in catalyst layer" *International Journal of Hydrogen Energy*, Volume 33, Issue 1, pp. 171-178 (2008)
- [86] Hua-Neng Su, Li-Jun Yang, Shi-Jun Liao, Qiao Zeng, "Membrane electrode assembly with Pt/SiO₂/C anode catalyst for proton exchange membrane fuel cell operation under low humidity conditions" *Electrochimica Acta*, Volume 55, Issue 28, pp. 8894-8900 (2010)
- [87] Ahmet Turhan, Soowhan Kim, Marta Hatzell, Matthew M. Mench , "Impact of channel wall hydrophobicity on through-plane water distribution and flooding behavior in a polymer electrolyte fuel cell" *Electrochimica Acta*, Volume 55, Issue 8, pp. 2734-2745 (2010)
- [88] Jin Hyun Nam, Kyu-Jin Lee, Gi-Suk Hwang, Charn-Jung Kim, Massoud Kaviani "Microporous layer for water morphology control in PEMFC" *International Journal of Heat and Mass Transfer*, Volume 52, Issues 11-12, pp. 2779-2791 (2009)

- [89] Tak Cheung Yau, Massimiliano Cimenti, Xiaotao Bi, Jürgen Stumper, "Effects of cathode gas diffusion layer design on polymer electrolyte membrane fuel cell water management and performance" *Journal of Power Sources*, Volume 196, Issue 22, pp. 9437-9444 (2011)
- [90] Zijie Lu, Michael M. Daino, Cody Rath, Satish G. Kandlikar, "Water management studies in PEM fuel cells, part III: Dynamic breakthrough and intermittent drainage characteristics from GDLs with and without MPLs" *International Journal of Hydrogen Energy*, Volume 35, Issue 9, pp. 4222-4233 (2010)
- [91] Wei-Mon Yan, Dong-Kai Wu, Xiao-Dong Wang, Ai-Lien Ong, Duu-Jong Lee, Ay Su, "Optimal microporous layer for proton exchange membrane fuel cell" *Journal of Power Sources*, Volume 195, Issue 17, pp. 5731-5734 (2010)
- [92] Wei Dai, Haijiang Wang, Xiao-Zi Yuan, Jonathan Martin, Jun Shen, Mu Pan, Zhiping Luo, "Measurement of water transport rates across the gas diffusion layer in a proton exchange membrane fuel cell, and the influence of polytetrafluoroethylene content and micro-porous layer" *Journal of Power Sources*, Volume 188, Issue 1, pp. 122-126 (2009)
- [93] M.S. Ismail, T. Damjanovic, D.B. Ingham, L. Ma, M. Pourkashanian, "Effect of polytetrafluoroethylene-treatment and microporous layer-coating on the in-plane permeability of gas diffusion layers used in proton exchange membrane fuel cells" *Journal of Power Sources*, Volume 195, Issue 19, pp. 6619-6628 (2010)
- [94] Minjeh Ahn, Yong-Hun Cho, Yoon-Hwan Cho, Jinho Kim, Namgee Jung, Yung-Eun Sung, "Influence of hydrophilicity in micro-porous layer for polymer electrolyte membrane fuel cells" *Electrochimica Acta*, Volume 56, Issue 5, pp. 2450-2457 (2011)
- [95] Xiaoli Wang, Huamin Zhang, Jianlu Zhang, Haifeng Xu, Xiaobing Zhu, Jian Chen, Baolian Yi, "A bi-functional micro-porous layer with composite carbon black for PEM fuel cells" *Journal of Power Sources*, Volume 162, Issue 1, pp. 474-479 (2006)
- [96] Jacob M. LaManna, Satish G. Kandlikar, "Determination of effective water vapor diffusion coefficient in pemfc gas diffusion layers" *International Journal of Hydrogen Energy*, Volume 36, Issue 8, pp. 5021-5029 (2011)
- [97] Chung-Jen Tseng, Shih-Kun Lo, "Effects of microstructure characteristics of gas diffusion layer and microporous layer on the performance of PEMFC" *Energy Conversion and Management*, Volume 51, Issue 4, pp. 677-684 (2010)
- [98] F.E. Hizir, S.O. Ural, E.C. Kumbur, M.M. Mench, "Characterization of interfacial morphology in polymer electrolyte fuel cells: Micro-porous layer and catalyst layer surfaces" *Journal of Power Sources*, Volume 195, Issue 11, pp. 3463-3471 (2010)
- [99] Tatsumi Kitahara, Toshiaki Konomi, Hironori Nakajima, "Microporous layer coated gas diffusion layers for enhanced performance of polymer electrolyte fuel cells" *Journal of Power Sources*, Volume 195, Issue 8, pp. 2202-2211 (2010)
- [100] Zhigang Zhan, Jinsheng Xiao, Dayong Li, Mu Pan, Runzhang Yuan, "Effects of porosity distribution variation on the liquid water flux through gas diffusion layers of PEM fuel cells" *Journal of Power Sources*, Volume 160, Issue 2, pp. 1041-1048 (2006)
- [101] Haolin Tang, Shenlong Wang, Mu Pan, Runzhang Yuan, "Porosity-graded micro-porous layers for polymer electrolyte membrane fuel cells" *Journal of Power Sources*, Volume 166, Issue 1, pp. 41-46 (2007)
- [102] Jeong Hwan Chun, Ki Tae Park, Dong Hyun Jo, Ji Young Lee, Sang Gon Kim, Sun Hee Park, Eun Sook Lee, Jy-Young Jyoung, Sung Hyun Kim, "Development of a novel hydrophobic/hydrophilic double micro porous layer for use in a cathode gas diffusion layer in PEMFC" *International Journal of Hydrogen Energy*, Volume 36, Issue 14, pp. 8422-8428 (2011)
- [103] Irfan S. Hussaini, Chao-Yang Wang, "Visualization and quantification of cathode channel flooding in PEM fuel cells" *Journal of Power Sources*, Volume 187, Issue 2, pp. 444-451 (2009)

- [104] M.G. Santarelli, M.F. Torchio, "Experimental analysis of the effects of the operating variables on the performance of a single PEMFC" Energy Conversion and Management, Volume 48, Issue 1, pp. 40-51 (2007)
- [105] Kui Jiao, Jaewan Park, Xianguo L, "Experimental investigations on liquid water removal from the gas diffusion layer by reactant flow in a PEM fuel cell" Applied Energy, Volume 87, Issue 9, pp. 2770-2777 (2010)
- [106] Wei Dai, Haijiang Wang, Xiao Zi Yuan, Jonathan J. Martin, Zhiping Luo, Mu Pan, "Measurement of the water transport rate in a proton exchange membrane fuel cell and the influence of the gas diffusion layer" Journal of Power Sources, Volume 185, Issue 2, pp. 1267-1271 (2008)
- [107] T. Ous, C. Arcoumanis, "Visualisation of water accumulation in the flow channels of PEMFC under various operating conditions" Journal of Power Sources, Volume 187, Issue 1, pp. 182-189 (2009)
- [108] Mehdi Amirinejad, Soosan Rowshanzamir, Mohammad H. Eikani, "Effects of operating parameters on performance of a proton exchange membrane fuel cell", Journal of Power Sources, Volume 161, Issue 2, pp. 872-875 (2006)
- [109] Jianlu Zhang, Zhong Xie, Jiujun Zhang, Yanghua Tang, Chaojie Song, Titichai Navessin, Zhiqing Shi, Datong Song, Haijiang Wang, David P. Wilkinson, Zhong-Sheng Liu, Steven Holdcroft, "High temperature PEM fuel cells", Journal of Power Sources, Volume 160, Issue 2, pp. 872-891 (2006)
- [110] Jin-Cherng Shyu, Kan-Lin Hsueh, Fanghei Tsau, "Performance of proton exchange membrane fuel cells at elevated temperature" Energy Conversion and Management, Volume 52, Issue 12, pp. 3415-3424 (2011)
- [111] Saswata Bose, Tapas Kuila, Thi Xuan Hien Nguyen, Nam Hoon Kim, Kin-tak Lau, Joong Hee Lee, "Polymer membranes for high temperature proton exchange membrane fuel cell: Recent advances and challenges" Progress in Polymer Science, Volume 36, Issue 6, pp. 813-843 (2011)
- [112] Eiji Endoh, Hisao Kawazoe, and Hideki Nakagawa, "Development of Highly Durable MEA for PEMFC under High Temperature Operations (2)", Electrochemical Society Transaction. Volume 1, Issue 8, pp. 221-227 (2006)
- [113] Qingting Liu, Xujin Bao, Daniel M. Rogers, and Siqin Zou, "Novel ABPBI/POSS Composite Membranes for High Temperature PEMFC Applications" Electrochemical Society Transaction. Volume 30, Issue 1, pp. 25-32 (2011)
- [114] Sang-Young Lee, Gunter Scharfenberger, Wolfgang H. Meyer, Gerhard Wegner, "A new water-free proton conducting membrane for high-temperature application" Journal of Power Sources, Volume 163, Issue 1, pp. 27-33 (2006)
- [115] Zhongwei Chen and Ryan Hsu, "Nafion/Acid Functionalized Mesoporous Silica Nanocomposite Membrane for High Temperature PEMFCs" Electrochemical Society Transaction. Volume 25, Issue 1, pp. 1151-1157 (2009)
- [116] Bruno R. Matos, Elisabete I. Santiago, Fabio C. Fonseca, Marcelo Linardi, Vladimir Lavayen, Rodrigo G. Lacerda, Luiz O. Ladeira, and Andre S. Ferlauto, "Nafion-Titanate Nanotube Composite Membranes for PEMFC Operating at High Temperature", Journal of Electrochemical Society, Volume 154, Issue 12, pp. B1358-B1361 (2007)
- [117] Mathieu Martinez, Cristina Iojoiu, Patrick Judeinstein, L. Cointeaux, Jean-Claude Lepretre, and Jean-Yves Sanchez, "Proton Conducting Ionic Liquid Electrolyte for High Temperature PEMFC", Electrochemical Society Transaction. Volume 25, Issue 1, pp. 1647-1657 (2009)
- [118] Eiji Endoh, "Development of Highly Durable PFSA Membrane and MEA for PEMFC Under High Temperature and Low Humidity Conditions" Electrochemical Society Transaction. Volume 16, Issue 2, pp. 1229-1240 (2008)

- [119] Elisabete I. Santiago, Bruno R. Matos, Fabio C. Fonseca, and Marcelo Linardi, "Performance of Nafion-TiO₂ Hybrids Produced by Sol-Gel Process as Electrolyte for PEMFC Operating at High Temperatures", *Electrochemical Society Transaction*, Volume 11, Issue 1, pp. 151-157 (2007)
- [120] H. Nakajima, S. Nomura, T. Sugimoto, S. Nishikawa, and I. Honma, "High Temperature Proton Conducting Organic/Inorganic Nanohybrids for Polymer Electrolyte Membrane", *Journal of Electrochemical Society*, Volume 149, Issue 8, pp. A953-A959 (2002)
- [121] Kui Jiao, Xianguo Li, "Water transport in polymer electrolyte membrane fuel cells" *Progress in Energy and Combustion Science*, Volume 37, Issue 3, pp. 221-291 (2011)
- [122] Yuka Oono, Takashi Fukuda, Atsuo Sounai, Michio Hori, "Influence of operating temperature on cell performance and endurance of high temperature proton exchange membrane fuel cells" *Journal of Power Sources*, Volume 195, Issue 4, pp. 1007-1014 (2010)
- [123] Gang Liu, Huamin Zhang, Jingwei Hu, Yunfeng Zhai, Dongyan Xu, Zhi-gang Shao, "Studies of performance degradation of a high temperature PEMFC based on H₃PO₄-doped PBI" *Journal of Power Sources*, Volume 162, Issue 1, pp. 547-552 (2006)
- [124] Qingfeng Li, Jens Oluf Jensen, Robert F. Savinell, Niels J. Bjerrum, "High temperature proton exchange membranes based on polybenzimidazoles for fuel cells" *Progress in Polymer Science*, Volume 34, Issue 5, pp. 449-477 (2009)
- [125] A. Bazylak, D. Sinton, Z.-S. Liu, N. Djilali, "Effect of compression on liquid water transport and microstructure of PEMFC gas diffusion layers" *Journal of Power Sources*, Volume 163, Issue 2, pp. 784-792 (2007)
- [126] H.M. Yu, J.O. Schumacher, M. Zobel, C. Hebling, "Analysis of membrane electrode assembly (MEA) by environmental scanning electron microscope (ESEM)" *Journal of Power Sources*, Volume 145, Issue 2, pp. 216-222 (2005)
- [127] Takashi Sasabe, Shohji Tsushima, Shuichiro Hirai, "In-situ visualization of liquid water in an operating PEMFC by soft X-ray radiography" *International Journal of Hydrogen Energy*, Volume 35, Issue 20, pp. 11119-11128 (2010)
- [128] H. Markötter, I. Manke, Ph. Krüger, T. Arlt, J. Haussmann, M. Klages, H. Riesemeier, Ch. Hartnig, J. Scholte, J. Banhart, "Investigation of 3D water transport paths in gas diffusion layers by combined in-situ synchrotron X-ray radiography and tomography" *Electrochemistry Communications*, Volume 13, Issue 9, pp. 1001-1004 (2011)
- [129] Yoshio Utaka, Ikunori Hirose, Yutaka Tasaki, "Characteristics of oxygen diffusivity and water distribution by X-ray radiography in microporous media in alternate porous layers of different wettability for moisture control in gas diffusion layer of PEFC" *International Journal of Hydrogen Energy*, Volume 36, Issue 15, pp. 9128-9138 (2011)
- [130] Phengxay Deevanhxay, Takashi Sasabe, Shohji Tsushima, Shuichiro Hirai, "Investigation of water accumulation and discharge behaviors with variation of current density in PEMFC by high-resolution soft X-ray radiography" *International Journal of Hydrogen Energy*, Volume 36, Issue 17, pp. 10901-10907 (2011)
- [131] Takashi Sasabe, Phengxay Deevanhxay, Shohji Tsushima, Shuichiro Hirai, "Investigation on the effect of microstructure of proton exchange membrane fuel cell porous layers on liquid water behavior by soft X-ray radiography" *Journal of Power Sources*, Volume 196, Issue 20, pp. 8197-8206 (2011)
- [132] Christoph Hartnig, Ingo Manke, Robert Kuhn, Sebastian Kleinau, Jürgen Goebels, John Banhart, "High-resolution in-plane investigation of the water evolution and transport in PEM fuel cells" *Journal of Power Sources*, Volume 188, Issue 2, pp. 468-474 (2009)
- [133] Takashi Sasabe, Phengxay Deevanhxay, Shohji Tsushima, Shuichiro Hirai, "Soft X-ray visualization of the liquid water transport within the cracks of micro porous layer in PEMFC" *Electrochemistry Communications*, Volume 13, Issue 6, pp. 638-641 (2011)

- [134] Ph. Krüger, H. Markötter, J. Haußmann, M. Klages, T. Arlt, J. Banhart, Ch. Hartnig, I. Manke, J. Scholta, "Synchrotron X-ray tomography for investigations of water distribution in polymer electrolyte membrane fuel cells" *Journal of Power Sources*, Volume 196, Issue 12, pp. 5250-5255 (2011)
- [135] C. Hartnig, I. Manke, "MEASUREMENT METHODS | Structural Properties: Neutron and Synchrotron Imaging, In-Situ for Water Visualization" *Encyclopedia of Electrochemical Power Sources*, pp. 738-757 (2009)
- [136] J. Park, Xianguo Li, D. Tran, T. Abdel-Baset, D.S. Hussey, D.L. Jacobson, M. Arif, "Neutron imaging investigation of liquid water distribution in and the performance of a PEM fuel cell" *International Journal of Hydrogen Energy*, Volume 33, Issue 13, pp. 3373-3384 (2008)
- [137] J.P. Owejan, T.A. Trabold, D.L. Jacobson, D.R. Baker, D.S. Hussey, M. Arif, "In situ investigation of water transport in an operating PEM fuel cell using neutron radiography: Part 2 – Transient water accumulation in an interdigitated cathode flow field" *International Journal of Heat and Mass Transfer*, Volume 49, Issues 25-26, pp. 4721-4731 (2006)
- [138] Mingtao Wang, Kirk W. Feindel, Steven H. Bergens, Roderick E. Wasylshen, "In situ quantification of the in-plane water content in the Nafion® membrane of an operating polymer-electrolyte membrane fuel cell using ¹H micro-magnetic resonance imaging experiments" *Journal of Power Sources*, Volume 195, Issue 21, pp. 7316-7322 (2010)
- [139] Jacqueline M. Sergi, Satish G. Kandlikar, "Quantification and characterization of water coverage in PEMFC gas channels using simultaneous anode and cathode visualization and image processing" *International Journal of Hydrogen Energy*, Volume 36, Issue 19, pp. 12381-12392 (2011)
- [140] T. Ous, C. Arcoumanis, "Visualisation of water droplets during the operation of PEM fuel cells" *Journal of Power Sources*, Volume 173, Issue 1, pp. 137-148 (2007)
- [141] Talal Ous, C. Arcoumanis, "The formation of water droplets in an air-breathing PEMFC" *International Journal of Hydrogen Energy*, Volume 34, Issue 8, pp. 3476-3487 (2009)
- [142] F. Y. Zhang, X. G. Yang, and C. Y. Wang, "Liquid Water Removal from a Polymer Electrolyte Fuel Cell" *Journal of Electrochemical Society*, Volume 153, Issue 2, pp. A225-A232 (2006)
- [143] Zhigang Zhan, Chen Wang, Weiguo Fu, Mu Pan, "Visualization of water transport in a transparent PEMFC" *International Journal of Hydrogen Energy*, Volume 37, Issue 1, pp. 1094-1105 (2012)
- [144] A. Bazylak, "Liquid water visualization in PEM fuel cells: A review" *International Journal of Hydrogen Energy*, Volume 34, Issue 9, pp. 3845-3857 (2009)
- [145] Shohji Tsushima, Shuichiro Hirai, "In situ diagnostics for water transport in proton exchange membrane fuel cells" *Progress in Energy and Combustion Science*, Volume 37, Issue 2, pp. 204-220 (2011)
- [146] N. Djilali, "Computational modelling of polymer electrolyte membrane (PEM) fuel cells: Challenges and opportunities" *Energy*, Volume 32 pp. 269–280 (2007)
- [147] Serhat Yesilyurmt, "Modeling and Simulations of Polymer Electrolyte Membrane Fuel Cells With Poroelastic Approach for Coupled Liquid Water Transport and Deformation in the Membrane" *Journal of Fuel Cell Science and Technology*, Volume 7, Issue 3, pp. 031008-031017 (2010)
- [148] Kreuer KD, Paddison SJ, Spohr E, Schuster M. "Transport in proton conductors for fuel-cell applications: simulations, elementary reactions, and phenomenology" *Chemical Review*, Volume 104, pp. 4637–4678 (2004)
- [149] Jin Hyun Nam, Massoud Kaviani, "Effective diffusivity and water-saturation distribution in single- and two-layer PEMFC diffusion medium", *International Journal of Heat and Mass Transfer*, Volume 46, Issue 24, pp. 4595–4611 (2003)

- [150] K. Seidenberger, F. Wilhelm, T. Schmitt, W. Lehnert, J. Scholta, "Estimation of water distribution and degradation mechanisms in polymer electrolyte membrane fuel cell gas diffusion layers using a 3D Monte Carlo model" *Journal of Power Sources*, Volume 196, Issue 12, pp. 5317-5324 (2011)
- [151] J.E. Dawes, N.S. Hanspal, O.A. Family, A. Turan, "Three-dimensional CFD modelling of PEM fuel cells: An investigation into the effects of water flooding" *Chemical Engineering Science*, Volume 64, Issue 12, pp. 2781-2794 (2009)
- [152] Yun Wang, Suman Basu, Chao-Yang Wang, "Modeling two-phase flow in PEM fuel cell channels" *Journal of Power Sources*, Volume 179, Issue 2, pp. 603-617 (2008)
- [153] Stefano Cordiner, Simon Pietro Lanzani, Vincenzo Mulone, "3D effects of water-saturation distribution on polymeric electrolyte fuel cell (PEFC) performance" *International Journal of Hydrogen Energy*, Volume 36, Issue 16, pp. 10366-10375 (2011)
- [154] Angelo Esposito, Cesare Pianese, Yann G. Guezennec, "Coupled modeling of water transport and air-droplet interaction in the electrode of a proton exchange membrane fuel cell" *Journal of Power Sources*, Volume 195, Issue 13, pp. 4149-4159 (2010)
- [155] Hua Meng, "Multi-dimensional liquid water transport in the cathode of a PEM fuel cell with consideration of the micro-porous layer (MPL)" *International Journal of Hydrogen Energy*, Volume 34, Issue 13, pp. 5488-5497(2009)
- [156] Hua Meng, "Numerical studies of liquid water behaviors in PEM fuel cell cathode considering transport across different porous layers" *International Journal of Hydrogen Energy*, Volume 35, Issue 11, pp. 5569-5579 (2010)
- [157] Z. Lu, S.G. Kandlikar, C. Rath, M. Grimm, W. Domigan, A.D. White, M. Hardbarger, J.P. Owejan, T.A. Trabold, "Water management studies in PEM fuel cells, Part II: Ex situ investigation of flow maldistribution, pressure drop and two-phase flow pattern in gas channels" *International Journal of Hydrogen Energy*, Volume 34, Issue 8, pp. 3445-3456 (2009)
- [158] Xun Zhu, P.C. Sui, Ned Djilali, "Dynamic behaviour of liquid water emerging from a GDL pore into a PEMFC gas flow channel" *Journal of Power Sources*, Volume 172, Issue 1, pp. 287-295 (2007)
- [159] Anh Dinh Le, Biao Zhou, Huan-Ruei Shiu, Chun-I. Lee, Wen-Chen Chang, "Numerical simulation and experimental validation of liquid water behaviors in a proton exchange membrane fuel cell cathode with serpentine channels" *Journal of Power Sources*, Volume 195, Issue 21, 1 pp. 7302-7315 (2010)
- [160] A. Theodorakakos, T. Ous, M. Gavaises, J.M. Nouri, N. Nikolopoulos, H. Yanagihara, "Dynamics of water droplets detached from porous surfaces of relevance to PEM fuel cells" *Journal of Colloid and Interface Science*, Volume 300, Issue 2, pp. 673-687 (2006)
- [161] J. Zachary Fishman, Hilary Leung, A. Bazylak, "Droplet pinning by PEM fuel cell GDL surfaces" *International Journal of Hydrogen Energy*, Volume 35, Issue 17, pp. 9144-9150 (2010)
- [162] Jon P. Owejan, Jeffrey J. Gagliardo, Jacqueline M. Sergi, Satish G. Kandlikar, Thomas A. Trabold, "Water management studies in PEM fuel cells, Part I: Fuel cell design and in situ water distributions" *International Journal of Hydrogen Energy*, Volume 34, Issue 8, pp. 3436-3444 (2009)
- [163] Xianguo Li, Imran Sabir, "Review of bipolar plates in PEM fuel cells: Flow-field designs" *International Journal of Hydrogen Energy*, Volume 30, Issue 4, pp. 359-371 (2005)
- [164] Xiao-Guang Yang, Qiang Ye, Ping Cheng, "Matching of water and temperature fields in proton exchange membrane fuel cells with non-uniform distributions" *International Journal of Hydrogen Energy*, Volume 36, Issue 19, pp. 12524-12537 (2011)
- [165] J.J. Hwnag, W.R. Chang, R.G. Peng, P.Y. Chen, A. Su, "Experimental and numerical studies of local current mapping on a PEM fuel cell", *International Journal of Hydrogen Energy*, Volume 33, Issue 20, pp. 5718-5727 (2008)

- [166] Daniel G. Strickland, Shawn Litster, Juan G. Santiago, “Current distribution in polymer electrolyte membrane fuel cell with active water management” *Journal of Power Sources*, Volume 174, Issue 1, pp. 272-281 (2007)
- [167] Hong Sun, Guangsheng Zhang, Lie-Jin Guo, Hongtan Liu, “A novel technique for measuring current distributions in PEM fuel cells” *Journal of Power Sources*, Volume 158, Issue 1, pp. 326-332 (2006)
- [168] Alex Hakenjos, Harald Muentter, Ursula Wittstadt, Christopher Hebling, “A PEM fuel cell for combined measurement of current and temperature distribution, and flow field flooding” *Journal of Power Sources*, Volume 131, Issues 1–2, pp. 213-216 (2004)
- [169] Shou-Shing Hsieh, Bing-Shyan Her, Yi-Ji Huang, “Effect of pressure drop in different flow fields on water accumulation and current distribution for a micro PEM fuel cell”, *Energy Conversion and Management*, Volume 52, Issue 2, pp. 975-982 (2011)
- [170] Andrew Higier, Hongtan Liu, “Direct measurement of current density under the land and channel in a PEM fuel cell with serpentine flow fields” *Journal of Power Sources*, Volume 193, Issue 2, pp. 639-648 (2009)
- [171] Guangsheng Zhang, Liejin Guo, Bin Ma, Hongtan Liu, “Comparison of current distributions in proton exchange membrane fuel cells with interdigitated and serpentine flow fields” *Journal of Power Sources*, Volume 188, Issue 1, pp. 213-219 (2009)
- [172] Jürgen Stumper, Stephen A. Campbell, David P. Wilkinson, Mark C. Johnson, Mike Davis, “In-situ methods for the determination of current distributions in PEM fuel cells” *Electrochimica Acta*, Volume 43, Issue 24, pp. 3773-3783 (1998)
- [173] Hui Li, Yanghua Tang, Zhenwei Wang, Zheng Shi, Shaohong Wu, Datong Song, Jianlu Zhang, Khalid Fatih, Jiujun Zhang, Haijiang Wang, Zhongsheng Liu, Rami Abouatallah, Antonio Mazza, “A review of water flooding issues in the proton exchange membrane fuel cell” *Journal of Power Sources*, Volume 178, Issue 1, pp. 103-117 (2008)
- [174] Dusan Spernjak, Ajay K. Prasad, Suresh G. Advani, “Experimental investigation of liquid water formation and transport in a transparent single-serpentine PEM fuel cell” *Journal of Power Sources*, Volume 170, Issue 2, pp. 334-344 (2007)
- [175] F. Barreras, A. Lozano, L. Valiño, C. Marín, A. Pascau, “Flow distribution in a bipolar plate of a proton exchange membrane fuel cell: experiments and numerical simulation studies” *Journal of Power Sources*, Volume 144, Issue 1, pp. 54-66 (2005)
- [176] W. Goddard, B. Merinov, A. Vanduin, T. Jacob, M. Blanco, V. Molinero, S.S. Jang and Y.H. Jang, “Multi-paradigm multi-scale simulations for fuel cell catalysts and membranes” *Molecular Simulation*, Vol. 32, Nos. 3–4, pp. 251–268 (2006)
- [177] M. Teliska, W. E. O’Grady, and D. E. Ramaker, “Determination of O and OH Adsorption Sites and Coverage in Situ on Pt Electrodes from Pt L_{2,3} X-ray Absorption Spectroscopy” *The Journal of Physical Chemistry B*, Volume 109, Issue 16, pp. 8076–8084 (2005)
- [178] Z.D. Wei, H.B. Ran, X.A. Liu, Y. Liu, C.X. Sun, S.H. Chan, P.K. Shen “Numerical analysis of Pt utilization in PEMFC catalyst layer using random cluster model” *Electrochimica Acta* Volume 51, Issue 15, pp. 3091–3096 (2006)
- [179] Y. Shao-Horn, W. C. Sheng, S. Chen, P. J. Ferreira, E. F. Holby, D. Morgan, “Instability of Supported Platinum Nanoparticles in Low-Temperature Fuel Cells” *Chemistry and Materials Science*, Volume 46, Numbers 3-4, 285-305 (2007)
- [180] Wu Bi, Thomas F. Fuller, “Modeling of PEM fuel cell Pt/C catalyst degradation” *Journal of Power Sources*, Volume 178, Issue 1, pp. 188-196 (2008)

- [181] Xuan Cheng, Ling Chen, Cheng Peng, Zhiwu Chen, Ying Zhang, and Qinbai Fan, "Catalyst Microstructure Examination of PEMFC Membrane Electrode Assemblies vs. Time" The Journal of Electrochemical Society Volume 151, Issue1, pp. A48-A52 (2004)
- [182] F. H. Garzon, John Davey, and Rodney Borup, "Fuel Cell Catalyst Particle Size Growth Characterized by X-Ray Scattering Methods" The Electrochemical Society Transactions, Volume 1, Issue 8, pp. 153-166 (2006)
- [183] Shuo Chen, Hubert A. Gasteiger, Katsuichiro Hayakawa, Tomoyuki Tada, and Yang Shao-Horn, "Platinum-Alloy Cathode Catalyst Degradation in Proton Exchange Membrane Fuel Cells: Nanometer-Scale Compositional and Morphological Changes" Journal of The Electrochemical Society Volume 157, Issue 1, pp. A82-A97 (2010)
- [184] C. H. Paik, G. S. Saloka, and G. W. Graham, "Influence of Cyclic Operation on PEM Fuel Cell Catalyst Stability" Electrochemical and Solid-State Letters, Volume 10, Issue 2, pp. B39-B42 (2007)
- [185] Masanobu Uchimura and Shyam S. Kocha, "The Impact of Cycle Profile on PEMFC Durability" Electrochemical Transactions, Volume 11, Issue 1, pp. 1215-1226 (2007)
- [186] Wu Bi, Gary E. Gray, and Thomas F. Fuller, "PEM Fuel Cell Pt/C Dissolution and Deposition in Nafion Electrolyte" Electrochemical and Solid-State Letters, Volume 10, Issue 5, pp. B101-B104 (2007)
- [187] Ronald S. Goeke, Abhaya K. Datye, Plamen Atanassov, and Jean St-Pierre, "Model Electrode Structures for Studies of Electrocatalyst Degradation" The ElectroChemical Society Transactions, Volume 33, Issue 1, pp. 361-368 (2010)
- [188] Sarah C. Ball, Sarah L. Hudson, Brian Theobald, and David Thompsett, "The Effect of Dynamic and Steady State Voltage Excursions on the Stability of Carbon Supported Pt and PtCo Catalysts" The Electrochemical Society Transactions Volume 3, Issue 1, pp. 595-605 (2006)
- [189] Sarah C. Ball, Sarah L. Hudson, Brian R. Theobald, and David Thompsett, "PtCo, a Durable Catalyst for Automotive PEMFC?" Electrochemical Society Transactions Volume 11, Issue 1, pp. 1267-1278 (2007)
- [190] Ping Yu, Marianne Pemberton, Paul Plasse, "PtCo/C cathode catalyst for improved durability in PEMFCs" Journal of Power Sources, Volume 144, Issue 1, pp. 11-20 (2005)
- [191] Bruno Pollet, Jill E. Newton, Jon A. Preece, and Oliver J. Curnick, "The Use of Ionic and Non-Ionic Surfactants for the Control of Platinum Nanoparticle Aggregation in Proton Exchange Membrane Fuel Cells (PEMFCs)" Electrochemical Society Transactions, Volume 41, Issue 1, pp. 2165-2173 (2011)
- [192] Mahlon S. Wilson, Fernando H. Garzon, Kurt E. Sickafus, and Shimshon Gottesfeld, "Surface Area Loss of Supported Platinum in Polymer Electrolyte Fuel Cells" Journal of The Electrochemical Society, Volume 140, Issue 10, pp. 2872-2877 (1993)
- [193] Jian Xie, David L. Wood, Karren L. More, Plamen Atanassov, and Rodney L. Borup, "Microstructural changes of membrane electrode assemblies during PEFC durability testing at high humidity conditions", Journal of the Electrochemical Society, Volume 152, Issue 5, pp. A1011-A1020 (2005)
- [194] Karl J.J. Mayrhofer, Josef C. Meier, Sean J. Ashton, Gustav K.H. Wiberg, Florian Kraus, Marianne Hanzlik, Matthias Arenz, "Fuel cell catalyst degradation on the nanoscale" Electrochemistry Communications, Volume 10, Issue 8, pp. 1144-1147 (2008)
- [195] Timothy W. Patterson and Robert M. Darling, "Damage to the Cathode Catalyst of a PEM Fuel Cell Caused by Localized Fuel Starvation", Electrochemical Solid-State Letters, Volume 9, Issue 4, pp. A183-A185 (2006)
- [196] Z. Y. Liu, B. K. Brady, R. N. Carter, B. Litteer, M. Budinski, J. K. Hyun, and D. A. Muller, "Characterization of Carbon Corrosion-Induced Structural Damage of PEM Fuel Cell Cathode Electrodes Caused by Local Fuel Starvation", The Journal of Electrochemical Society, Volume 155, Issue 10, pp. B979-B984 (2008)

- [197] Jingxin Zhang, Brian A. Litteer, Wenbin Gu, Han Liu, and Hubert A. Gasteiger, "Effect of Hydrogen and Oxygen Partial Pressure on Pt Precipitation within the Membrane of PEMFCs" Journal of the Electrochemical Society 154, Issue 10, pp. B1006-B1011 (2007)
- [198] A. P. Young, J. Stumper, S. Knights, and E. Gyenge, "Ionomer Degradation in Polymer Electrolyte Membrane Fuel Cells" Journal of the Electrochemical Society, Volume 157, Issue 3, pp. B425-B436 (2010)
- [199] Carlotta Francia, Vijaykumar S. Ijeri, Stefania Specchia, Paolo Spinelli, "Estimation of hydrogen crossover through Nafion® membranes in PEMFCs" Journal of Power Sources, Volume 196, Issue 4, pp. 1833-1839 (2011)
- [200] Sumit Kundu, Michael W. Fowler, Leonardo C. Simon, Rami Abouatallah, Natasha Beydokhti, "Degradation analysis and modeling of reinforced catalyst coated membranes operated under OCV conditions", Journal of Power Sources, Volume 183, Issue 2, pp. 619-628 (2008)
- [201] Sumit Kundu, Michael W. Fowler, Leonardo C. Simon, Rami Abouatallah, Natasha Beydokhti, "Open circuit voltage durability study and model of catalyst coated membranes at different humidification levels" Journal of Power Sources, Volume 195, Issue 21, pp. 7323-7331 (2010)
- [202] Y. Kawasoe, S. Tanaka, T. Kuroki, H. Kusaba, K. Ito, Y. Teraoka, and K. Sasaki, "Preparation and Electrochemical Activities of Pt-Ti Alloy PEFC Electrocatalysts" Journal of the Electrochemical Society, Volume 154, Issue 9, B969-B975 (2007)
- [203] Sarah C. Ball, Brian Theobald, David Thompsett, and Sarah Hudson, "Enhanced Stability of PtCo catalysts for PEMFC", Electrochemical Society Transactions, Volume 1, Issue 8, pp.141-152 (2006)
- [204] Tomoyuki Tada, Yumi Yamamoto, Koichi Matsutani, Katsuichiro Hayakawa, and Tatsunori Namai, "Current Progress of Electrocatalyst R&D in TKK", Electrochemical Society Transactions, Volume 16, Issue 2, 215-224 (2008)
- [205] Sang Hyun Ahn, Soo-Kil Kim, Oh Joong Kwon, Sun-Mi Hwang, and Jae Jeong Kim, "Preparation of Pt-Ru-Co Ternary Catalyst on Carbon Paper for PEMFC with Electrodeposition and Galvanic Displacement" Electrochemical Society Transactions, Volume 16, Issue 2, pp. 1111-1116 (2008)
- [206] Margaret A. Gabriel, Thierry Deutsch, and Alejandro A. Franco, "Fullerene-Based Materials as Catalysts for Fuel Cells" Electrochemical Society Transactions, Volume 25, Issue 22, pp.1-6 (2010)
- [207] Jiajun Wang, Geping Yin, Yuyan Shao, Zhenbo Wang, and Yunzhi Gao, "Platinum Deposition on Multiwalled Carbon Nanotubes by Ion-Exchange Method as Electrocatalysts for Oxygen Reduction", Journal of the Electrochemical Society, Volume 154, Issue 7, B687-B693 (2007)
- [208] Zhongwei Chen, Weiqiao Deng, Xin Wang, and Yushan Yan, "Durability and Activity Study of Single-Walled, Double-Walled and Multi-Walled Carbon Nanotubes Supported Pt Catalyst for PEMFCs" Electrochemical Society Transactions, Volume 11, Issue 1, pp. 1289-1299 (2007)
- [209] Zhe Tang, How Y. Ng, Jianyi Lin, Andrew T. S. Wee, and Daniel H. C. Chua, "Pt/CNT-Based Electrodes with High Electrochemical Activity and Stability for Proton Exchange Membrane Fuel Cells" Journal of the Electrochemical Society, Volume 157, Issue 2, B245-B250 (2010)
- [210] Wei Zhu, Jim P. Zheng, R. Liang, Ben Wang, Chun Zhang, Shawn Walsh, George Au, and Edward J. Plichta, "Highly-Efficient Buckypaper-Based Electrodes for PEMFC" Electrochemical Society Transactions, Volume 16, Issue 2, pp. 1615-1626 (2008)
- [211] W. Zhu, J. P. Zheng, R. Liang, B. Wang, C. Zhang, G. Au, and E. J. Plichta, "Durability Study on SWNT/Nanofiber Buckypaper Catalyst Support for PEMFCs" Journal of Electrochemical Society, Volume 156, Issue 9, pp. B1099-B1105 (2009)
- [212] R. Imran Jafri, T. Arockiados, N. Rajalakshmi, and S. Ramaprabhu, "Nanostructured Pt Dispersed on Graphene-Multiwalled Carbon Nanotube Hybrid Nanomaterials as Electrocatalyst for PEMFC", Journal of the Electrochemical Society, Volume 157, Issue 6, pp. B874-B879 (2010)

- [213] Anil V. Virkar and Yingke Zhou, "Mechanism of Catalyst Degradation in Proton Exchange Membrane Fuel Cells" Journal of the Electrochemical Society, Volume 154, Issue 6, B540-B547 (2007)
- [214] Dong-Ha Lim, Woo-Jin Lee, Jess Wheldon, Nathan L. Macy, and William H. Smyrl, "Electrochemical Characterization and Durability of Sputtered Pt Catalysts on TiO₂ Nanotube Arrays as a Cathode Material for PEFCs" Journal of the Electrochemical Society, Volume 157, Issue 6, pp. B862-B867 (2010)
- [215] Yuichi Suzuki, Akimitsu Ishihara, Shigenori Mitsushima, Nobuyuki Kamiya, and Ken-ichiro Ota, "Sulfated-Zirconia as a Support of Pt Catalyst for Polymer Electrolyte Fuel Cells", Electrochemical Solid-State Letters, Volume 10, Issue 7, B105-B107 (2007)
- [216] Madhu Sudan Saha, Ruying Li, Mei Cai, and Xueliang Sun, "High Electrocatalytic Activity of Platinum Nanoparticles on SnO₂ Nanowire-Based Electrodes", Electrochemical Solid-State Letters, Volume 10, Issue 8, pp. B130-B113 (2007)
- [217] Zhongwei Chen, Mahesh Waje, Wenzhen Li, and Yushan Yan, "Supportless Pt and Pt-Pd Nanotubes with High Durability and Activity Towards Oxygen Reduction Reaction for PEMFCs" Electrochemical Society Transactions, Volume 11, Issue 1, pp. 1301-1311 (2007)
- [218] Wolfgang Schmittinger, Ardalan Vahidi, "A review of the main parameters influencing long-term performance and durability of PEM fuel cells" Journal of Power Sources, Volume 180, Issue 1, pp. 1-14 (2008)
- [219] N. Yousfi-Steiner, Ph. Moçotéguy, D. Candusso, D. Hissel, A. Hernandez, A. Aslanides, "A review on PEM voltage degradation associated with water management: Impacts, influent factors and characterization" Journal of Power Sources, Volume 183, Issue 1, pp. 260-274 (2008)
- [220] J. Parrondo, M. Ortueda and F. Mijangos, "Swelling behaviour of PEMFC during conditioning" Brazilian Journal of Chemical Engineering, Vol. 24, No. 03, pp. 411 – 419 (2007)
- [221] Ahmet Kusoglu, Brian L. Kienitz, and Adam Z. Weber, "Understanding the Effects of Compression and Constraints on Water Uptake of Fuel-Cell Membranes" Journal of the Electrochemical Society, Volume 158, Issue 12, pp. B1504-B1514 (2011)
- [222] Vivek S. Murthi, Joseph Dura, Sushil Satija, and Charles Majkrzak, "Water Uptake and Interfacial Structural Changes of Thin Film Nafion® Membranes Measured by Neutron Reflectivity for PEM Fuel Cells" The Electrochemical Society Transactions, Volume 16, Issue 2, pp. 1471-1485 (2008)
- [223] Statterfield, M. B.; Majsztrik, P. W.; Ota, H.; Benziger, J. B.; Bocarsly, A. B. "Mechanical properties of Nafion and titania/Nafion composite membranes for polymer electrolyte membrane fuel cells" Journal of Polymer Science Part B: Polymer Physics, Volume 44, Issue 16, pp. 2327–2345 (2006).
- [224] Paul W. Majsztrik, Andrew B. Bocarsly and Jay B. Benziger "Viscoelastic response of Nafion. Effects of Temperature and Hydration on Tensile Creep" Macromolecules, Volume 41, Issue 24, pp 9849–9862 (2008)
- [225] Ahmet Kusoglu, Anette M. Karlsson, Michael H. Santare, Simon Cleghorn, William B. Johnson, "Mechanical response of fuel cell membranes subjected to a hygro-thermal cycle" Journal of Power Sources, Volume 161, Issue 2, pp. 987-996 (2006)
- [226] Ahmet Kusoglu, Michael H. Santare, Anette M. Karlsson, Simon Cleghorn, and William B. Johnson, "Numerical Investigation of Mechanical Durability in Polymer Electrolyte Membrane Fuel Cells" Journal of the Electrochemical Society, Volume 157, Issue 5, pp. B705-B713 (2010)
- [227] Timothy J. Silverman, Jeremy P. Meyers, and Joseph J. Beaman, "Modeling Water Transport and Swelling in Polymer Electrolyte Membranes" Journal of the Electrochemical Society, Volume 157, Issue 10, B1376-B1381(2010)

- [228] Xiqiang Yan, Ming Hou, Liyan Sun, Haibo Cheng, Youlu Hong, Dong Liang, Qiang Shen, Pingwen Ming, Baolian Yi, "The study on transient characteristic of proton exchange membrane fuel cell stack during dynamic loading" *Journal of Power Sources*, Volume 163, Issue 2, pp. 966-970 (2007)
- [229] Jingrong Yu, Toyoaki Matsuura, Yusuke Yoshikawa, Md Nazrul Islam, and Michio Hori, "In Situ Analysis of Performance Degradation of a PEMFC under Nonsaturated Humidification" *Electrochemical and Solid-State Letters*, Volume 8, Issue 3, pp. A156-158 (2005)
- [230] Vijay A. Sethuraman, John W. Weidner, Andrew T. Haug, and Lesia V. Protsailo, "Durability of Perfluorosulfonic Acid and Hydrocarbon Membranes: Effect of Humidity and Temperature" *Journal of The Electrochemical Society*, Volume 155, Issue 2, pp. B119-B124 (2008)
- [231] D A Schiraldi, "Perfluorinated polymer electrolyte membrane durability" *Journal of Macromolecular Science, Part C: Polymer Reviews*, Volume: 46, Issue: 3, pp. 315-327 (2006)
- [232] Jingrong Yu, Toyoaki Matsuura, Yusuke Yoshikawa, Md Nazrul Islam and Michio Hori, "Lifetime behavior of a PEM fuel cell with low humidification of feed stream" *Journal of Physical Chemistry. Chemical Physics*. Issue 7, pp. 373-378 (2005)
- [233] Cheng Chen, Thomas F. Fuller, "The effect of humidity on the degradation of Nafion® membrane" *Polymer Degradation and Stability*, Volume 94, Issue 9, pp. 1436-1447 (2009)
- [234] H. A. Gasteiger, W. Gu, B. Litteer, R. Makharia, B. Brady, M. Budinski, E. Thompson, F. T. Wagner, S. G. Yan and P. T. Yu, "Catalyst Degradation Mechanisms in PEM and Direct Methanol Fuel Cells" *Mini-Micro Fuel Cells; NATO Science for Peace and Security Series C: Environmental Security*, pp. 225-233, DOI: 10.1007/978-1-4020-8295-5_15 (2008)
- [235] Huang, X. Y.; Solasi, R.; Zou, Y.; Feshler, M.; Reifsnider, K.; Condit, D.; Burlatsky, S.; Madden, T. "Mechanical endurance of polymer electrolyte membrane and PEM fuel cell durability" *Journal of Polymer Science Part B: Polymer Physics*, Volume 44, Issue 16, pp. 2346-2357 (2006).
- [236] Reyna-Valencia, A.; Kaliguine, S.; Bousmina, M. "Tensile mechanical properties of sulfonated poly(ether ether ketone) (SPEEK) and BPO₄/SPEEK membranes" *Journal of Applied Polymer Science*, Volume 98, Issue 6, pp. 2380–2393 (2005).
- [237] Ahmet Kusoglu, Michael H. Santare and Anette M. Karlsson, "Aspects of fatigue failure mechanisms in polymer fuel cell membranes" *Journal of Polymer Science Part B: Polymer Physics*, Volume 49, Issue 21, pp. 1506–1517 (2011)
- [238] Ahmet Kusoglu, Anette M. Karlsson, Michael H. Santare, Simon Cleghorn, William B. Johnson, "Mechanical behavior of fuel cell membranes under humidity cycles and effect of swelling anisotropy on the fatigue stresses" *Journal of Power Sources*, Volume 170, Issue 2, pp. 345-358 (2007)
- [239] Vijay A. Sethuraman, John W. Weidner, Andrew T. Haug, Sathya Motupally, and Lesia V. Protsailo, "Hydrogen Peroxide Formation Rates in a PEMFC Anode and Cathode" *Journal of The Electrochemical Society*, Volume 155, Issue 1, pp. B50-B57 (2008)
- [240] Eiji Endoh, Shinji Terazono, Hardiyanto Widjaja, and Yasuyuki Takimoto, "Degradation Study of MEA for PEMFCs under Low Humidity Conditions", *Electrochemical and Solid-State Letters*. Volume 7, Issue 7, pp. A209-A211 (2004)
- [241] R. Borup, J. Meyers, B. Pivovar, Y. S. Kim, R. Mukundan, N. Garland, D. Myers, M. Wilson, F. Garzon, D. Wood, P. Zelenay, K. More, K. Stroh, T. Zawodzinski, J. Boncella, J. E. McGrath, M. Inaba, K. Miyatake, M. Hori, K. Ota, Z. Ogumi, S. Miyata, A. Nishikata, Z. Siroma, Y. Uchimoto, K. Yasuda, K.-i. Kimijima, N. Iwashita; "Scientific Aspects of Polymer Electrolyte Fuel Cell Durability and Degradation" *Chemical Reviews*, Volume 107, Issue 10, pp 3904–3951 (2007)

- [242] Amanda Collier, Haijiang Wang, Xiao Zi Yuan, Juijun Zhang, David P. Wilkinson, “Degradation of polymer electrolyte membranes” International Journal of Hydrogen Energy, Volume 31, Issue 13, pp. 1838-1854 (2006)
- [243] Carl A. Reiser, Lawrence Bregoli, Timothy W. Patterson, Jung S. Yi, J. Deliang Yang, Mike L. Perry, and Thomas D. Jarvi, “A Reverse-Current Decay Mechanism for Fuel Cells” Electrochemical Solid-State Letters, Volume 8, Issue 6, pp. A273-A276 (2005)
- [244] D. A. Stevens, M. T. Hicks, G. M. Haugen, and J. R. Dahn, “Ex Situ and In Situ Stability Studies of PEMFC Catalysts” Journal of The Electrochemical Society, Volume 152, Issue 12, pp. A2309-A2315 (2005)
- [245] Masanobu Uchimura, Seiho Sugawara, Yosuke Suzuki, Jianbo Zhang, and Shyam S. Kocha, “Electrocatalyst Durability under Simulated Automotive Drive Cycles”, The ElectroChemical Society Transactions, Volume 16, Issue 2, pp. 225-234 (2008)
- [246] Carl A. Reiser, Lawrence Bregoli, Timothy W. Patterson, Jung S. Yi, J. Deliang Yang, Mike L. Perry, and Thomas D. Jarvi, “A Reverse-Current Decay Mechanism for Fuel Cells”, Electrochemical and Solid-State Letters Volume 8, Issue 6, pp. A273-A276 (2005)
- [247] Wolfgang R. R. Baumgartner, Wolfgang R. R. Baumgartner, Eva Wallnöfer, Thomas Schaffer, Viktor Hacker, Volker Peinecke, and Peter Prenninger, “Electrocatalytic Corrosion of Carbon Support in PEMFC at Fuel Starvation” Electrochemical Society Transactions Volume 3, Issue 1, pp. 811-825 (2006)
- [248] Yuyan Shao, Jun Wang, Rong Kou, Mark Engelhard, Jun Liu, Yong Wang, Yuehe Lin, “The corrosion of PEM fuel cell catalyst supports and its implications for developing durable catalysts” Electrochimica Acta, Volume 54, Issue 11, pp. 3109-3114 (2009)
- [249] S. Maass, F. Finsterwalder, G. Frank, R. Hartmann, C. Merten, “Carbon support oxidation in PEM fuel cell cathodes” Journal of Power Sources, Volume 176, Issue 2, pp. 444-451 (2008)
- [250] Wei Li, Alan M. Lane, “Analysis of oxygen sources and reaction pathways of carbon support corrosion at the cathode in PEMFC using oxygen-18 DEMS” Electrochimica Acta, Volume 55, Issue 22, pp. 6926-6931 (2010)
- [251] A. P. Young, J. Stumper, and E. Gyenge, “Characterizing the Structural Degradation in a PEMFC Cathode Catalyst Layer: Carbon Corrosion” Journal of Electrochemical Society, Volume 156, Issue 8, pp. B913-B922 (2009)
- [252] K. H. Kangasniemi, D. A. Condit, and T. D. Jarvi, “Characterization of Vulcan Electrochemically Oxidized under Simulated PEM Fuel Cell Conditions” Journal of The Electrochemical Society, Volume 151, Issue 4, pp. E125-E132 (2004)
- [253] Renato A. Antunes, Mara Cristina L. Oliveira, Gerhard Ett, Volkmar Ett, “Corrosion of metal bipolar plates for PEM fuel cells: A review” International Journal of Hydrogen Energy, Volume 35, Issue 8, pp. 3632-3647 (2010)
- [254] H. Tawfika, Y. Hunga,c, D. Mahajan, “Metal bipolar plates for PEM fuel cell—A review” Journal of Power Sources, Volume 163, Issue 2, pp. 755–767 (2007)
- [255] Kung-Hsu Hou, Chien-Hung Lin, Ming-Der Ger, Sheau-Wen Shiah, Hsi-Ming Chou, “Analysis of the characterization of water produced from proton exchange membrane fuel cell (PEMFC) under different operating thermal conditions” International Journal of Hydrogen Energy, Volume 37, Issue 4, pp. 3890-3896 (2012)
- [256] Ying Yang, Lie-jin Guo, Hongtan Liu, “Corrosion characteristics of SS316L as bipolar plate material in PEMFC cathode environments with different acidities” International Journal of Hydrogen Energy, Volume 36, Issue 2, pp. 1654-1663 (2011)
- [257] Heli Wang, Mary Ann Sweikart, John A Turner, “Stainless steel as bipolar plate material for polymer electrolyte membrane fuel cells “ Journal of Power Sources, Volume 115, Issue 2, pp. 243-251 (2003)

- [258] Heli Wang, John A. Turner, "Ferritic stainless steels as bipolar plate material for polymer electrolyte membrane fuel cells" *Journal of Power Sources*, Volume 128, Issue 2, pp. 193-200 (2004)
- [259] Johan André, Laurent Antoni, Jean-Pierre Petit, "Corrosion resistance of stainless steel bipolar plates in a PEFC environment: A comprehensive study" *International Journal of Hydrogen Energy*, Volume 35, Issue 8, pp. 3684-3697 (2010)
- [260] Y. Hung, H. Tawfik, D. Mahajan, "Durability and characterization studies of polymer electrolyte membrane fuel cell's coated aluminum bipolar plates and membrane electrode assembly" *Journal of Power Sources*, Volume 186, Issue 1, pp. 123-127 (2009)
- [261] Nada Zamel, Xianguo Li, "Effect of contaminants on polymer electrolyte membrane fuel cells" *Progress in Energy and Combustion Science*, Volume 37, Issue 3, pp. 292-329 (2011)
- [262] M Kelly, Bernhard Egger, G Fafilek, J Besenhard, H Kronberger, G Nauer, "Conductivity of polymer electrolyte membranes by impedance spectroscopy with microelectrodes" *Solid State Ionics*, Volume 176, Issue 25-28, pp. 2111-2114 (2005)
- [263] Y. Ishikawa, H. Hamada, M. Uehara, M. Shiozawa, "Super-cooled water behavior inside polymer electrolyte fuel cell cross-section below freezing temperature" *Journal of Power Sources*, Volume 179, Issue 2, pp. 547-552 (2008)
- [264] Abdul-Kader Srouji, Matthew M. Mench, "Chapter 6 - Freeze Damage to Polymer Electrolyte Fuel Cells" *Polymer Electrolyte Fuel Cell Degradation*, pp. 293-333 (2012)
- [265] EunAe Cho, Jae-Joon Ko, Heung Yong Ha, Seong-Ahn Hong, Kwan-Young Lee, Tae-Won Lim, and In-Hwan Oh, "Characteristics of the PEMFC Repetitively Brought to Temperatures below 0°C" *The Journal of Electrochemical Society*, Volume 150, Issue 12, pp. A1667- A1670 (2003)
- [266] Dennis E. Curtin, Robert D. Lousenberg, Timothy J. Henry, Paul C. Tangeman, Monica E. Tisack, "Advanced materials for improved PEMFC performance and life" *Journal of Power Sources*, Volume 131, Issues 1-2, pp. 41-48 (2004)
- [267] Qunhui Guo, Zhigang Qi, "Effect of freeze-thaw cycles on the properties and performance of membrane-electrode assemblies" *Journal of Power Sources*, Volume 160, Issue 2, pp. 1269-1274 (2006)
- [268] Jing Li, Stephen Lee, and Joy Roberts, "Ice Formation and Distribution in the Catalyst Layer During Freeze-Start Process - CRYO- SEM Investigation" *The Electrochemical Society Transactions*, Volume 11, Issue 1, pp. 595-605 (2007)
- [269] Stephen Lee, Joy Roberts, Jing Li, and Siyu Ye, "Characterization of the Catalyst Layer in a PEMFC During Subzero Operation" *The Electrochemical Society Transactions*, Volume 12, Issue 1, pp. 13-19 (2008)
- [270] Yongtaek Lee, Bosung Kim, Yongchan Kim, Xianguo Li, "Effects of a microporous layer on the performance degradation of proton exchange membrane fuel cells through repetitive freezing" *Journal of Power Sources*, Volume 196, Issue 4, Pages 1940-1947 (2011)
- [271] EunAe Cho, Jae-Joon Ko, Heung Yong Ha, Seong-Ahn Hong, Kwan-Young Lee, Tae-Won Lim, and In-Hwan Oh, "Characteristics of the PEMFC Repetitively Brought to Temperatures below 0°C" *The Journal of Electrochemical Society*, Volume 150, Issue 12, pp. A1667-A1670 (2003)
- [272] Shengsheng Zhang, Xiaozi Yuan, Haijiang Wang, Walter Mérida, Hong Zhu, Jun Shen, Shaohong Wu, Jiujun Zhang, "A review of accelerated stress tests of MEA durability in PEM fuel cells" *International Journal of Hydrogen Energy*, Volume 34, Issue 1, pp. 388-404 (2009)
- [273] Qiang Yan, Hossein Toghiani, Young-Whan Lee, Kaiwen Liang, Heath Causey, "Effect of sub-freezing temperatures on a PEM fuel cell performance, startup and fuel cell components" *Journal of Power Sources*, Volume 160, Issue 2, pp. 1242-1250 (2006)

- [274] Shichun Mu, Pei Zhao, Cheng Xu, Ying Gao, Mu Pan, “Detaching behaviors of catalyst layers applied in PEM fuel cells by off-line accelerated test” International Journal of Hydrogen Energy, Volume 35, Issue 15, pp. 8155-8160 (2010)
- [275] Mathias Gerard, Jean-Philippe Poirot-Crouvezier, Daniel Hissel, Marie-Cécile Pera, “Oxygen starvation analysis during air feeding faults in PEMFC” International Journal of Hydrogen Energy, Volume 35, Issue 22, pp. 12295-12307 (2010)
- [276] R. Lin, B. Li, Y.P. Hou, J.M. Ma, “Investigation of dynamic driving cycle effect on performance degradation and micro-structure change of PEM fuel cell” International Journal of Hydrogen Energy, Volume 34, Issue 5, pp. 2369-2376 (2009)
- [277] R. Alink, D. Gerteisen, M. Oszcipok, “Degradation effects in polymer electrolyte membrane fuel cell stacks by sub-zero operation—An in situ and ex situ analysis” Journal of Power Sources, Volume 182, Issue 1, pp. 175-187 (2008)
- [278] Feng Rong, Cheng Huang, Zhong-Sheng Liu, Datong Song, Qianpu Wang, “Microstructure changes in the catalyst layers of PEM fuel cells induced by load cycling: Part I. Mechanical model” Journal of Power Sources, Volume 175, Issue 2, pp. 699-711 (2008)
- [279] Sang-Yeop Lee, Hyoung-Juhn Kim, EunAe Cho, Kug-Seung Lee, Tae-Hoon Lim, In Chul Hwang, Jong Hyun Jang, “Performance degradation and microstructure changes in freeze–thaw cycling for PEMFC MEAs with various initial microstructures” International Journal of Hydrogen Energy, Volume 35, Issue 23, pp. 12888-12896 (2010)
- [280] Soowhan Kim, Manish Khandelwal, Charles Chacko, and Matthew Mench, “Two-dimensional Anisotropic Interfacial Delamination Model for Polymer Electrolyte Fuel Cell Performance Loss” The Electrochemical Society Transactions, Volume 16, Issue 2, pp. 1977-1986 (2008)
- [281] X. G. Yang, Y. Tabuchi, F. Kagami, and Chao-Yang Wang, “Durability of Membrane Electrode Assemblies under Polymer Electrolyte Fuel Cell Cold-Start Cycling” The Journal of Electrochemical Society, Volume 155, Issue 7, pp. B752-B761 (2008)
- [282] Suhao He and Matthew M. Mench, “One-Dimensional Transient Model for Frost Heave in Polymer Electrolyte Fuel Cells” The Journal of Electrochemical Society, Volume 153, Issue 9, pp. A1724- A1731 (2006)
- [283] Matthew Mench and Suhao He, “Computational Model of Physical Damage during Freeze/Thaw of PEFCs” The Journal of Electrochemical Society, Volume 153, Issue 1, pp. 897-907 (2006)
- [284] Shanhai Ge and Chao-Yang Wang, “Cyclic Voltammetry Study of Ice Formation in the PEFC Catalyst Layer during Cold Start” The Journal of Electrochemical Society, Volume 154, Issue 12, pp. B1399-B1406 (2007)
- [285] Hiroshima Yoshida, Yuka Miura, “Behavior of water in perfluorinated ionomer membranes containing various monovalent cations” Journal of Membrane Science, Volume 68, Issues 1-2, pp. 1-10 (1992)
- [286] Zijie Lu, Georgios Polizos, Digby D. Macdonald, and E. Manias, “State of Water in Perfluorosulfonic Ionomer (Nafion 117) Proton Exchange Membranes” The Journal of Electrochemical Society, Volume 155, Issue 2, pp. B163-B171 (2008)
- [287] Shanhai Ge and Chao-Yang Wang, “In Situ Imaging of Liquid Water and Ice Formation in an Operating PEFC during Cold Start” Electrochemical Solid-State Letters, Volume 9, Issue 11, pp. A499-A503 (2006)
- [288] Shanhai Ge, Chao-Yang Wang, “Characteristics of subzero startup and water/ice formation on the catalyst layer in a polymer electrolyte fuel cell” Electrochimica Acta, Volume 52, Issue 14, pp. 4825-4835 (2007)
- [289] Y. Ishikawa, T. Morita, K. Nakata, K. Yoshida, M. Shiozawa, “Behavior of water below the freezing point in PEFCs” Journal of Power Sources, Volume 163, Issue 2, pp. 708-712 (2007)

- [290] Yuji Ishikawa, Tohru Morita, Keiichi Nakata, Kazuhiko Yoshida, and Masahiro Shiozawa, "Verification of Generated Water in a Super-cooled State Below Freezing Point in PEFC" *Electrochemical Society Transactions*, Volume 1, Issue 6, pp. 359-364 (2006)
- [291] Morihiro Saito, Kikuko Hayamizu, and Tatsuhiro Okada, "Temperature Dependence of Ion and Water Transport in Perfluorinated Ionomer Membranes for Fuel Cells" *The Journal of Physical Chemistry B*, Volume 109, Issue 8, pp. 3112-3119 (2005)
- [292] R. Mukundan, Yu Seung Kim, F. H. Garzon, and Bryan Pivovar, "Freeze/Thaw Effects in PEM Fuel Cells" *The Electrochemical Society Transactions*, Volume 1, Issue 8, pp. 403-413 (2006)
- [293] McDonald, R. C., Mittelsteadt, C. K., & Thompson, E. L. "Effects on deep temperature cycling on nafion [R] 112 membranes and membrane electrode assemblies" *Fuel Cells*, Volume 4, Issue 3, pp. 208-213 (2004)
- [294] Kevin G. Gallagher, Bryan S. Pivovar, and Thomas F. Fuller, "Electro-osmosis and Water Uptake in Polymer Electrolytes in Equilibrium with Water Vapor at Low Temperatures" *The Journal of Electrochemical Society*, Volume 156, Issue 3, pp. B330-B338 (2009)
- [295] Akihiko Koiwai, Atsushi Kamiya, and Masaya Kawasumi, "Study on Water Content of Perfluorosulfonic Acid Ionomer Membranes Below Water Freezing Point" *Electrochemical Society Transactions*, Volume 11, Issue 1, pp. 587-593 (2007)
- [296] Ahmet Kusoglu, Anette Karlsson, Michael Santare, Simon Cleghorn, and William B. Johnson, "Investigation of Stress and Water Distribution in Membrane Electrode Assembly (MEA) During Fuel Cell Operation" *The Electrochemical Society Transactions*, Volume 16, Issue 2, pp. 551-561 (2008)
- [297] Hossein Ghassemi, Ram Subbaraman, Christopher Brockman, Brandon Pyle, and Thomas Zawodzinski, "Proton Exchange Membrane Based on Sulfonated Polyethersulfone for H₂/Air and Direct Methanol Fuel Cells" *Electrochemical Society Transactions*, Volume 16, Issue 2, pp. 689-697 (2008)
- [298] Jason B. Ballengee and Peter Pintauro, "Nanofiber-Based Composite Membranes for Fuel Cells" *Electrochemical Society Transactions*, Volume 41, Issue 1, pp. 1507-1516 (2011)
- [299] Jinhui Pang, Haibo Zhang, Xuefeng Li, Dianfu Ren and Zhenhua Jiang, "Low Water Swelling and High Proton Conducting Sulfonated Poly(arylene ether) with Pendant Sulfoalkyl Groups for Proton Exchange Membranes" *Macromolecular Rapid Communications*, Volume 28, Issue 24, pp. 2332–2338 (2007)
- [300] Z. Zhu, N. M. Walsby, H. M. Colquhoun, D. Thompsett, E. Petrucco, "Microblock Ionomers: A New Concept in High Temperature, Swelling-Resistant Membranes for PEM Fuel Cells" *Fuel Cells*, Volume 9, Issue 4, pp. 305–317 (2009)
- [301] M. A. Navarra, A. Farnicola, S. Panero, and B. Scrosati, "Composite Gel-Type Proton Membranes" *Journal of The Electrochemical Society*, Volume 153, Issue 7, pp. A1284-A1289 (2006)
- [302] M. A. Navarra, S. Panero, and B. Scrosati, "Novel, Ionic-Liquid-Based, Gel-Type Proton Membranes" *Electrochemical and Solid-State Letters*, Volume 8, Issue 6, pp. A324-A327 (2005)
- [303] A. Martinelli, A. Matic, P. Jacobsson, L. Börjesson, M. A. Navarra, S. Panero, and B. Scrosati, "A Structural Study on Ionic-Liquid-Based Polymer Electrolyte Membranes" *Journal of The Electrochemical Society*, Volume 154, Issue 8, pp. G183-G187 (2007)
- [304] Xin Wang, Wenzhen Li, Zhongwei Chen, Mahesh Waje, Yushan Yan, "Durability investigation of carbon nanotube as catalyst support for proton exchange membrane fuel cell" *Journal of Power Sources*, Volume 158, Issue 1, pp. 154-159 (2006)
- [305] Sheng-Yang Huang, Prabhu Ganesan, Won Suk Jung, Nicholas Cadirov, and Branko N. Popov, "Titania Supported Platinum Catalyst with High Electrocatalytic Activity and Stability for Polymer Electrolyte Membrane Fuel Cell" *The Electrochemical Society Transactions*, Volume 33, Issue 1, pp. 483-491 (2010)

- [306] Mike L. Perry, Timothy Patterson, and Carl Reiser, "Systems Strategies to Mitigate Carbon Corrosion in Fuel Cells" *The Electrochemical Society Transactions*, Volume 3, Issue 1, pp. 783-795 (2006)
- [307] S. Vinod Selvaganesh, G. Selvarani, P. Sridhar, S. Pitchumani, and A. K. Shukla, "A Durable PEFC with Carbon-Supported Pt-TiO₂ Cathode: A Cause and Effect Study" *Journal of the Electrochemical Society*, Volume 157, Issue 7, pp. B1000- B1007 (2010)
- [308] Satheesh Sambandam, Vinodh Valluri, Wilaiwan Chanmanee, Normar De Tacconi, Wesley A Wampler, Wen-Yuan Lin, Thomas F Carlson, Vijay Ramani, Krishnan Rajeshwar, "Platinum-carbon black-titanium dioxide nanocomposite electrocatalysts for fuel cell applications" *Journal of Chemical Science*, Vol. 121, Issue 5, pp. 655–664 (2009)
- [309] H. Li, K. Lee, J. Zhang, "PEM Fuel Cell Electrocatalysts and Catalyst Layers", *Fundamentals and Applications*, pp. 135-163, 1st Edition. ISBN 978-1-84800-935-6 (2008)
- [310] Madhusudhana R. Dowlapalli, Plamen Atanassov, Jian Xie, and Gordon Rice, "Electrochemical Oxidation Resistance of Carbonaceous Materials" *The Electrochemical Society Transactions*, Volume 1, Issue 8, pp. 41-50 (2006)
- [311] Tatsuhiko Okada, Mikio Sugiura, and Gang Xie, "Degradation of Carbon Supported Pt Anode and Cathode Catalysts in PEM Fuel Cells" *The Electrochemical Society Transactions*, Volume 3, Issue 1, pp. 667-676 (2006)
- [312] J. Jayaraj, Y.C. Kim, K.B. Kim, H.K. Seok, E. Fleury, "Corrosion studies on Fe-based amorphous alloys in simulated PEM fuel cell environment" *Science and Technology of Advanced Materials*, Volume 6, Issues 3-4, pp. 282-289 (2005)
- [313] Rujin Tian, Juncai Sun, "Corrosion resistance and interfacial contact resistance of TiN coated 316L bipolar plates for proton exchange membrane fuel cell" *International Journal of Hydrogen Energy*, Volume 36, Issue 11, pp. 6788-6794 (2011)
- [314] M.P. Brady, H. Wang, J.A. Turner, H.M. Meyer III, K.L. More, P.F. Tortorelli, B.D. McCarthy, "Pre-oxidized and nitrided stainless steel alloy foil for proton exchange membrane fuel cell bipolar plates: Part 1. Corrosion, interfacial contact resistance, and surface structure" *Journal of Power Sources*, Volume 195, Issue 17, pp. 5610-5618 (2010)
- [315] Shine Joseph, J.C. McClure, P.J. Sebastian, J. Moreira, Edgar Valenzuela, "Polyaniline and polypyrrole coatings on aluminum for PEM fuel cell bipolar plates" *Journal of Power Sources*, Volume 177, Issue 1, pp. 161-166 (2008)
- [316] Shuo-Jen Lee, Ching-Han Huang, Yu-Pang Chen, "Investigation of PVD coating on corrosion resistance of metallic bipolar plates in PEM fuel cell" *Journal of Materials Processing Technology*, Volume 140, Issues 1-3, pp. 688-693 (2003)
- [317] J Wind, R Späh, W Kaiser, G Böhm, "Metallic bipolar plates for PEM fuel cells" *Journal of Power Sources*, Volume 105, Issue 2, pp. 256-260 (2002)
- [318] Xuan Cheng, Zheng Shi, Nancy Glass, Lu Zhang, Jiujun Zhang, Datong Song, Zhong-Sheng Liu, Haijiang Wang, Jun Shen, "A review of PEM hydrogen fuel cell contamination: Impacts, mechanisms, and mitigation" *Journal of Power Sources*, Volume 165, Issue 2, pp. 739-756 (2007)
- [319] Shucheng Sun, Hongmei Yu, Junbo Hou, Zhigang Shao, Baolian Yi, Pingwen Ming, Zho, "Catalytic hydrogen/oxygen reaction assisted the proton exchange membrane fuel cell (PEMFC) startup at subzero temperature" *Journal of Power Sources*, Volume 177, Issue 1, pp. 137-141 (2008)
- [320] Kui Jiao, Ibrahim E. Alaeifour, Gholamreza Karimi, Xianguo Li, "Simultaneous measurement of current and temperature distributions in a proton exchange membrane fuel cell during cold start processes" *Electrochimica Acta*, Volume 56, Issue 8, pp. 2967-2982 (2011)

[321] Junbo Hou, Hongmei Yu, Shengsheng Zhang, Shucheng Sun, Hongwei Wang, Baolian Yi, Pingwen Ming, “Analysis of PEMFC freeze degradation at -20°C after gas purging” *Journal of Power Sources*, Volume 162, Issue 1, pp. 513-520 (2006)

[322] Sang-Yeop Lee, Sang-Uk Kim, Hyoung-Juhn Kim, Jong Hyun Jang, In-Hwan Oh, Eun Ae Cho, Seong-Ahn Hong, Jaejun Ko, Tae-Won Lim, Kwan-Young Lee, Tae-Hoon Lim, “Water removal characteristics of proton exchange membrane fuel cells using a dry gas purging method” *Journal of Power Sources*, Volume 180, Issue 2, pp. 784-790 (2008)

[323] G. Gavello, J. Zeng, C. Francia, U.A. Icardi, A. Graizzaro, S. Specchia, “Experimental studies on Nafion® 112 single PEM-FCs exposed to freezing conditions” *International Journal of Hydrogen Energy*, Volume 36, Issue 13, pp. 8070-8081 (2011)

[324] Kah-Young Song, Hee-Tak Kim, “Effect of air purging and dry operation on durability of PEMFC under freeze/thaw cycles” *International Journal of Hydrogen Energy*, Volume 36, Issue 19, pp. 12417-12426 (2011)

[325] EunAe Cho, Jae-Joon Ko, Heung Yong Ha, Seong-Ahn Hong, Kwan-Young Lee, Tae-Won Lim, and In-Hwan Oh, “Effects of Water Removal on the Performance Degradation of PEMFCs Repetitively Brought to $<0^{\circ}\text{C}$ ” *The Journal of Electrochemical Society*, Volume 151, Issue 5, pp. A661-A665 (2004)

[326] Liang Wang, Ajay K. Prasad, and Suresh G. Advani, “Freeze/Thaw Durability Study of MWCNT-Reinforced Nafion Membranes”, *Journal of the Electrochemical Society*, Volume 158, Issue 12, pp. B1499-B1503 (2011)

[327] Wei Song, Hongmei Yu, Lixing Hao, Baolian Yi, Zhigang Shao, “Effect of catalytic ink on sub-freezing endurance of PEMFCs” *International Journal of Hydrogen Energy*, Volume 35, Issue 20, pp. 11129-11137 (2010)

[328] S. Roy and M. E. Orazem, “Stochastic Analysis of Flooding in PEM Fuel Cells by Electrochemical Impedance Spectroscopy” *Electrochemical Society Transactions*, Volume 11, Issue 1, pp. 485-495 (2007)

[329] Ion C. Halalay, Swathy Swathirajan, Belabbes Merzougui, Michael P. Balogh, Gregory C. Garabedian, and Michael K. Carpenter, “Anode Materials for Mitigating Hydrogen Starvation Effects in PEM Fuel Cells” *Journal of Electrochemical Society*, Volume 158, Issue 3, pp. B313-B321 (2011)

[330] Jing Li, Ping He, Keping Wang, Mike Davis, and Siyu Ye, “Characterization of Catalyst Layer Structural Changes in PEMFC as a Function of Durability Testing” *The Electrochemical Society Transactions*, Volume 3, Issue 1, pp. 743-751 (2006)

[331] Keun-Hwan Oh, Wan-Keun Kim, Kyung A. Sung, Min-Ju Choo, Kwan-Woo Nam, Jang Wook Choi, Jung-Ki Park, “A hydrophobic blend binder for anti-water flooding of cathode catalyst layers in polymer electrolyte membrane fuel cells” *International Journal of Hydrogen Energy*, Volume 36, Issue 21, pp. 13695-13702 (2011)

[332] Aidan Li, Siew Hwa Chan, Nam-trung Nguyen, “Anti-flooding cathode catalyst layer for high performance PEM fuel cell” *Electrochemistry Communications*, Volume 11, Issue 4, pp. 897-900 (2009)

[333] Guangyu Lin and Trung Van Nguyen, “Effect of Thickness and Hydrophobic Polymer Content of the Gas Diffusion Layer on Electrode Flooding Level in a PEMFC” *The Journal of Electrochemical Society*, Volume 152, Issue 10, pp. A1942-A1948 (2005)

[334] T. Colinart, S. Didierjean, O. Lottin, G. Maranzana, and C. Moyne, “Transport in PFSA Membranes” *Journal of the Electrochemical Society*, Volume 155, Issue 3, pp. B244-B257 (2008)

[335] T. Colinart, A. Chenu, S. Didierjean, O. Lottin, S. Besse, “Experimental study on water transport coefficient in Proton Exchange Membrane Fuel Cell” *Journal of Power Sources*, Volume 190, Issue 2, pp. 230-240 (2009)

[336] G. S. Hwang, M. Kaviany, J. H. Nam, M. H. Kim, and S. Y. Son, “Pore-Water Morphological Transitions in Polymer Electrolyte of a Fuel Cell”, *Journal of the Electrochemical Society*, Volume 156, pp. B1192- (2009)

- [337] J. Ramousse, J. Deseure, O. Lottin, S. Didierjean, D. Maillet, "Modelling of heat, mass and charge transfer in a PEMFC single cell" *Journal of Power Sources*, Volume 145, Issue 2, pp. 416-427 (2005)
- [338] N.P. Siegel, M.W. Ellis, D.J. Nelson, M.R. von Spakovsky, "A two-dimensional computational model of a PEMFC with liquid water transport" *Journal of Power Sources*, Volume 128, Issue 2, pp. 173-184(2004)
- [339] G.J.M Janssen, M.L.J Overvelde, "Water transport in the proton-exchange-membrane fuel cell: measurements of the effective drag coefficient", *Journal of Power Sources*, Volume 101, Issue 1, pp. 117-125 (2001)
- [340] Hiroyuki Uchida, Makoto Aoki, and Masahiro Watanabe, "New Evaluation Method for Degradation Rate of Polymer Electrolytes" *The Electrochemical Society Transactions*, Volume 3, Issue 1, pp. 485-492 (2006)
- [341] Wen Liu and S. Cleghorn, "Effect of Relative Humidity on Membrane Durability in PEM Fuel Cells" *The Electrochemical Transactions*, Volume 1, Issue 8, pp. 263-273 (2006)
- [342] Thor Anders Aarhaug, Ann Mari Svensson, Axel Baumann Ofstad, Jan Gregor Høydahl Sørli, and Héloïse Couvert, "PEMFC Degradation Assessed by Effluent Analysis from Designed Experiments", *The Electrochemical Society Transactions*, Volume 16, Issue 2, pp. 1687-1695 (2008)
- [343] Jae Hong Kim, Yoo Yeon Jo, Eun Ae Cho, Jong Hyun Jang, Hyoung Juhn Kim, Tae-Hoon Lim, In-Hwan Oh, Jae Jun Ko, and Ik Jae Son, "Effects of Cathode Inlet Relative Humidity on PEMFC Durability during Startup–Shutdown Cycling" *Journal of The Electrochemical Society*, Volume 157, Issue 5, pp. B633-B642 (2010)
- [344] Gang Luo, Yan Ji, Chao-Yang Wang, Puneet K. Sinha, "Modeling liquid water transport in gas diffusion layers by topologically equivalent pore network" *Electrochimica Acta*, Volume 55, Issue 19, pp. 5332-5341 (2010)
- [345] Yan Ji, Gang Luo, and Chao-Yang Wang, "Pore-Level Liquid Water Transport Through Composite Diffusion Media of PEMFC" *Journal of The Electrochemical Society*, Volume 157, Issue 12, pp. B1753-B1761 (2010)
- [346] A. Casalegno, L. Colombo, S. Galbiati, R. Marchesi, "Quantitative characterization of water transport and flooding in the diffusion layers of polymer electrolyte fuel cells" *Journal of Power Sources*, Volume 195, Issue 13, pp. 4143-4148 (2010)
- [347] Chaozhong Qin, Dirk Rensink, Stephan Fell, S. Majid Hassanizadeh, "Two-phase flow modeling for the cathode side of a polymer electrolyte fuel cell" *Journal of Power Sources*, Volume 197, pp. 136-144 (2012)
- [348] M. Acosta, C. Merten, G. Eigenberger, H. Class, R. Helmig, B. Thoben, H. Müller-Steinhagen, "Modeling non-isothermal two-phase multicomponent flow in the cathode of PEM fuel cells" *Journal of Power Sources*, Volume 159, Issue 2, pp. 1123-1141 (2006)
- [349] J.P. Feser, A.K. Prasad, S.G. Advani, "Experimental characterization of in-plane permeability of gas diffusion layers" *Journal of Power Sources*, Volume 162, Issue 2, pp. 1226-1231 (2006)
- [350] Guangli He, Pingwen Ming, Zongchang Zhao, Abuliti Abudula, Yu Xiao , "A two-fluid model for two-phase flow in PEMFCs" *Journal of Power Sources*, Volume 163, Issue 2, pp. 864-873(2007)
- [351] Yun Wang, Sungchan Cho, Ralf Thiedmann, Volker Schmidt, Werner Lehnert, Xuhui Feng, "Stochastic modeling and direct simulation of the diffusion media for polymer electrolyte fuel cells" *International Journal of Heat and Mass Transfer*, Volume 53, Issues 5–6, pp. 1128-1138 (2010)
- [352] A. Casalegno, F. Bresciani, G. Groppi, R. Marchesi, "Flooding of the diffusion layer in a polymer electrolyte fuel cell: Experimental and modelling analysis" *Journal of Power Sources*, Volume 196, Issue 24, pp. 10632-10639 (2011)

[353] Jeff T. Gostick, Marios A. Ioannidis, Michael W. Fowler, Mark D. Pritzker, “Pore network modeling of fibrous gas diffusion layers for polymer electrolyte membrane fuel cells” *Journal of Power Sources*, Volume 173, Issue 1, pp. 277-290 (2007)

[354] Puneet K. Sinha, Chao-Yang Wang, “Pore-network modeling of liquid water transport in gas diffusion layer of a polymer electrolyte fuel cell” *Electrochimica Acta*, Volume 52, Issue 28, pp. 7936-7945 (2007)

[355] A. Kopanidis, A. Theodorakakos, M. Gavaises, D. Bouris, “Pore scale 3D modelling of heat and mass transfer in the gas diffusion layer and cathode channel of a PEM fuel cell” *International Journal of Thermal Sciences*, Volume 50, Issue 4, pp. 456-467 (2011)

[356] Y. Ding, H.T. Bi, D.P. Wilkinson, “Three dimensional numerical simulation of gas–liquid two-phase flow patterns in a polymer–electrolyte membrane fuel cells gas flow channel” *Journal of Power Sources*, Volume 196, Issue 15, pp. 6284-6292 (2011)

[357] Jürgen Becker, Christian Wieser, Stephan Fell, Konrad Steiner, “A multi-scale approach to material modeling of fuel cell diffusion media” *International Journal of Heat and Mass Transfer*, Volume 54, Issues 7–8, pp. 1360-1368 (2011)

[358] Tetsuya Koido, Toru Furusawa, Koji Moriyama, “An approach to modeling two-phase transport in the gas diffusion layer of a proton exchange membrane fuel cell” *Journal of Power Sources*, Volume 175, Issue 1, pp. 127-136 (2008)

[359] W. K. Liu, S. J. C. Cleghorn, B. E. Delaney, and M. Crum, “Chemical and mechanical membrane degradation”, *Handbook of fuel cells: fundamentals, technology, and applications. Advances in electrocatalysis, materials, diagnostics and durability*: Chapter 26, ISBN: 978-0-470-72311-1 (2009)

[360] A. Pozio, R.F. Silva, M. De Francesco, L. Giorgi, “Nafion degradation in PEFCs from end plate iron contamination” *Electrochimica Acta*, Volume 48, Issue 11, pp. 1543-1549 (2003)

[361] Panagiotis Trogadas, Javier Parrondo, and V. Ramani, “Degradation Mitigation in Polymer Electrolyte Membranes using Free Radical Scavengers” *The Electrochemical Society Transactions*, Volume 16, Issue 2, pp.1725-1733 (2008)

[362] More, K. L. “VII.I.2 Microstructural Characterization of Polymer Electrolyte Membrane Fuel Cell (PEMFC) Membrane Electrode Assemblies (MEAs)”, DOE Hydrogen Program FY 2005 Progress Report

[363] More, K. L. “IV.I.2 Microstructural Characterization of Polymer Electrolyte Membrane Fuel Cell (PEMFC) Membrane Electrode Assemblies (MEAs)”, DOE Hydrogen Program FY 2004 Progress Report